



Photodesorption of specific organic compounds from titanium dioxide particles in aqueous media

Mohammad Shahid^a, Ibrahim El Saliby^a, Andrew McDonagh^b, Jong-Ho Kim^c,
Ho Kyong Shon^{a,*}

^a*School of Civil and Environmental Engineering, University of Technology, Sydney (UTS), P.O. Box 123, Broadway, NSW 2007, Australia*

Email: Hokyong.Shon-1@uts.edu.au

^b*School of Chemistry and Forensic Science, University of Technology, Sydney (UTS), P.O. Box 123, Broadway, NSW 2007, Australia*

^c*The Research Institute for Catalysis, Chonnam National University, Gwangju 500-757, South Korea*

Received 21 February 2013; Accepted 18 March 2013

ABSTRACT

This study investigates the photodesorption of organic compounds (beef extract, peptone, humic acid, tannic acid, sodium lignin sulphonate, sodium lauryl sulphate, arabic gum powder and arabic acid) from TiO₂ (1 g/L in water, pH 7). After a period to reach adsorption equilibrium, photodesorption experiments were conducted in a recirculated reactor at a constant flow rate of 150 mL/min with a UV light intensity of 24 W. Photodesorption was observed only for sodium lauryl sulphate (50%), sodium lignin sulphonate (43.47%), beef extract (20.35%) and tannic acid (10.5%) indicating that photodesorption is specific to some organic compounds but not to all. Using liquid chromatography-organic carbon detection, untreated beef extract and sodium lignin sulphonate were found to contain significant amounts of humic substances (~1,000 g/mol), which decreased in concentration after dark phase adsorption, while a significant increase in low molecular weight (<350 g/mol) concentrations was observed after photodesorption. UV-treated sodium lauryl sulphate photodesorbed to give both higher molecular weight (HMW) and lower molecular weight (LMW) organics. Thus, the HMW fractions of organic compounds decomposed into smaller compounds after UV irradiation, which subsequently desorbed from TiO₂ surface. However, untreated tannic acid contained a larger proportion of LMW acids, which shows a high adsorption affinity to TiO₂ during adsorption and poorly desorbs upon irradiation.

Keywords: Adsorption; Dissolved organic carbon; Organic compounds; Photodesorption; Titanium dioxide

*Corresponding author.

Presented at the Fifth Annual International Conference on “Challenges in Environmental Science & Engineering—CESE 2012” Melbourne, Australia, 9–13 September 2012

1. Introduction

Photo-induced desorption of DOC from TiO₂ particles in aqueous media can be initiated by UV illumination of the suspension for a short period of time. This phenomenon has potential applications in water treatment as it significantly reduces process times and facilitates the regeneration of the adsorbent with low energy consumption. It has been proposed that photodesorption of DOC from TiO₂ in synthetic waste water (SWW) [1] involves a significantly reduced affinity between the photocatalyst and organic pollutants upon illumination, leading to the detachment of adsorbed pollutants [2–5]. The photo-desorption effect strongly depends on the nature of organic compounds and their constituents. A recent study by El Saliby et al. [1] involved the photodesorption of DOC using SWW, which is a complex blend of several organic and inorganic compounds. The organic constituents are beef extract (a mixture of peptides and amino acids, nucleotide fractions, organic acids, minerals and some vitamins [6]), peptone (an enzymatic digest of animal protein consisting of short polymers of amino acids linked by peptide bonds [7]), humic acid (a complex mixture of acids containing carboxyl and phenolated groups that behaves as a dibasic or occasionally a tribasic acid [8]), tannic acid (a polyphenolic compound containing hydroxyl groups that cross link to other compounds), sodium lauryl sulphate (an anionic orthosulphonate consisting of a 12-carbon chain attached to a sulphate group [9]), and gum arabic powder (a mixture of polysaccharides and glycoproteins [10,11]). The organic compounds in SWW can be classified as polysaccharides (as found in beef extract, arabic acid and arabic gum powder), proteins and amino acids (as found in beef extract and peptone) and depending on the functional group attached, humic acid, tannic acid and sodium lignin sulphonate can be classified as carboxylic and phenolic hydrocarbons, whereas sodium lauryl sulphate represents an organosulphate compound. However, in previous studies using SWW, the contributions from each of the individual components to photodesorption were unclear. The purpose of the current work is to elucidate the contributions from each of the individual components of SWW to the photodesorption process and to investigate aspects such as variations in the physical transport and chemical reactivity of different organic pollutants. Therefore, in this study, the photodesorption behaviour of individual organic constituents of SWW (such as beef extract, humic acid, tannic acid, acacia gum powder and arabic acid) is reported. In particular, DOC data collected after adsorption and UV light illumination are presented and discussed.

2. Experimental

2.1. Materials

Titanium dioxide (Degussa P25) is a mixed phase nanopowder with anatase, rutile and amorphous structures. It has a surface area of 50 m²/g and an apparent density of 130 kg/m³. Sodium hydroxide (97% w/w) was obtained from ChemSupply Pty Ltd and hydrochloric acid (37% v/v) from Scharlau Chemie S.A. The properties of individual organic compounds used in the photodesorption experiments can be found elsewhere [1]. Distilled water was used to prepare solutions.

2.2. Photoreactor set-up

A recirculating photoreactor set-up (as reported elsewhere [1]) was used to study the photodesorption of specific organic compounds. The reactor was exposed to a luminous source composed of three 8 W germicidal lamps (G8T5, Sankyo Denki Co.). The dominant wavelength is 254 nm and the light intensity is 3.6 mW/cm² [12]. Suspensions of TiO₂ and organic solutions in a dark adsorption tank were continuously stirred at 400 rpm using a magnetic stirrer (IKA, C-MAG, MS7). Influent was pumped through three columns by an adjustable flow FMI lab pump (Fluid metering, INC, USA, Model QD) through connection tubes (Masterflex, precision pump tube 06508–17) at a flow rate of 150 mL/min.

2.3. Photodesorption of dissolved organic matter

The DOC of SWW in previous studies was ~7 mg/L [1]. Hence, the photodesorption of individual organic compounds in the current work was studied by adjusting the DOC concentration to 7 mg/L using the individual compounds. Experiments were conducted at pH 7 using 1 g/L of TiO₂ catalyst at a flow rate of 150 mL/min and a light intensity of 24 W. After the addition of TiO₂ to the organic solution, the slurry was mixed with a magnetic stirrer at 400 rpm for 30 min for dark adsorption. Then, the slurry was pumped into the photoreactor columns and UVC lamps were switched on. Photodesorption rapidly started after illuminating the suspension with UV light. Slurry samples were collected at fixed time intervals, filtered through 0.45 μm regenerated cellulose filters (Whatman, UNIFLO) and analysed using a Multi N/C 3100 (Analytik Jena) DOC analyser. Organic matter was identified and classified using liquid chromatography-organic carbon detection (LC-OCD) and associated software (Model 8, DOC-Labor, Germany). Three replicate experiments for each specific organic compound were conducted.

2.4. Calculation of adsorption and photodesorption

The adsorption and desorption percentages were calculated as follows:

$$\text{Adsorption (\%)} = \frac{[C_0 - C_{\text{ads}}] \times 100}{C_0} \quad (1)$$

where C_0 is the DOC in mg/L at $t=0$, C_{ads} is the DOC at $t=30$ min.

$$\text{Photodesorption (\%)} = \frac{[C_{\text{des}} - C_{\text{ads}}] \times 100}{[C_0 - C_{\text{ads}}]} \quad (2)$$

where C_{des} is the DOC in mg/L at $t=33$ or 35 min (maximum photodesorption).

3. Results and discussion

3.1. Photodesorption of DOC

Beef extract, peptone, humic acid, tannic acid, sodium lignin sulphonate, sodium lauryl sulphate and Arabic acid were studied individually by adjusting the DOC to 7 mg/L at pH 7 and with a catalyst loading of 1 g/L (TiO_2). Three replicate experiments were conducted to obtain standard deviation and error obtained to be about 5%. As shown in Fig. 1, after allowing 30 min of dark phase adsorption, the DOC of tannic acid and beef extract was reduced by 97.25 and 42.79%, respectively, whereas the other organic compounds had adsorption ranging from 8 to 22%.

After adsorption in the dark, the influent was pumped into a photoreactor and illuminated with UVC light. Fig. 1 illustrates the detachment of sodium lauryl sulphate, sodium lignin sulphonate, beef extract and tannic acid from TiO_2 surfaces after UV light irradiation, indicated by an increase in the DOC immediately after irradiation.

In particular (see Fig. 2), photodesorption of sodium lauryl sulphate was 50% of the adsorbed fraction (14.73%), sodium lignin sulphonate (43.47% of adsorbed fraction), beef extract (20.35% of adsorbed fraction) and tannic acid (10.5% of adsorbed fraction). Arabic acid shows negligible photodesorption with extended UV exposure while desorption did not occur with peptone, humic acid and arabic gum powder.

3.2. Molecular weight distribution of organic compounds

LC-OCD experiments were used to investigate the molecular fraction of untreated, adsorbed and photo-desorbed organic compounds [13].

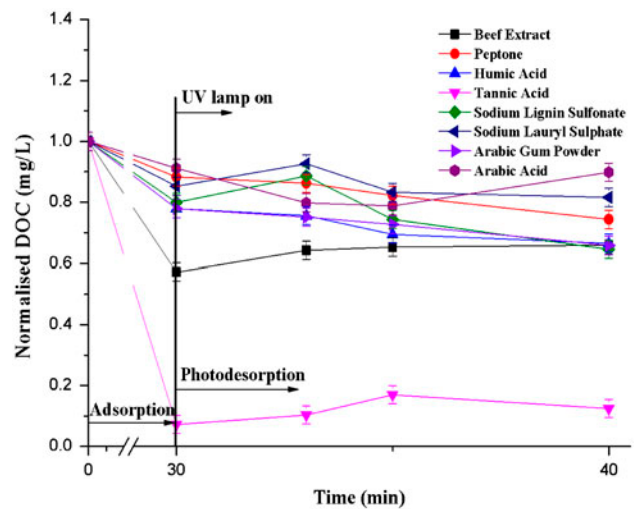


Fig. 1. Normalised rate of adsorption and photodesorption of DOC of individual organic compounds.

LC-OCD chromatograms of water containing beef extract, tannic acid, sodium lauryl sulphate and sodium lignin sulphonate are shown in Fig. 3. Table 1 shows the percentage of organic fractions of untreated, adsorbed and photodesorbed organic compounds as a function of the total DOC. The untreated beef extract and sodium lignin sulphonate solution (Fig. 3(a) and (b)) contain significant amounts of humic substances (~1,000 g/mol). After the dark adsorption phase, the amount of high molecular weight (HMW i.e. ~1,000 g/mol) species remaining in solution decreases. After photodesorption, the beef extract shows a significant increase in low molecular weight (LMW

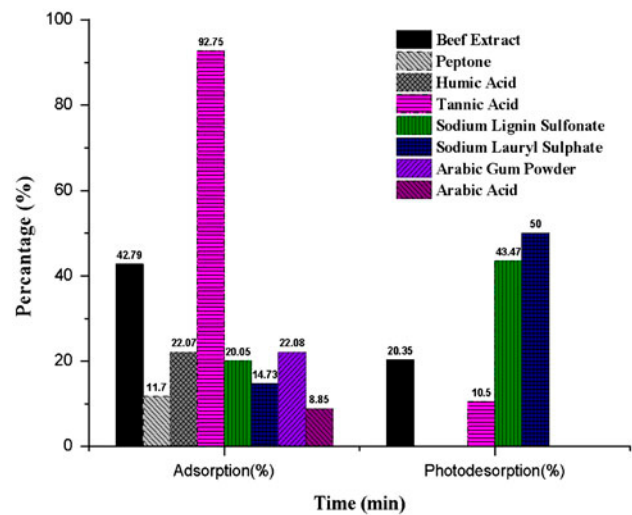


Fig. 2. Percentage of adsorption and photodesorption of several organic compounds.

i.e. <350 g/mol). Therefore, the process of adsorption/desorption converted a reasonable proportion of HMW organics into LMW organic material. This process also occurred to a lesser extent in the sodium lignin sulphonate sample. Shon et al. [3] reported similar findings after conducting a high performance size exclusion chromatography analysis on desorbed fractions. Desorption of LMW organics may be enhanced by the accumulation of negative charge on the TiO_2 surface upon irradiation [14].

In contrast, the LC-OCD chromatogram of UV-treated sodium lauryl sulphate (Fig. 3(c)) reveals the photodesorption of a larger fraction of both HMW and LMW organics. Upon UV irradiation, fractions of hydrophobic constituents of sodium lauryl sulphate degrade into hydrophilic species [15] by oxidation of carbon containing groups into carbonyl groups [16] which photodesorb (Table 1). However, the LC-OCD chromatograms

of untreated tannic acid (Fig. 3(d)) contained a larger proportion of LMW acids, which showed a high adsorption affinity to TiO_2 during dark phase adsorption and were found to poorly desorb upon irradiation. The photodesorption of HMW organic compounds such as beef extract, sodium lignin sulphonate and sodium lauryl sulphate was observed to be higher than the LMW tannic acid. Thus, the HMW fractions of organic compounds decomposed into smaller compounds after UV irradiation, which were subsequently desorbed from the TiO_2 surface.

4. Conclusions

The photodesorption of specific organic compounds with a DOC of 7 mg/L was investigated at pH 7 with a flow rate of 150 mL/min and a TiO_2

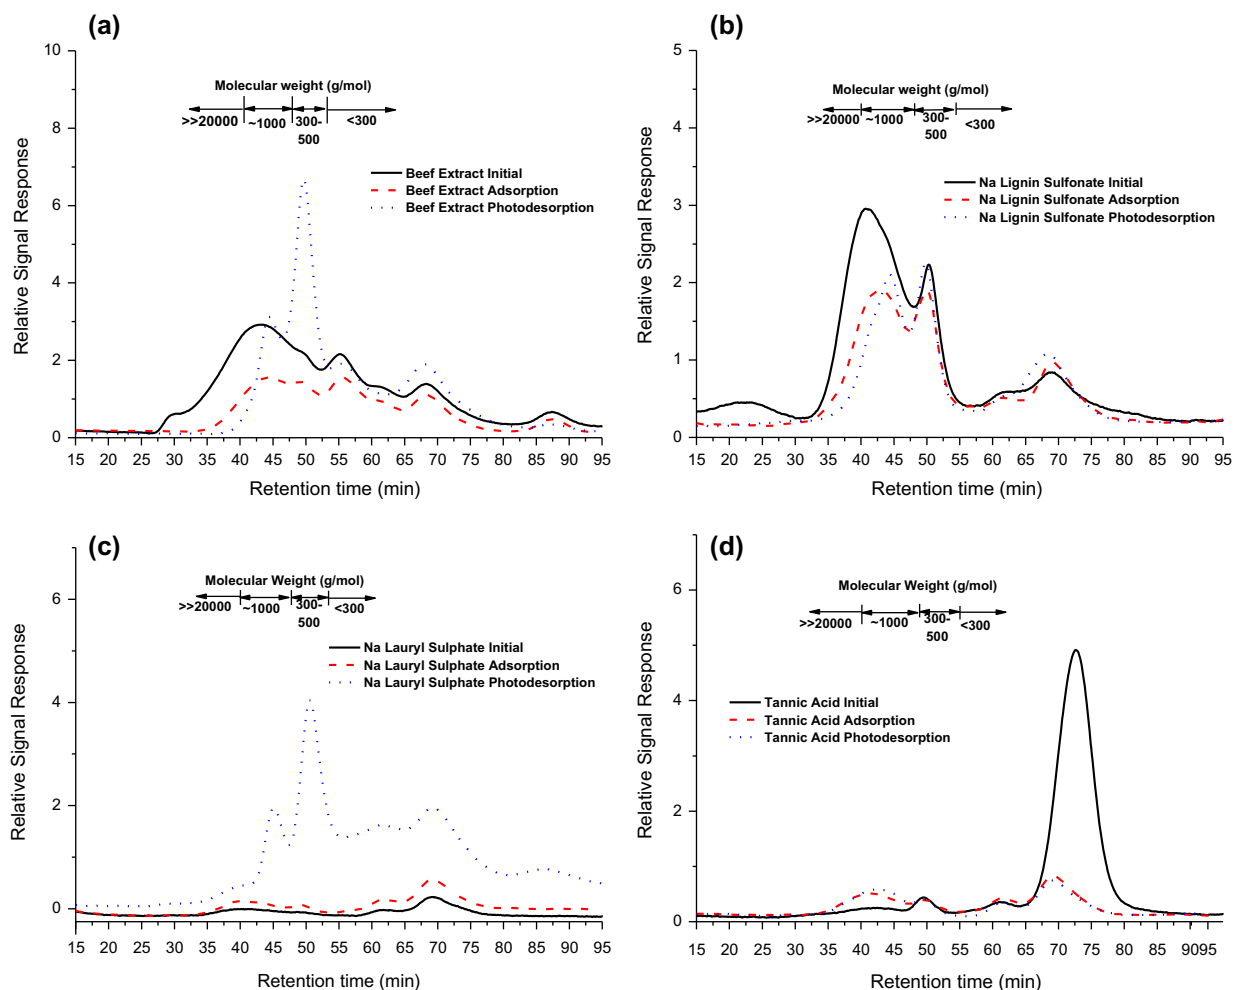


Fig. 3. LC-OCD chromatograms of DOM before treatment (black line), after adsorption (red line) and after photodesorption (blue line) for (a) Beef extract. (b) Sodium lignin sulphonate. (c) Sodium lauryl sulphate. (d) Tannic acid.

Table 1
LC-OCD fractionation results of organic compounds, after adsorption and photodesorption

Sample	Total DOC		Approximate molecular weight distribution (g/mol)					
	Dissolved (%)	Total DOC (%)	HOC			CDOC		
			Hydrophobic (%)	Hydrophilic (%)	>>20,000 Biopolymer (%)	-1,000 Humic substance (%)	300–500 Building blocks (%)	<350 LMW neutrals (%)
Beef extract initial	100	16.60	83.40	1.50	34.40	10.50	36.80	0.20
Beef extract adsorption	100	24.10	75.90	–	25.60	7.50	42.10	0.70
Beef extract photodesorption	100	25.00	75.00	1.40	17.90	9.80	35.60	10.40
Na lignin sulphonate initial	100	35.80	64.20	–	49.70	–	8.20	6.80
Na lignin sulphonate adsorption	100	52.60	47.40	0.30	25.30	4.70	12.10	4.90
Na lignin sulphonate photodesorption	100	33.40	66.60	5.70	25.90	2.20	25.40	7.30
Na lauryl sulphate initial	100	97.40	2.60	–	0.70	0.20	1.70	–
Na lauryl sulphate adsorption	100	95.70	4.30	–	1.00	0.30	2.90	0.10
Na lauryl sulphate photodesorption	100	63.40	36.60	1.10	5.70	6.70	23.00	0.10
Tannic acid initial	100	51.20	48.80	0.10	1.90	1.00	45.00	0.80
Tannic acid adsorption	100	51.70	48.30	–	16.10	1.90	28.60	1.70
Tannic acid photodesorption	100	67.40	32.60	1.30	12.50	0.70	16.50	1.50

catalyst loading of 1 g/L. Sodium lauryl sulphate, sodium lignin sulphonate and beef extract were found to be the major contributing organic compounds for photodesorption in terms of adsorption of DOC and efficiency of photodesorption. LC-OCD fractionation of untreated and adsorbed organics reflects adsorption of HMW organic particulate matter onto TiO₂. The LC-OCD results after UV illumination indicate photodesorption of LMW organic, specifically <500 Da organic. Hence, the HMW organics were decomposed into smaller ones, which were subsequently desorbed from the TiO₂ surface.

Acknowledgements

This research was funded by ARC-LP, a UTS internal grant and Australian Postgraduate Award Scholarship. This work was supported by Priority Research Centre Programmes through the National Research Foundation of Korea (NRF) funded by the Ministry of Education, Science and Technology (2009-0094055).

References

- [1] I. El Saliby, M. Shahid, A. McDonagh, H.K. Shon, J.-H. Kim, Photodesorption of organic matter from titanium dioxide particles in aqueous media, *J. Ind. Eng. Chem.* 18 (2012) 1774–1780.
- [2] R.B. Bjorklund, S. Karlsson, H. Borén, B. Allard, I. Lundström, Photodesorption of fulvic acid from iron oxide surfaces into aqueous solutions, *Appl. Surf. Sci.* 174 (2001) 167–175.
- [3] H.K. Shon, S. Vigneswaran, H.H. Ngo, J.H. Kim, Chemical coupling of photocatalysis with flocculation and adsorption in the removal of organic matter, *Water Res.* 39 (2005) 2549–2558.
- [4] L. Erdei, N. Arecrachakul, S. Vigneswaran, A combined photocatalytic slurry reactor-immersed membrane module system for advanced wastewater treatment, *Sep. Purif. Technol.* 62 (2008) 382–388.
- [5] Z. Ambrus, K. Mogyorosi, A. Szalai, T. Alapi, K. Demeter, A. Dombi, P. Sipos, Low temperature synthesis, characterization and substrate-dependent photocatalytic activity of nanocrystalline TiO₂ with tailor-made rutile to anatase ratio, *Appl. Catal., A: General* 340 (2008) 153–161.
- [6] A.A. Asif Durrani, S. Durrani, J.B. Shaikh, A. Upadhyay, Z.H. Khan, Non-animal peptone for serum free cultivation of recombinant mammalian and animal cells, *Int. J. Biol.* 3 (2011) 140–145.
- [7] J.W. Payne, M.W. Smith, Peptide transport by microorganisms, in: A.H. Rose, D.W. Tempest (Eds.), *Advances in Microbial Physiology*, Academic Press, London, 1994, pp. 1–80.
- [8] F.J. Stevenson, *Humus Chemistry — Genesis, Composition, Reactions*, Wiley, New York, 1982, pp. 443.
- [9] R.A. Tupker, C. Wills, E. Beradesca, H.C. Lee, M. Fartasch, J. Serup, Guidelines on sodium lauryl sulfate exposer tests. A report from the Stabilization Group of European Society of Contact Dermatitis, vol. 37(2), 1997, pp. 53–69.
- [10] D.M.W. Anderson, J.F. Stoddart, Studies on uronic acid materials: Part XV. The use of molecular-sieve chromatography in studies on acacia senegal gum (gum arabic), *Carbohydr. Res.* 2 (1996) 104–114.
- [11] C.A.A. Street, D.M.W. Anderson, Refinement of structures previously proposed for gum arabic and other acacia gum exudates, *Talanta* 30 (1983) 878–893.
- [12] D.S. Kim, Y.S. Park, Photocatalytic decolorization of rhodamine B by immobilized TiO₂ onto silicone sealant, *Chem. Eng. J.* 116 (2006) 133–137.
- [13] S.A. Huber, A. Balz, M. Abert, W. Pronk, Characterisation of aquatic humic and non-humic matter with size-exclusion chromatography—organic carbon detection—organic nitrogen detection (LC-OCD-OND), *Water Res.* 45 (2011) 879–885.
- [14] W.W. Dunn, Y. Aikawa, A.J. Bard, Characterization of particulate titanium dioxide photocatalysts by photoelectroretic and electrochemical measurements, *J. Am. Chem. Soc.* 103 (1981) 3456–3459.
- [15] Y. Ikeguchi, H. Nakamura, A novel method for the on-line room-temperature hydrolysis of hydrophobic organic phosphates using a cooperative action of sodium dodecyl sulfate, acid and UV-irradiation, *Anal. Sci.* 14 (1998) 815–817.
- [16] N.M. Panich, A.F. Seliverstov, B.G. Ershov, Photooxidative decomposition of sodium dodecyl sulfate in aqueous solutions, *Russ. J. Appl. Chem.* 81 (2008) 2104–2107.