



## Dual-sorption model for H<sub>2</sub>/CO<sub>2</sub> permeation in glassy polymeric Matrimid membrane

Oana Cristina David, Daniel Gorri, Inmaculada Ortiz, Ane Maria Urriaga\*

*Departamento de Ingeniería Química y Química Inorgánica, Universidad de Cantabria Avda. Los Castros s/n, 39005 Santander, Spain  
Tel. +34 942201587; email: ana.urriaga@unican.es*

Received 28 May 2010; Accepted 20 July 2010

### ABSTRACT

This work deals with the membrane separation of hydrogen and carbon dioxide. Permeation experiments of pure and binary mixtures of H<sub>2</sub> and CO<sub>2</sub> were performed using the constant pressure technique and a planar membrane made of the commercial polyimide Matrimid 5218. For pure gases permeability values of 23.4 Barrer for hydrogen and of 5.2 Barrer for carbon dioxide were obtained leading to an ideal selectivity of 4.5 at 6 bar feed pressure. In the case of gas mixtures, H<sub>2</sub> permeability decreases with increasing contents of CO<sub>2</sub>, while the permeability of carbon dioxide in mixtures presents similar values to pure gas permeabilities. As a result, the H<sub>2</sub>/CO<sub>2</sub> selectivity obtained from mixed gas experiments decays to an average value of 3. The dual-sorption model with a partial permeant immobilization was used to predict each component permeation behavior for pure gases and binary mixtures. The carbon dioxide diffusion coefficients through the Matrimid polymer in the Henry and Langmuir mode were obtained,  $D_{D,CO_2} = 2.14 \times 10^{-8}$  cm<sup>2</sup>/s and  $D_{H,CO_2} = 2.79 \times 10^{-9}$  cm<sup>2</sup>/s. The model and the estimated parameters provide a reasonable agreement between experimental data and predicted permeability values with correlation coefficient  $R^2 > 0.95$  and mean squared relative error (MSRE) lower than 0.01.

*Keywords:* Mixed gas separation; Matrimid membrane; Dual-sorption model

### 1. Introduction

The introduction of hydrogen economy requires the development of efficient means to separate and retrieve hydrogen [1]. Today hydrogen production on a large scale is mostly through the steam reforming of methane, followed by the water gas shift reaction [2,3]. In addition, alternative and renewable resources for hydrogen production are proposed [4–9]. These involve biomass, water and carbohydrates rich, nitrogen deficient wastes such as solid (cellulose, starch), agricultural and food wastes. In the case of water and waste, bioprocess technologies like biophotolysis and anaerobic fermentation

are being developed. The resulting product in all cases is a mixture of hydrogen with carbon dioxide and other minor gases. In spite of their high interest, the separation of hydrogen and carbon dioxide through membranes has not reached a commercial development. The main reason is related to the difficulty of combining a high hydrogen permeability and a low permeability to carbon dioxide.

For hydrogen separation, three types of materials can be used: inorganic-metallic, inorganic nano-porous (silica, ceramic, carbon, zeolite, oxide, glass) and organic polymeric membranes [10]. The choice between them must take into account the H<sub>2</sub> purity requirements for different applications and the temperature and pressure properties of the feed gas mixture. While fuel cell technology requires high purity hydrogen (minimum

\*Corresponding author.

99.99%), hydrogen used as feedstock for hydro-cracking requires only 70–80% purity. The process gases rich in hydrogen that come from a thermochemical production process are at high temperature (the temperature of the second step of WGS is of 190–210°C). In this case palladium alloys are investigated to obtain ultrapure hydrogen even though these metals are too costly and evidence surface contamination by sulfur containing species. Meanwhile the biohydrogen that comes from water biophotolysis and waste anaerobic fermentation is at low temperature. Polymeric membranes are preferred when the operating conditions permit their usage because of their important benefits over inorganic membranes (lower material and fabrication costs, ease of processability, and capacity of long-term operation). Glassy polymers are the preferred materials for H<sub>2</sub> selective membranes since their rigid structures provide the capacity to discriminate molecules according to their size variation [11].

From the literature data [12], one can conclude that membranes based on polyimides provide an excellent selectivity in the separation of H<sub>2</sub>/N<sub>2</sub>, H<sub>2</sub>/CH<sub>4</sub> and H<sub>2</sub>/CO. H<sub>2</sub>/CO<sub>2</sub> separation is more problematic, behavior assigned to the high solubility of carbon dioxide in polymers. Ideal H<sub>2</sub>/CO<sub>2</sub> selectivities are calculated as the ratio of pure gas permeabilities, regardless membrane properties can be severely affected by a mixture of complex composition as that encountered in most off-gas streams. On the other hand, a notable decrease in hydrogen permeability when separated from mixtures containing carbon dioxide is expected, since it is documented that the higher the carbon dioxide concentration in the gas mixture, the higher the importance of membrane plasticizing phenomena [13]. To this date, the majority of the work related to the functional characterization of membrane materials is still carried out in single gas experiments rather than with gas mixtures even though it is well accepted that single and mixed gas data will differ significantly [14].

In the present study, a commercial polyimide, Matrimid 5218, was chosen for the manufacturing of the membrane. This material has attracted a lot of attention for gas separation membranes due to the combination of relatively high gas permeability coefficients and separation factors coupled with excellent mechanical properties, solubility in non-hazard organic solvents and commercial availability [3]. The present study reports new gas permeability data for the commercially available and industrially applicable Matrimid 5218 membrane, related to gas mixtures of hydrogen and carbon dioxide and reveals specific phenomena to gas mixtures like solubility coupling and competitive sorption effects. Also, the “dual-mode sorption, partial immobilization” model was used to describe hydrogen and carbon dioxide permeation

behavior for pure and binary mixtures. In this way new transport properties related to real process conditions are revealed. A reasonable agreement between predicted results and experimental data allows the satisfactory use of the resulted model to predict transport behavior of hydrogen and carbon dioxide in real mixtures.

## 2. Theoretical background

The transport, i.e., permeability  $P$ , of a gas through a dense polymeric film can be described as a solution–diffusion mechanism where the solubility  $S$  is a thermodynamic parameter and the diffusivity  $D$  is a kinetic parameter, Eq. (1)

$$P = DS \quad (1)$$

Gas sorption and diffusion in glassy polymeric membranes has been described by several established models but the use of the “dual-mode sorption, partial immobilization” theory has been more prevalent [13]. According to the dual-mode sorption model, gas sorption ( $C_m$ ) in a polymer occurs in two types of sites, Henry and Langmuir sites, respectively. The first type is filled by gas molecules dissolved in the equilibrium free volume portion of the material (concentration  $C_D$ ) and the second one corresponds to the population dissolved in the excess free volume of the glassy polymer ( $C_H$ ) [12]. For a multicomponent gas mixture,

$$C_{m,i} = C_{D,i} + C_{H,i} = k_{D,i}p_i + \frac{c'_{H,i}b_i p_i}{1 + b_i p_i} \quad (2)$$

$$S_i \equiv \frac{C_{m,i}}{p_i} = k_{D,i} + \frac{c'_{H,i}b_i}{1 + b_i p_i} \quad (3)$$

where,  $p_i$  is the partial pressure and  $k_{D,i}$  represents the Henry law constant.  $c'_{H,i}$  is the Langmuir capacity constant that characterizes the total sorption capacity of the lower density regions (unrelaxed gaps) in a glassy polymer for a particular penetrant. The parameter  $b_i$  is the Langmuir affinity constant which characterizes the tendency of a given penetrant to sorb in the Langmuir mode. The primary effect for a mixture is the simple competition by the various penetrants for the excess free volume fraction of the polymer which causes a significant depression in sorption of all components of the mixture [13].

As a consequence of the existence of two types of adsorption sites in glassy polymeric membranes two diffusion coefficients can be defined.  $D_D$  is used for the mobility of the gas population dissolved in the polymer according to the Henry's law expression in

the equilibrium free volume of the polymer and  $D_H$  for the mobility of the gas population contained in the excess free volume. The Fick's law expression for flux ( $J$ ) through the membrane has the form:

$$J = -D_D \frac{dC_D}{dx} - D_H \frac{dC_H}{dx} \quad (4)$$

Substituting Eq. (2) into Eq. (4) and integrating from the high pressure to the low pressure across the membrane, one can get the permeability as follows, if  $D_D$  and  $D_H$  are constant and the downstream pressure is negligible [15].

$$P_i = k_{Di} \left( 1 + \frac{F_i K_i}{1 + \sum_{i=1}^n b_i p_i} \right) D_{Di} \quad (5)$$

where

$$K = \frac{c'_H b}{k_D} \quad (6)$$

$$F = \frac{D_H}{D_D} \quad (7)$$

and  $p$  is the feed side pressure,  $K$  is a concentration sorption parameter and  $F$  can be viewed as the moving fraction of the Langmuir's population and the value  $(1 - F)$  is always greater than 1.

Alternatively, Eq. (5) can be expressed in terms of component fugacity rather than partial pressures. The use of penetrant fugacity is clearly preferred as non-ideal gas phase mixture effects can be easily accounted for [16].

$$P_i = k_{Di} \left( 1 + \frac{F_i K_i}{1 + \sum_{i=1}^n b_i f_{2i}} \right) D_{Di} \quad (8)$$

By fitting Eq. (8) with mixed gas experimental data of permeability versus gas partial pressure one can obtain diffusivities for the Henry's law and Langmuir mode.

### 3. Experimental

The commercial polymer Matrimid 5218 (polyimide of 3,3',4,4'-benzophenone tetracarboxylic dianhydride and diamino-phenylidene) was provided by Huntsman Advanced Polymers in powder form. Gases were purchased from Air Liquide (Spain) with a purity of at least 99.95%.

Film membranes, based on the polyimide Matrimid 5218, were prepared. After drying of the polymer powder at 120°C for 12 h, polymeric solutions (10–15 wt.%) were prepared by using dichloromethane (Panreac) as solvent. Thin films with an average thickness of 50 μm were obtained by solution casting on a glass plate using a casting knife (Elcometer 3580). The cast films were dried first at room temperature for 24 h and next in a vacuum oven (Selecta Vaciotem-T) at 120°C for 24 h and 200 mbar. The membrane sample had an effective membrane area of 12.13 cm<sup>2</sup>.

Fig. 1 shows the permeation set-up used for the measurement of pure and binary mixtures (CO<sub>2</sub>, H<sub>2</sub>) gas permeabilities. The desired concentration of the feed mixture is obtained by controlling the flow rate of each gas with the mass flow controllers (Brooks 5850S). This gas mixture flows over the polymeric film mounted in the membrane test cell and leaves the system via the backpressure regulator (Brooks 5866). In the permeate side, where the pressure is maintained at atmospheric level the gas is removed with an argon sweep gas and introduced into a gas chromatograph (Agilent Micro GC 3000 – TCD detector), where the concentration of each component is determined.

For pure and mixed gas experiments, permeabilities  $P_i$  were calculated using Eq. (9)

$$P_i = \frac{Q_i \delta}{A \Delta p_i} \quad (9)$$

where  $Q_i$  is permeate flow rate for the component  $i$ ,  $\delta$  is the membrane thickness,  $A$  is the membrane area,  $\Delta p_i$  is the partial pressure gradient of component  $i$  through the membrane. Fugacities of the components were calculated using the Peng–Robinson equation. The separation factors were calculated as the ratio of permeabilities.

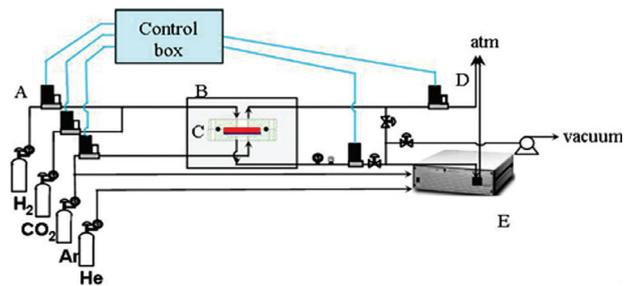


Fig. 1. The experimental permeation set-up: (A) Mass flow controller, (B) control box, (C) heating oven, (D) membrane test cell, (E) backpressure regulator and (F) gas chromatograph.

#### 4. Results and discussion

The transport of pure carbon dioxide and hydrogen was studied at 2, 4 and 6 bar feed pressure at a temperature of 30°C through Matrimid polymeric membrane. The resulting permeability values of 23.4 Barrer for hydrogen and 5.2 Barrer for carbon dioxide are in good correlation with literature data [17–20], Table 1, at a total feed pressure of 6 bar. As expected, hydrogen permeability presents a small decrease with pressure meanwhile the permeability of carbon dioxide presents a stronger decrease when pressure increases. Carbon dioxide transport is affected by pressure because is a more condensable gas and therefore more dependent of the solubility parameter that decreases when pressure increases. For pure gases the agreement with literature data validates the experimental procedure employed in this work.

In the case of binary gas mixtures of carbon dioxide with hydrogen a strong reduction in hydrogen permeability is observed with increasing values of CO<sub>2</sub> fugacity, as shown in Fig. 2. The depletion in H<sub>2</sub> permeability in the presence of CO<sub>2</sub> is related to the competitive sorption phenomenon between the two gases and is enhanced at increasing fugacity of CO<sub>2</sub> when more sorption of carbon dioxide in the Langmuir sites occurs because of carbon dioxide's larger affinity constant and solubility in glassy polymers. On the other hand, the permeability of H<sub>2</sub> is mostly independent on its own fugacity. For example, if we compare the experiments no. 2 and 8 collected in Table 1 (see also Fig. 2) where the CO<sub>2</sub> fugacity is kept practically constant (2.75 and 2.92 bar) and H<sub>2</sub> fugacity

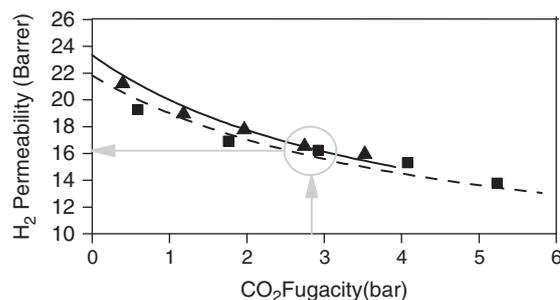


Fig. 2. H<sub>2</sub> Permeability vs. CO<sub>2</sub> fugacity obtained with feed binary mixtures H<sub>2</sub>/CO<sub>2</sub>, 30°C and Matrimid 5218 membrane. (▲) Experimental values of H<sub>2</sub> permeability,  $P_{\text{total}} = 4$  bar; (■) experimental values of H<sub>2</sub> permeability,  $P_{\text{total}} = 6$  bar; (---) model calculated values of H<sub>2</sub> permeability,  $P_{\text{total}} = 4$  bar; (—) model calculated values of H<sub>2</sub> permeability,  $P_{\text{total}} = 6$  bar.

changes from 1.21 to 3.02, the H<sub>2</sub> permeability is almost constant (16.7 and 16.4 Barrers, respectively).

As a consequence of the lower permeability of hydrogen in mixtures with carbon dioxide the real selectivity for the H<sub>2</sub>/CO<sub>2</sub> gas pair, calculated from permeability data obtained in mixed gas experiments, decreases to an average value of 3, in the range of pressures 2–6 bars.

The transport data of pure carbon dioxide and hydrogen and their binary gas mixtures were fitted to the “dual-sorption partial immobilization model”, Eq. (8), by nonlinear regression methods. To facilitate calculation, the gathering in smaller number of independent parameters was done as follows:

Table 1  
Pure gas and binary mixtures H<sub>2</sub> and CO<sub>2</sub> permeabilities through a Matrimid membrane

Total pressure (bar)	Pure gas			Mixed gas					
	Permeability (Barrer) <sup>a</sup>		Ideal selectivity H <sub>2</sub> /CO <sub>2</sub>	Exp. no.	Fugacity (bar)		Permeability (Barrer)		Selectivity H <sub>2</sub> /CO <sub>2</sub>
	H <sub>2</sub>	CO <sub>2</sub>			H <sub>2</sub>	CO <sub>2</sub>	H <sub>2</sub>	CO <sub>2</sub>	
2	24.4	6.1	4.0	–	–	–	–	–	–
				1	0.41	3.53	16.2	5.4	3.0
				2	1.21	2.75	16.7	5.5	3.0
4	24.0	5.5	4.4	3	2.01	1.97	17.9	5.8	3.1
				4	2.81	1.18	19.0	6.1	3.1
				5	3.60	0.40	21.2	6.9	3.1
				6	0.61	5.23	14.1	5.2	2.7
				7	1.82	4.08	15.3	5.3	2.9
6	23.4	5.2	4.5	8	3.02	2.92	16.4	5.5	3.0
				9	4.22	1.76	17.0	5.6	3.0
				10	5.41	0.59	19.3	6.2	3.1

<sup>a</sup>1 Barrer = 10<sup>-10</sup> cm<sup>3</sup>/s·cm/cm<sup>2</sup>/cmHg.

$$A_1 = k_D D_D \quad (10)$$

$$A_2 = k_D F K D_D = D_H c'_{Hb} \quad (11)$$

As a consequence the permeability parameters are defined as follows:

$$P_{H_2} = A_{1H_2} + \frac{A_{2H_2}}{1 + b_{H_2} f_{H_2} + b_{CO_2} f_{CO_2}} \quad (12)$$

$$P_{CO_2} = A_{1CO_2} + \frac{A_{2CO_2}}{1 + b_{H_2} f_{H_2} + b_{CO_2} f_{CO_2}} \quad (13)$$

The resulting system is composed of two equations with five independent parameters:  $A_{1H_2}$ ,  $A_{1CO_2}$ ,  $A_{2H_2}$ ,  $A_{2CO_2}$ ,  $b_{H_2}$ . Although the number of parameters is relatively high, the regression solution was unique due to the large domain of experimental data of permeability that in the case of  $P_{H_2}$  was in the range 13.7–24 Barrer. By substitution into Eqs. (10) and (11) of the known values of the sorption parameters of carbon dioxide in the Matrimid polymer [21]:  $C'_{HCO_2} = 25.5 \text{ cm}^3/\text{cm}^3$ ,  $b_{CO_2} = 0.367 \text{ 1/bar}$  and  $k_D = 1.42 \text{ cm}^3(\text{STP})/\text{cm}^3/\text{bar}$ , at  $35^\circ\text{C}$ , we obtained the values of the  $\text{CO}_2$  diffusion parameters in Henry mode  $D_{D,CO_2} = 2.14 \times 10^{-8} \text{ cm}^2/\text{s}$  and Langmuir mode  $2.79 \text{ E-}9 \text{ cm}^2/\text{s}$ . These results fall in the same order of magnitude as previously reported values for glassy polymers [22]. We did not encounter published data for hydrogen solubility in Matrimid and therefore the final results are expressed as the grouped parameters  $A_{1H_2} = 6.15 \text{ Barrer}$ ,  $A_{2H_2} = 21.31 \text{ Barrer}$  and  $b = 0.06 \text{ 1/bar}$ . There is a reasonable agreement between predicted permeability values and experimental data, with correlation coefficient ( $R$ ) higher than 0.95 and value of the mean squared relative error (MSRE) lower than 0.01, as it is exemplified by the plotted calculated lines shown in Fig. 2.

## 5. Conclusions

Pure gas permeability data are different from mixed gas permeability data. To be able to correctly design an industrial separation membrane system one should consider this aspect [12]. In the case of gas mixtures of hydrogen with carbon dioxide, hydrogen permeability is considerably lower than for pure gas meanwhile the permeability of carbon dioxide is unchanged resulting, therefore, an important decay in selectivity from an ideal value of 4.3 to a value of 3. This behavior was related to competitive sorption of the two gases in the polymer matrix and was satisfactorily described by the dual-sorption partial immobilization model. Therefore,

this model can be used when designing the separation process as a useful tool to predict the permeability values at different partial pressures of the species.

## Acknowledgements

Financial support from the Spanish Ministry of Education and Science under the projects: CTQ 2008–00690/PPQ, CTM 2006–00317 and ENE 2010–15585 is gratefully acknowledged. Oana C. David also thanks the Ministry of Education (Spain) for a postgraduate research grant.

## References

- [1] R.W. Baker, Future directions of membrane gas separation technology, *Indus. Eng. Chem. Res.*, 41 (2002) 1393–1411.
- [2] <http://www.hydrogen.energy.gov/production.html>
- [3] S. Shishatskiy, C. Nistor, M. Popa, S.P. Nunes and K.V. Peinemann, Polyimide asymmetric membranes for hydrogen separation: influence of formation conditions on gas transport properties, *Adv. Eng. Mater.*, 8 (5) (2006) 390–397.
- [4] R. Kothari, V.V. Tyagi and A. Pathak, Waste-to-energy: A way from renewable energy sources to sustainable development, *Renew. Sust. Energy Rev.*, 14 (9)(2010) X3164–3170.
- [5] X.M. Guo, E. Trably, E. Latrille, H. Carrère and J.-P. Steyer, Hydrogen production from agricultural waste by dark fermentation: a review, *Int. J. Hydrogen Energy*, 35 (19) (2010) 10660–10673.
- [6] D. Das, Advances in biohydrogen production processes: an approach towards commercialization, *Int. J. Hydrogen Energy*, 34 (17) (2009) 7349–7357.
- [7] A. Demirbas, Biofuels securing the planet's future energy needs, *Energy Convers. Manage.*, 50 (9) (2009) 2239–2249.
- [8] P.C. Hallenbeck, Fermentative hydrogen production: principles, progress, and prognosis, *Int. J. Hydrogen Energy*, 34 (17) (2009) 7379–7389.
- [9] M.-L. Chong, V. Sabaratnam, Y. Shirai and M.A. Hassan, Biohydrogen production from biomass and industrial wastes by dark fermentation, *Int. J. Hydrogen Energy*, 34 (8) (2009) 3277–3287.
- [10] J.W. Phair and S.P.S. Badwal, Materials for separation membranes in hydrogen and oxygen production and future power generation, *Sci. Tec. Adv. Mat.*, 7 (8) (2006) 792–805.
- [11] L. Shao, B.T. Low, T. Chung and A.R. Greenberg, Polymeric membranes for the hydrogen economy: contemporary approaches and prospects for the future, *J. Membr. Sci.*, 327 (2009) 18–31.
- [12] R. Baker, *Membrane Technology and Applications*, 2nd ed. Wiley, 2004.
- [13] W.J. Koros, A.H. Chan and D.R. Paul, Sorption and transport of various gases in polycarbonate, *J. Membr. Sci.*, 2 (1977) 165–190.
- [14] T. Visser and M. Wessling, Auto and mutual plasticization in single and mixed gas  $\text{C}_3$  transport through Matrimid-based hollow fiber membranes, *J. Membr. Sci.*, 312 (2008) 84–96.
- [15] W.J. Koros, D.R. Paul and A.A. Rocha, Carbon dioxide sorption and transport in polycarbonate, *J. Polym. Sci. Part A-2 Polym. Phys.*, 14 (1976) 687–702.
- [16] E.S. Sanders, W.J. Koros, H.B. Hopfenberg and V.T. Stannett, Pure and mixed gas sorption of carbon dioxide and ethylene in poly(methyl methacrylate), *J. Membr. Sci.*, 18 (1984) 53–74.
- [17] Y. Zhang, I.H. Musselman, J.P. Ferraris and K.J. Balkus Jr., Gas permeability properties of Matrimid® membranes containing the metal-organic framework Cu-BPY-HFS, *J. Membr. Sci.*, 313 (2008) 170–181.

- [18] S.S. Hosseini, M.M. Teoh and T.S. Chung, Hydrogen separation and purification in membranes of miscible polymer blends with interpenetration networks, *Polymer*, 49 (2008) 1594–1603.
- [19] H. Rösler, Membrantechnologie in der Prozessindustrie – Polymere Membranwerkstoffe, *Chemie-Ingenieur-Technik*, 77 (2005) 487–503.
- [20] H. Zhao, Y. Cao, X. Ding, M. Zhou and Q. Yuan, Effects of cross-linkers with different molecular weights in cross-linked Matrimid 5218 and test temperature on gas transport properties, *J. Membr. Sci.*, 323 (2008) 176–184.
- [21] T.T. Moore and W.J. Koros, Gas sorption in polymers, molecular sieves, and mixed matrix membranes, *J. Appl. Polym. Sci.*, 104 (2007) 4053–4059.
- [22] C.L. Aitken, W.J. Koros and D.R. Paul, Gas transport properties of biphenol polysulfones, *Macromolecules*, 25 (1992) 3651–3658.