

Inhibition of calcium carbonate (CaCO_3) scale formation by calix [4] resorcinarene compounds

Suharso^{a,*}, Buhani^a, Suripto Dwi Yuwono^a, Tugiyono^b

^aDepartment of Chemistry, Faculty of Mathematics and Natural Sciences, University of Lampung, Jl. Soemantri Brojonegoro No. 1 Bandar Lampung, Indonesia, Tel. +62721704625, Fax +62721702767, email: suharso@fmipa.unila.ac.id, suharso_s@yahoo.com

^bDepartment of Biology, Faculty of Mathematic and Natural Sciences, University of Lampung, Jl. Soemantri Brojonegoro No. 1 Bandar Lampung, Indonesia

Received 5 May 2016; Accepted 1 November 2016

ABSTRACT

Inhibition effect of tetrakis((dimethylamino)methyl)C-methyl calix [4] resorcinarene (TDMACMKR) compound on calcium carbonate (CaCO_3) scale formation has been studied using seeded experiment and bottle roller bath method. The effect of the addition TDMACMKR as inhibitor on CaCO_3 scale formation was analyzed by measuring the weight of precipitation of CaCO_3 formed. The morphology and particle size distribution of obtained CaCO_3 crystals caused by the addition of TDMACMKR were analyzed by scanning electron microscopy (SEM), and particle size analyzer. The data obtained show that the TDMACMKR inhibits formation of CaCO_3 scale at various inhibitor concentrations added.

Keywords: Calix [4] resorcinarene; Scale inhibitor; Calcium carbonate

1. Introduction

One of the most serious problems encountered in some industrial processes such as oil and gas, chemical industry, power generation, and geothermal industry is the formation of scale (undesired crystal growth) on surface of industrial equipment [1–6]. This scaling impact on the efficiency of the equipment, and because of this, for example, the Indonesian Oil Company (PT PERTAMINA) has spent US\$ 6–7 million to renew every pipeline at the Geothermal Industry every 10 y [7].

A widespread method used to reduce the impact of scale formation is to add an inhibitor. Selection of an appropriate inhibitor can provide a cheap and effective reduction in scale formation, as low concentrations can have a large impact on acystal growth. Research into scale inhibitors is driven by the strong industrial need for effective inhibitors [8–11].

In this report, the calix [4] resorcinarene (TDMACMKR) compound was synthesized and reported previously [12], and tested as an inhibitor of CaCO_3 precipitation. TDMACMKR was selected for investigation as it combines O-donor groups, with amine functional groups. While most inhibitors studied to date involve O-donor groups, such as carboxylates and phenolates, there are relatively few report where these groups are used alongside amine functional groups. Another reason the use of TDMACMKR as the inhibitor of CaCO_3 precipitation is the existence of amine group classified as a hard bases and the cation of Ca^{2+} classified as a hard acid. According to Person's hard soft acid base (HSAB) theory, the hard bases are more likely to pair up with the hard acids. Therefore, the existence of amine groups in TDMACMKR will inhibit growth rate of the CaCO_3 crystals. Previous studies of this compound focused on its use as an adsorbent to bind the heavy metal ions [12–19].

*Corresponding author.

2. Experimental methods

TDMACMKR was synthesized using standard methodology reported by Sardjono [12]. Reaction scheme of TDMACMKR synthesis is shown in Fig. 1 and full details of the synthesis and characterizations were reported by Sardjono [12]. The characterization of TDMACMKR was investigated by the Fourier transform infrared spectroscopy (FTIR)(Prestige-21 Shimadzu) and ^1H NMR spectroscopy (JEOL MY60 60 MHz).

2.1. Crystal seed preparation

The preparation of seed crystals was performed by mixing 1 M of Na_2CO_3 solution and 1 M of CaCl_2 anhydrate solution each in 50 mL of water at temperature of 80°C . The mixtures were stirred at temperature of 80°C and left for 2 h to produce seed crystals. Then, the seed crystals obtained were separated from the liquor by filtration through a $0.45\ \mu\text{m}$ Millipore filter washed thoroughly with water and dried in the oven at temperature

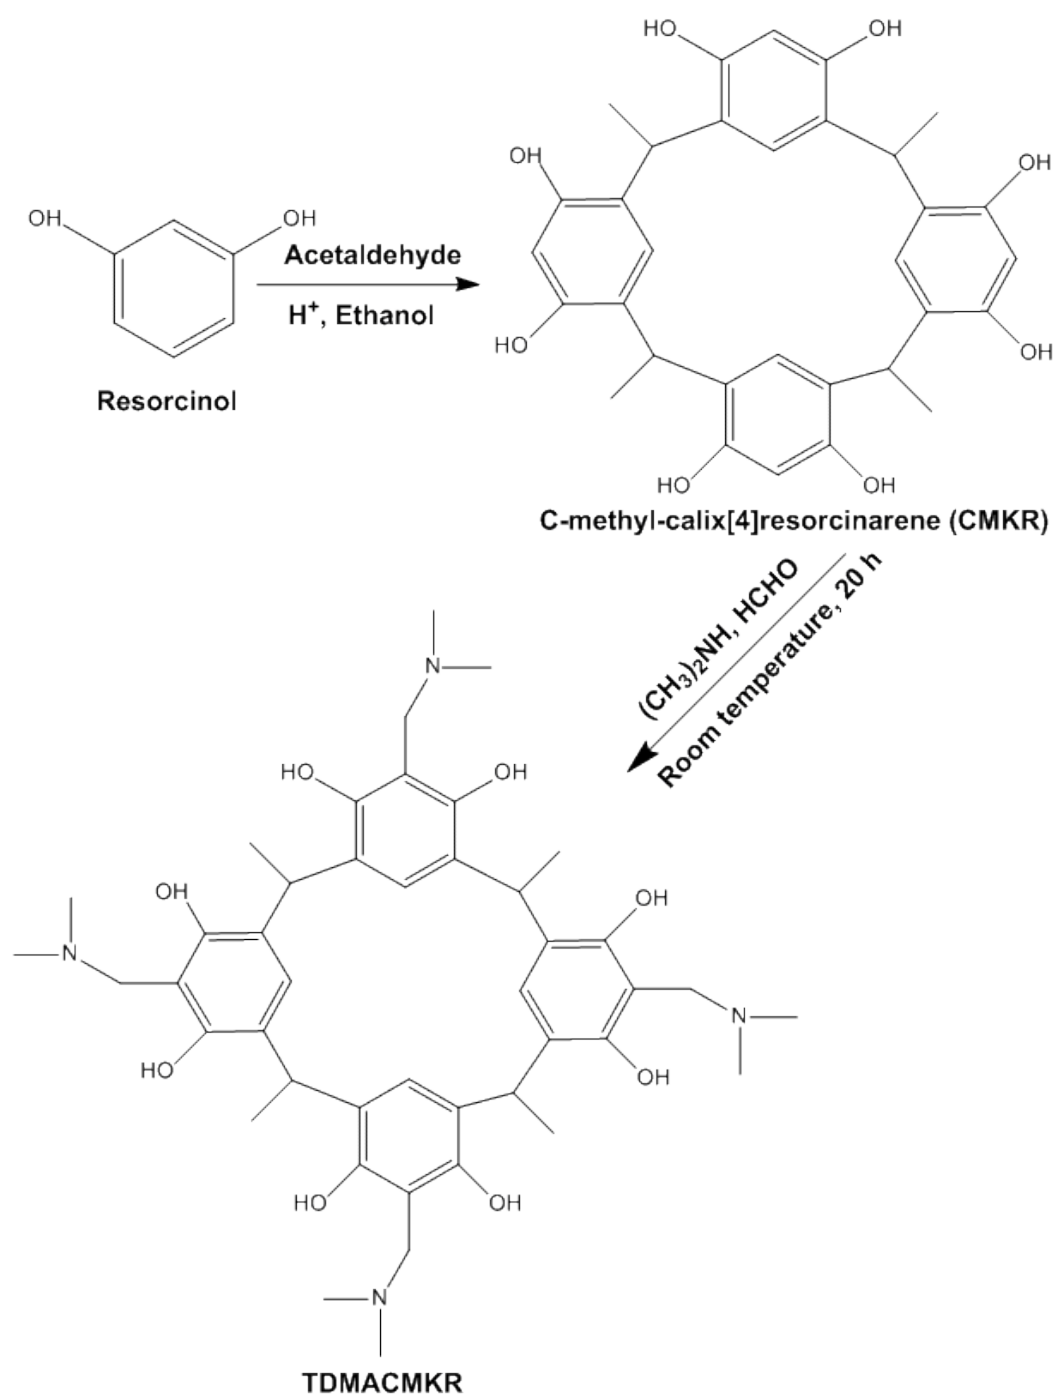


Fig. 1. Reaction scheme of TDMACMKR synthesis.

of 105°C. These methods were repeated several times to procure the required amount of seed crystals for doing the experiments.

2.2. Crystallization experiments

The amount of 200 mL of 0.2 M CaCl₂ anhydrate solution and 200 mL of 0.2 M Na₂CO₃ solution were placed in 500 mL Nalgene polypropylene bottles at a temperature of 80°C, mixed, and stirred by magnetic stirrer to produce 0.1 M CaCO₃ growth solution up to a homogeneous solution. Then, the homogeneous solution obtained was filtered through a 0.45 μm Millipore filter. 50 mL aliquots of this stock solution were added to six 250 mL Nalgene polypropylene bottles. The bottles containing 50 mL of the CaCO₃ growth solution were returned to the bottle-roller bath. Into each bottle, the amount of 200 mg seed crystals was placed at an experiment temperature of 80°C. The bottle-roller was controlled automatically to rotate at 40 rpm. Over the 1.5 h experiment, a bottle was removed for every 15 min and the weight of the crystals precipitated was determined. The crystals resulted were cleaned thoroughly with water and were dried for 1 d in the oven at temperature of 105°C, and then weighed [7].

For each precipitation investigation, a blank experiment was performed in parallel with the inhibitor experiment. The same procedure was carried out for 0.3 and 0.6 M CaCO₃ growth solutions. Preparation of 0.3 M stock growth solution of CaCO₃ was performed by mixing 200 mL of 0.6 M CaCl₂ anhydrate solution and 200 mL of 0.6 M Na₂CO₃ solution. Preparation of 0.6 M stock growth solution of CaCO₃ was carried out by mixing 200 mL of 1.2 M CaCl₂ anhydrate solution and 200 mL of 1.2 M Na₂CO₃ solution.

2.3. Effect of TDMACMKR

In the same procedure, the influence of TDMACMKR presence at different concentrations in the CaCO₃ growth solution was investigated by adding different amounts of TDMACMKR (0, 25, 50, and 75 ppm). The crystal weight after TDMACMKR added as inhibitor was also calculated and analyzed. Inhibitor Effectiveness (%) can be calculated based on Eq. (1) [20].

$$\text{Inhibitor Effectiveness (\%)} = 100 \times \frac{(Cx - Cy)}{(Cz - Cy)} \quad (1)$$

where Cx = CaCO₃ concentration after presented inhibitor at equilibrium (g/L); Cy = CaCO₃ concentration without inhibitor at equilibrium (g/L); Cz = initial CaCO₃ concentration (g/L).

2.4. Data analysis

Using MS Excel 2007, the amount of precipitation versus time at various concentrations of TDMACMKR added and various concentrations of CaCO₃ growth solution were plotted as the amount of precipitation versus time for each different concentration of TDMACMKR added (0, 25, 50, and 75 ppm) in each the growth solution of CaCO₃ applied 0.1, 0.3, and 0.6 M. The ability of TDMACMKR in inhibiting the rate of CaCO₃ precipitation can be analyzed

from the mass of precipitation obtained. Using SEM (JSM 6360 LA, Made in Japan), the CaCO₃ crystals morphology resulted from the experiment was identified to observe morphology change of CaCO₃ single crystal. In order to prove the effectiveness of TDMACMKR in inhibiting the rate of CaCO₃ precipitation, the particle size distribution of CaCO₃ crystals obtained from the experiments with and without inhibitor were analyzed by a particle size analyzer (Sedigraph III 5120–Micrometrics).

3. Results and discussion

3.1. Characterization of TDMACMKR

First step to synthesize TDMACMKR is synthesis of CMKR as raw material. The CMKR obtained and TDMACMKR produced were characterized by FTIR (Fig. 2). The existence of CMKR (Fig. 2a) was shown by peak band at 3425.58 1/cm as hydroxyl groups, 2877.79–2970.38 1/cm and supported clearly at 1427.32 and 1373.32 1/cm showing methine groups (=CH–) and –CH₂, as well as 1620.21 and 1512.19 1/cm as characteristic peaks of C=C aromatic group from condensation product. The FTIR of TDMACMKR is displayed in Fig. 2b. The characteristic change from the FTIR spectrum of CMKR can be seen clearly, but it is difficult to show the substitution has occurred because the

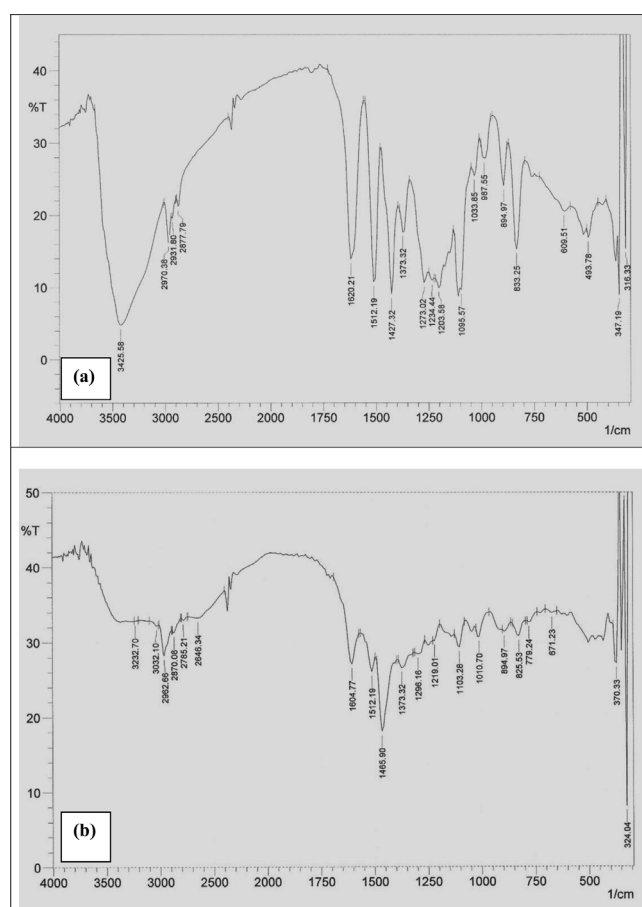


Fig. 2. FTIR spectra of (a) CMKR and (b) TDMACMKR.

existence of tertiary amine group does not give a specific peak. However, as the proof of TDMACMKR resulted from CMKR, the FTIR spectrum of TDMACMKR (Fig. 2b) shows characteristic peaks at the movement of hydroxyl existence from 3232.70–3425.58 $1/\text{cm}$, continued by the peak movement of C=C aromatic showing clearly the characteristic difference from first compound (CMKR). These are as the evident that the TDMACMKR synthesis was carried out successfully.

In order to prove the existence of tertiary amine group, TDMACMKR compound produced was investigated by ^1H NMR spectroscopy. The ^1H NMR spectra of TDMACMKR (Fig. 3) shows the existence of tertiary amine groups at singlet peaks of δ 2.1 dan 3.8 ppm each derived from 8 $-\text{CH}_3$ and 4 $-\text{CH}_2$ -groups of N,N-dimethylamine group substituting H from CMKR. This indication was supported with the absence of proton peak at ortho position from hydroxyl group at around δ 6.0 ppm. These facts were supported with appearing peaks at δ 4.5 ppm indicating methine proton. These results are consistent with that obtained by Sardjono [12].

3.2. Influence of TDMACMKR on CaCO_3 scale formation

The effect of various concentrations of CaCO_3 growth solution on the amount of CaCO_3 precipitation can be seen in Fig. 4. This figure explains that the higher the concentration of the CaCO_3 growth solution, the bigger the amount of CaCO_3 precipitation obtained. Generally, the rate of CaCO_3 precipitation in the beginning of growth is fast and it will be relatively constant after 60 min. This obtained result is similar with the result found by Suharso et al., on the effect of Gambier extracts upon CaCO_3 scale formation [7].

The effect of various concentrations of TDMACMKR addition on the precipitation of CaCO_3 at various CaCO_3 growth solutions with 100 mg of CaCO_3 crystal seed added into growth solution can be seen in Figs. 5–7. From Figs. 5–7, it can be stated that the higher the amount of TDMACMKR (inhibitor) added, the bigger the inhibition of CaCO_3 precipitation over the concentration range investigated. The addition of 75 ppm of TDMACMKR in the CaCO_3 growth solution of 0.1 M will dramatically inhibit the growth rate of CaCO_3 precipitation (Fig. 5). In addition, the ability of inhibitor to inhibit the CaCO_3 precipitation decreases while the growth solution of CaCO_3 is increased from 0.1–0.6 M. The result obtained in this research can be compared to the results found by Suharso et al., on CaCO_3 precipitation using green inhibitor and Jones et al., [7,10] on inorganic materials using additive from calix [4] arene with the functional groups from aspartic and glutamic acid [21]. These results are also comparable to those observed for the calcium carbonate precipitation in the addition of metallocene complexes [22], green inhibitors [7,23], calixarene [24], and several inhibitors produced by industry [25].

Inhibitor effectiveness is one of parameters to investigate the ability of inhibitor to inhibit CaCO_3 precipitation. In this study, the value of inhibitor effectiveness (%) may be calculated based on modification of Eq. (1). Calculating data of the inhibitor effectiveness value are listed in Tables 1–3. From these tables, it can be observed that the inhibitor effectiveness to inhibit the CaCO_3 precipitation is around 57–94% for the growth solution of 0.1 M, 48–73% for the

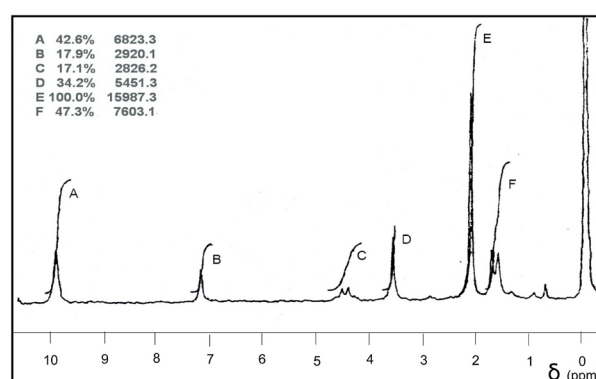


Fig. 3. ^1H NMR spectra of TDMACMKR.

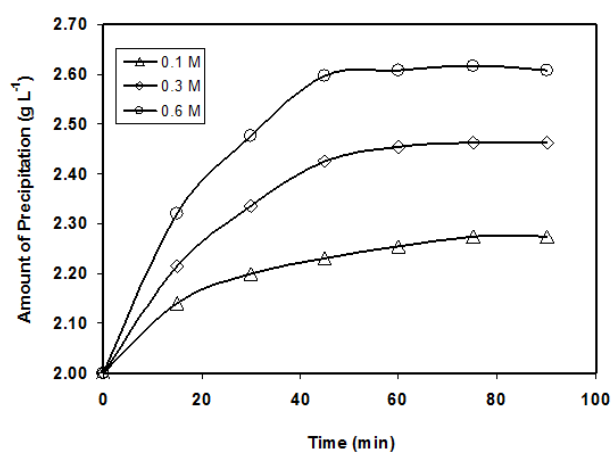


Fig. 4. The effect of various concentrations of growth solution on the precipitation of CaCO_3 with 100 mg of CaCO_3 crystal seed.

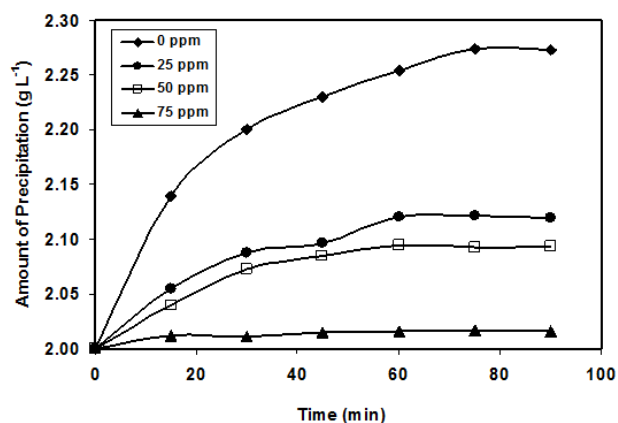


Fig. 5. The effect of TDMACMKR addition on the precipitation of CaCO_3 at a growth solution of 0.1 M.

growth solution of 0.3 M, and 38–58% for the growth solution of 0.6 M, respectively. It is showed that the inhibitor effectiveness to inhibit the CaCO_3 precipitation decreases, while the growth solution concentration increases (Tables 1–3). These facts show that the growth rate of CaCO_3 crys-

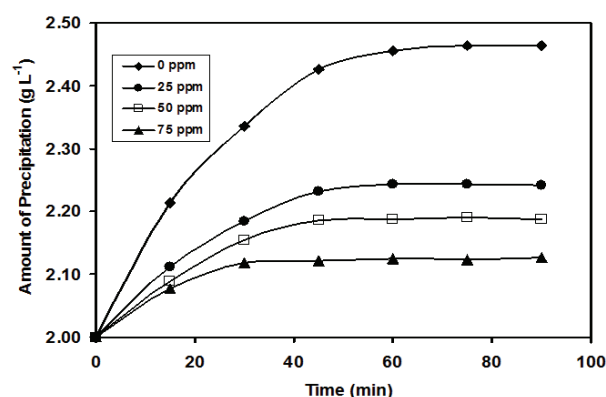


Fig. 6. The effect of TDMACMKR addition on the precipitation of CaCO_3 at a growth solution of 0.3 M.

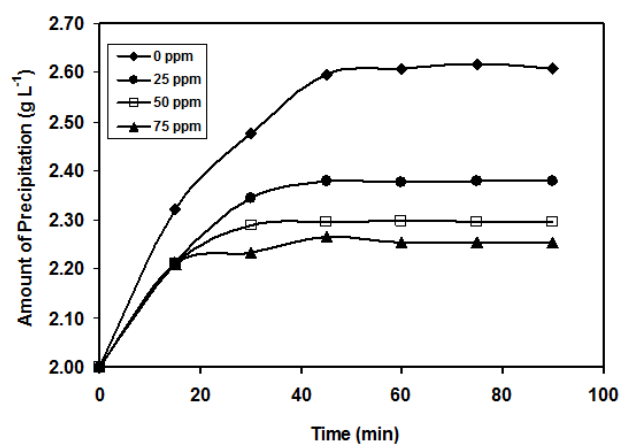


Fig. 7. The effect of TDMACMKR addition on the precipitation of CaCO_3 at a growth solution of 0.6 M.

tallization at the higher growth solution concentration will grow faster causing decreasing of inhibitor ability to inhibit the CaCO_3 precipitation or to react with Ca^{2+} ions and active sites on the crystal surface of CaCO_3 . It can be stated that the concentration change of the growth solution affects the interaction competition among inhibitor, CO_3^{2-} , and Ca^{2+} ions in the growth solution. Therefore, in the higher growth solution concentration and at the same concentration inhibitor added (Tables 1–3), the interaction between the inhibitor and Ca^{2+} ions in the growth solution will run slower than the interaction between CO_3^{2-} and Ca^{2+} ions to form CaCO_3 crystal causing decreasing of the inhibitor effectiveness (%). Generally, in the growth solution concentration range studied, TDMACMKR are able to inhibit formation of CaCO_3 scale with the most effective (94%) of TDMACMKR concentration of 75 ppm for CaCO_3 growth solution of 0.1 M. The inhibitor effectiveness (%) of these results can be compared with (Table 4) the results of calcium carbonate crystal growth inhibition with addition of homopolymer of polymaleic acid (PMA-1), terpolymer of polymaleic acid (PMA-2), copolymer of polymaleic acid (PMA-3), polycarboxylic acid (EM), Polyacrylate (PAA), and Phosphonate [20]. The addition of these inhibitors derived from polyma-

Table 1
TDMACMKR effectiveness in inhibiting CaCO_3 scale formation on the CaCO_3 growth solution concentration of 0.1 M

Inhibitor concentration (ppm)	Inhibitor effectiveness (%)
0	0
25	57
50	66
75	94

Table 2
TDMACMKR effectiveness in inhibiting CaCO_3 scale formation on the CaCO_3 growth solution concentration of 0.3 M

Inhibitor concentration (ppm)	Inhibitor effectiveness (%)
0	0
25	48
50	60
75	73

Table 3
TDMACMKR effectiveness in inhibiting CaCO_3 scale formation on the CaCO_3 growth solution concentration of 0.6 M

Inhibitor concentration (ppm)	Inhibitor effectiveness (%)
0	0
25	38
50	51
75	58

Table 4
Inhibitor effectiveness in inhibiting CaCO_3 crystal of different inhibitors, experiment methods, and growth solution concentrations

Name of inhibitors	Inhibitor concentration (ppm)	Inhibitor effectiveness (%)	References
TDMACMKR	25–75	38–94	This work
Gambier extracts	50–250	60–100	[7]
Homopolymer of polymaleic acid	4	67	[20]
Terpolymer of polymaleic acid	4	73	[20]
Copolymer of polymaleic acid	4	18	[20]
Polycarboxylic acid	4	70	[20]
Metalocene complexes	10	27–66	[22]
Polymaleic acid	1–4	20–100	[23]
C-methyl-4, 10, 16, 22-tetramethoxy calix[4]arene	10–100	34–100	[24]

leic acid polycarboxylic acid, polyacrylate, and phosphonate groups on the calcium carbonate crystal growth gave the inhibitor effectiveness (%) around 10–70% [20].

SEM images of CaCO_3 crystals in the absence and presence of TDMACMKR at the growth solution of 0.1 and 0.6 M were displayed in Figs. 8 and 9. These images prove that the addition of TDMACMKR in the growth solution of CaCO_3 can inhibit growth rate of CaCO_3 crystals. The size of CaCO_3 crystal morphology under presence of TDMACMKR gives smaller crystal size than in the absence of TDMACMKR. At the growth solution concentration of 0.1 M, the addition of TDMACMKR changes dramatically the morphology of CaCO_3 crystals (Fig. 8). Crystals grown in the absence of the inhibitor (control samples) corresponding to calcite phase (CaCO_3 crystals) were always regular shaped rhombohedra (Figs. 8a and 9a) [9]. However, the regular shaped rhombohedrons disappeared when TDMACMKR added into the growth solution of 0.1 M (Fig. 8b) or the morphologies of the precipitates changed from the cube portion into a spherical shape. The change of morphology can be caused by interaction of inhibitor and the active sites on the surface of the crystals. The interaction between amine group from TDMACMKR and the active sites of the crystal surface

change the stereochemical orientation of CaCO_3 growth [26], and thus the stereochemical orientation of CaCO_3 growth was modified. The irregular spherical shaped morphology was gained. But in the higher growth solution concentration (0.6 M), the inhibitor could not change the morphology of the crystals because the growth solution concentration affects the ability of inhibitor to change the morphology of the crystal. It is assumed that in the higher growth solution concentration (0.6 M) resulting faster growth rate of CaCO_3 crystal, the inhibitor adsorbs whole of the surface of the crystal so that the inhibitor can inhibit of crystal growth but it cannot alter the morphology of CaCO_3 crystal. As the comparison of these results, generally the bigger the concentration of the inhibitor added the smaller the particle size resulted, however, there may be exceptions and this is best to observed this explicitly [27,28]. For instance, commonly as the growth solution raises particle size decreases but this does not occur with lactose crystal [29]. The changes in morphology are able to provide an indication as to which crystal faces are preferentially adsorbing the inhibitor, as such faces are going to grow more slowly and become more dominant in the producing morphology [28]. But in the case in Fig. 9, the inhibitor does not dominate in adsorbing one

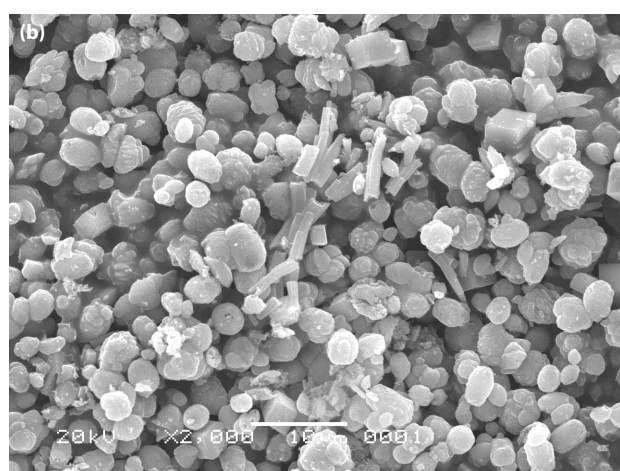
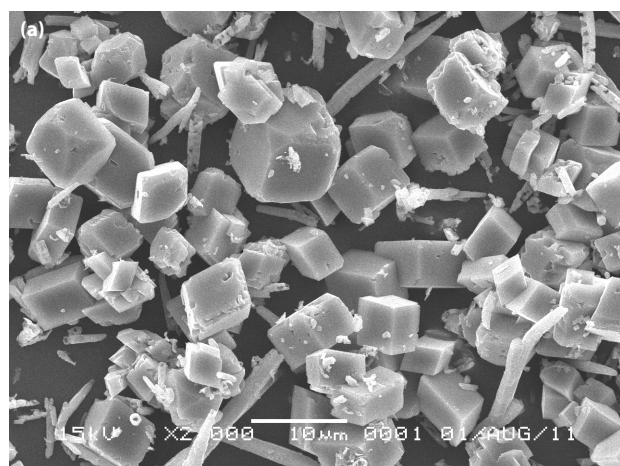


Fig. 8. SEM Images of CaCO_3 crystals (a) in the absence of the inhibitor (b) in the presence of 75 ppm of TDMACMKR at a growth solution of 0.1 M.

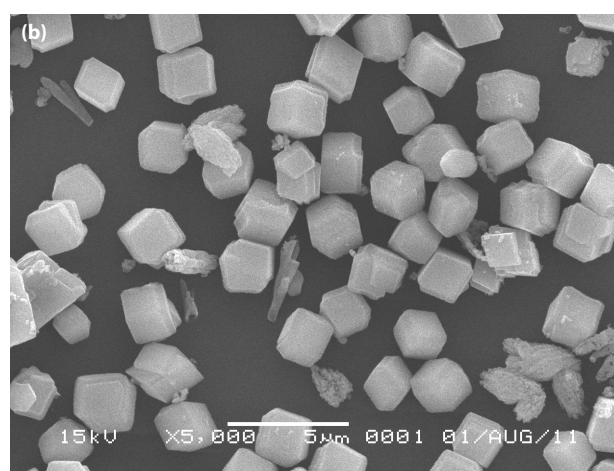
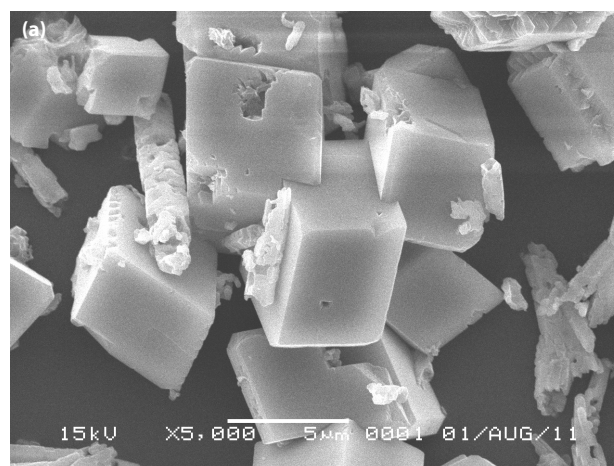


Fig. 9. SEM Images of CaCO_3 crystals (a) in the absence of the inhibitor (b) in the presence of 75 ppm of TDMACMKR at a growth solution of 0.6 M.

or several faces of the surface crystal, therefore the morphology of CaCO_3 crystal does not change as in Fig. 8.

The morphology change of CaCO_3 crystal may be caused by the inhibitor molecules adsorbing onto the active growth sites of the crystal surface area and inhibiting the regular outgrowth of calcium carbonate crystals. The TDMACMKR as the inhibitor molecules may also play a role as a heterogeneous nucleator controlling and stabilizing the precipitating polymorph [7,30–32]. Based on the lattice distortion happens in the addition of the TDMACMKR inhibitor, and the crystal structure and morphology are then altered dramatically (Fig. 8) [1]. From Figs. 8 and 9, it can be seen clearly the changes of the morphology and the crystal size of CaCO_3 and it can be concluded that the inhibitor of TDMACMKR may adsorb on the calcium carbonate crystals surface. However, Fig. 9 indicates that at higher solution concentration of 0.6 M, the additive effectiveness is low. This is evident by less modification of CaCO_3 crystals in Fig. 9 as compared to that in Fig. 8 at the same additive dose level of 75 ppm. TDMACMKR molecules with its amine group may react with Ca^{2+} via an electrostatic forces or crystal nucleus of CaCO_3 and then affect the growth of CaCO_3 crystals. The amine groups on the TDMACMKR molecules may also react with the active sites on the crystal surface and thus the TDMACMKR molecules may inhibit the CaCO_3 crystal growth by binding the crystal nucleus. In addition, via the interaction between amine groups on TDMACMKR molecules and the active sites on the crystal surface of CaCO_3 , this inhibitor may change the stereochemical orientation of CaCO_3 growth. This result is consistent with the result of effect of hydrolyzed polymaleic anhydride on the crystal of calcium carbonate [33].

In order to examine the ability of TDMACMKR as inhibitor to inhibit the growth rate of CaCO_3 crystallization as seen in Figs. 8 and 9, the particle size distribution of CaCO_3 crystals obtained from the experiments with and without inhibitor added was examined by the particle size analyzer. The addition of inhibitor into the growth solution of the CaCO_3 precipitation should result a smaller particle size distribution of the crystal diameter than in the absence of inhibitor. Figs. 10 and 11 show the particle size distribution of CaCO_3 crystals in the absence and presence of 75 ppm of TDMACMKR at the growth solution of 0.1 and 0.6 M. In the growth solution of 0.1 M, the average particle size distribution of CaCO_3 without inhibitor is 9.15 μm and the average particle size distribution of CaCO_3 with inhibitor TDMACMKR decrease to be 6.12 μm . With the similar result, the mean of particle size distribution of CaCO_3 without inhibitor in the growth solution of 0.6 M is 14.30 μm and the mean of the particle size distribution of CaCO_3 with inhibitor TDMACMKR occurs decreasing to be 11.16 μm . These data obtained support the data gained from the SEM images showing CaCO_3 crystal size with the addition of TDMACMKR smaller than without TDMACMKR. It is also evident that TDMACMKR works as inhibitor of the CaCO_3 precipitation. Therefore, these results are in good agreement with those obtained by SEM. These data found show that TDMACMKR is able to play a role as inhibitor of the CaCO_3 precipitation under these experiment conditions. The data of the particle size distribution of CaCO_3 crystals obtained can be compared with the previous result using Gambier extract as inhibitor of CaCO_3 crystallization showing a similar trend with this study [7,34].

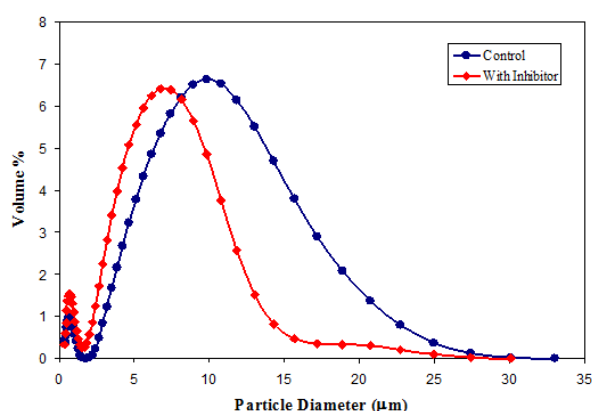


Fig. 10. Particle size distribution of CaCO_3 crystals in the absence and presence of 75 ppm of TDMACMKR at the growth solution of 0.1 M.

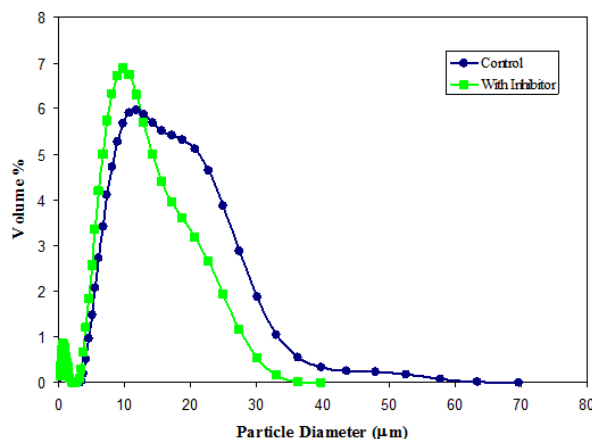


Fig. 11. Particle size distribution of CaCO_3 crystals in the absence and presence of 75 ppm of TDMACMKR at the growth solution.

4. Conclusions

The TDMACMKR can act as an inhibitor of the CaCO_3 precipitation under these operation conditions. The presence of TDMACMKR in the growth solution of 0.1 M can change significantly the morphology and size of the CaCO_3 crystal. But, the presence of TDMACMKR in the growth solution of 0.6 M does not change the morphology of the CaCO_3 crystal. The inhibitor effectiveness to inhibit the CaCO_3 precipitation is around 38–94% depending on the growth solution concentration and the inhibitor concentration added.

Acknowledgements

This research was supported by the Directorate of Research and Community Services, Directorate General of Higher Education (DIKTI), Ministry of Research, Technology and Higher Education of the Republic of Indonesia (Kemristekdikti), (Competency Research Grant/*Penelitian Hibah Kompetensi*) with contract number: 050/SP2H/PL/

Dit.Litabmas/II/2015. We are very grateful to Mr. Abdul Somad, Mrs. Dewi Asmarani, and Mrs. Rivera for collecting data and technical assistance.

References

- [1] Y. Tang, W. Yang, X. Yin, Y. Liu, Y.P. Yin, J. Wang, Investigation of CaCO_3 scale inhibition by PAA, ATMP, and PAPEMP, *Desalination*, 228 (2008) 55–60.
- [2] K.D. Demadis, E. Mavredaki, A. Stathouloupoulou, E. Neofotistou, C. Mantzaridis, Industrial water systems: problem, challenges, and solution for process industries, *Desalination*, 213 (2007) 38–46.
- [3] T. Chen, A. Neville, M. Yuan, Calcium carbonate scale formation—assessing the initial stages of precipitation and deposition, *J. Pet. Sci. Eng.*, 46 (2005) 185–194.
- [4] T. Waly, M.D. Kennedy, G.J. Witkamp, G. Amy, J.C. Schippers, The role of inorganic ions in the calcium carbonate scaling of seawater reverse osmosis systems, *Desalination*, 284 (2012) 279–287.
- [5] J.Y. Gal, Y. Fovet, N. Gatche, Mechanisms of scale formation and carbon dioxide partial pressure influence. Part I. Elaboration of an experimental method and a scaling model, *Water Res.*, 36 (2002) 755–763.
- [6] S.J. Dyer, G.M. Graham, Thermal stability of generic barium sulphate scale inhibitor species under static and dynamic conditions, *J. Pet. Sci. Eng.*, 37 (2003) 171–181.
- [7] Suharso, Buhani, S. Bahri, T. Endaryanto, Gambier extracts as an inhibitor of calcium carbonate (CaCO_3) scale formation, *Desalination*, 265 (2011) 102–106.
- [8] F. Manoli, J. Kanakis, P. Malkaj, E. Dalas, The effect of aminoacids on the crystal growth of calcium carbonate, *J. Cryst. Growth*, 236 (2002) 363–370.
- [9] R. Fried, Y. Mastai, The effect of sulfated polysaccharides on the crystallization of calcite superstructures, *J. Cryst. Growth*, 338 (2012) 147–151.
- [10] F. Jones, A. Oliveira, A.L. Rohl, G.M. Parkinson, M.I. Ogden, M.M. Reyhani, Investigation into the effect of phosphonate inhibitors on barium sulfate precipitation, *J. Cryst. Growth*, 237 (2002) 424–429.
- [11] D.J. Choi, S.J. You, J.G. Kim, Development of an environmentally safe corrosion, scale, and microorganism inhibitor for open recirculating cooling systems, *Mater. Sci. Eng. A*, 335 (2002) 228–235.
- [12] R.E. Sardjono, Sintesis dan penggunaan tetramer siklik seri kaliksresorsinarena, alkoksikaliksarena, dan alkenilkaliksarena untuk adsorpsi kation logam berat, Dissertation (2007), University of Gadjah Mada, Yogyakarta.
- [13] P. Engrand, J.B. Regnouf-de-Vans, A bifunctional calixarene designed for immobilisation on natural polymer and for metal complexation, *Tetrahedron Lett.*, 43 (2002) 8863–8866.
- [14] P. Thuery, Z. Asfari, J. Vicens, V. Lamare, J.F. Dozal, Synthesis and crystal structure of sodium and cesium ion complexes of unsubstituted calix [4] arene. New polymeryc chain arrangements, *Polyhedron*, 21 (2002) 2497–2503.
- [15] C.D. Gutsche, Calixarene revisited: monograph in supramolecular chemistry, Royal Society of Chemistry, Cambridge, 1998.
- [16] V. Bohmer, *Angewandte Chemie (International Edition in English)*, 34 (1995) 713.
- [17] D. Roundhill, Metal complexes of calixarenes: Progress in inorganic chemistry, K. Karlin, John Wiley & Sons, 43 (1995), 533.
- [18] J.M. Harrowfield, M. Mocerino, B. Peachy, B.W. Skelton, A.H. White, Rare earth solvent extraction with calixarene phosphonates, *J. Chem. Soc. Dalton Trans.*, (1996) 1687–1699.
- [19] C. Hill, J.F. Dozol, V. Lamare, H. Rouquette, S. Eymard, B. Tounois, Nuclear waste treatment by means of supported liquid membranes containing calixcrown compounds, *J. Inc. Phen. Mol. Rec. Chem.*, 19 (1994) 399–408.
- [20] S. Patel, M.A. Finan, New antifoulants for deposit control in MSF and MED plants, *Desalination*, 124 (1999) 63–74.
- [21] F. Jones, M. Mocerino, M.I. Ogden, A. Oliveira, G.M. Parkinson, Bio-inspired calix [4] arene additives for crystal growth modification of inorganic materials, *Cryst. Growth Des.*, 5 (2005) 2336–2343.
- [22] P. Malkaj, E. Dalas, Effect of metallocene dichlorides on the crystal growth of calcium carbonate, *J. Cryst. Growth*, 242 (2002) 405–411.
- [23] A. Martinod, M. Euvrard, A. Foissy, A. Neville, Progressing the understanding of chemical inhibition of mineral scale by green inhibitors, *Desalination*, 220 (2008) 345–352.
- [24] Suharso, Buhani, T. Suhartati, The role of C-methyl-4,10,16, 22-tetramethoxy calix [4] arene as inhibitor of calcium carbonate (CaCO_3) scale formation, *Indo. J. Chem.*, 9 (2009) 206–210.
- [25] Ch. Tzotzi, T. Pahiadaki, S.G. Yiantsios, A.J. Karabelas, N. Andritsos, A study of CaCO_3 scale formation and inhibition in RO and NF membrane processes, *J. Membr. Sci.*, 296 (2007) 171–184.
- [26] M.M. Reddy, A.R. Hoch, Calcite crystal growth rate inhibition by polycarboxylic acids, *J. Colloid Interface Sci.*, 235 (2001) 365–370.
- [27] F. Wang, G.Y. Xu, Z.Q. Zhang, S. Song, S.L. Dong, A systematic morphosynthesis of barium sulfate in the presence of phosphonate inhibitor, *J. Colloid Interface Sci.*, 293 (2006) 394–400.
- [28] F. Jones, M.I. Ogden, Controlling crystal growth with modifiers, *Crys. Eng. Comm.*, 12 (2010) 1016–1023.
- [29] S. Garnier, S. Petit, G. Coquerel, Influence of supersaturation and structurally related additives on the crystal growth of α -lactose monohydrate, *J. Cryst. Growth*, 234 (2002) 207–219.
- [30] P.G. Koutsoukos, G.H. Nancollas, The mineralization of collagen in vitro, *Colloids Surf.*, 28 (1987) 95–108.
- [31] E. Dalas, P.G. Koutsoukos, Crystallization of calcite on collagen type I, *Langmuir*, 4 (1988) 907–910.
- [32] E. Dalas, Crystallization of sparingly soluble salts on functionalized polymers, *J. Mater. Chem.*, 1 (1991) 473–474.
- [33] Z. Shen, J. Li, K. Xu, L. Ding, H. Ren, The effect of synthesized hydrolyzed polymaleic anhydride (HPMA) on the crystal of calcium carbonate, *Desalination*, 284 (2012) 238–244.
- [34] Suharso, Buhani, L. Aprilia, Influence of calix [4] arene derived compound on calcium sulphate scale formation, *Asian J. Chem.*, 26 (2014) 6155–6158.