Desalination and Water Treatment
www.deswater.com

doi: 10.5004/dwt.2019.24613

172 (2019) 395–416
December

A critical review on recent developments in the low-cost adsorption of dyes from wastewater

P. Senthil Kumar[a,*], G. Janet Joshiba[a], Carolin C. Femina[a], P. Varshini[a], S. Priyadharshini[a], M.S. Arun Karthick[a], R. Jothirani[b]

[a]*Department of Chemical Engineering, SSN College of Engineering, Chennai 603 110, India, Tel. +919884823425; email: senthilchem8582@gmail.com (P. Senthil Kumar), Tel. +9790818301; email: janujosh21@gmail.com (G. Janet Joshiba), Tel. +919003196798; email: feminacarolin@gmail.com (C.C. Femina), Tel. +917338707931; email: varshupaddy@gmail.com (P. Varshini), Tel. +9600624112; email: pspriya2411@gmail.com (S. Priyadharshini), Tel. +9884107060; email: msarunkarthik@gmail.com (M.S. Arun Karthick)*
[b]*Department of Chemistry, Adhiparasakthi Engineering College, Melmaruvathur 603 319, India, Tel. +919444342541; email: jothirani.rk@gmail.com*

Received 15 February 2019; Accepted 24 June 2019

ABSTRACT

Water is one of the most important components in the environment. This is essential for all forms of life and leisurely plays a vital role in the world economy. The discharge of large amount of dye wastewater from different industries such as textile, leather, pulp, rubber pharmaceuticals, food processing, electroplating cosmetics, plastic, paper industries, etc. to the aquatic system constitutes the major hazards to the living environment. Hence, the rapid removal of these dyes from wastewater before their discharge is an important necessity of day to day life as well as for environmental safety. Several traditional treatment methods were available for the removal of dyes from water/wastewater such as chemical coagulation, filtration, flocculation, ozonation, oxidation, photocatalytic degradation, ion exchange, biodegradation, electrolysis and adsorption. Among all these treatment methods, adsorption process using activated carbon is one of the most important, effective and reliable method for the removal of dyes from aquatic system. However, the widespread application of activated carbon is restricted because of its high cost. Therefore, the attention has moved to select the low-cost and efficient adsorbents which are alternative to the existing activated carbon. Some of the natural materials, agricultural wastes, industrial wastes and biosorbents have been reported as an effective low-cost adsorbent for the removal of dyes from aquatic system by many researchers. The current review paper explains the detailed survey on the dye removal methods, and scope for the improvement can be done on the removal of dyes from industrial wastewater.

Keywords: Dyes; Methods; Removal; Adsorption; Wastewater; Toxicity

1. Introduction

Water is an essential component for living environment. Water pollution by various toxic pollutants has become one of the most important serious issues worldwide. The rapid growth of industrialization, anthropogenic activities, unplanned urbanization, unskilled utilization of natural water resources and tremendous increase in population lead to release of several toxic contaminants in to the environment [1–4]. In addition, on a total of 75% of underground water only 3% of water is found to be pure, in which only 1% is available for drinking and domestic purposes [5]. The provision for the pure water which is basically utilized for domestic and survival purposes is shrinking. This may be due to the

---

* Corresponding author.

fresh water pollution. The water and soil resources are getting contaminated due to the release of several noxious compounds such as industrial effluents, chemicals, agricultural runoff, domestic wastes and municipal waste. The wastewater not only decreases the available fresh water resources but also increases the probability of millions of waterborne disorders [6,7]. The important sources of water pollution include industrial chemicals, fertilizers, pesticides, radioactive wastes, solid waste, oil sludges and commercial waste. Apart from the anthropogenic sources some of the natural sources also cause water pollution but most of the frequent water pollution was caused by human activities [8]. Some of the organic compounds available are solvents, pesticides, polychlorinated biphenyls, dioxins and dyes [9]. Among the different pollutants generated from the different industrial applications, dye is considered to be one of the most hazardous pollutants due to their environmental impacts especially for their toxicity to the living organisms. Dyes are mainly discharged from the different industries such as textile, dye production, paper, food, printing, cosmetic, plastic and leather [10–16]. The release of these pollutants into the hydrosphere provides a significant threat to the living environment due to their visibility even at very low concentrations, reduces the sunlight penetration and their toxicity, potential mutagenecity and carcinogenicity [17–23].

1.1. Industrial dye materials

The dyes are coloured organic materials which are utilized by several industries such as textile, leather, paper, plastic, pharmaceuticals, cosmetics, food, etc. and applied for hair, fur, oil refinery products and grease [7,24–26]. Commonly, the dyes utilized in the garments manufacturing sectors are acidic, basic, reactive, specific, azo, vat, caustic, disperse and sulphur dyes [27]. The derivatives of the azo dyes are the major class of dyes used in the industrial applications [28]. Generally, the dyes can be classified into three categories: (i) cationic, (ii) anionic and (iii) non-ionic dyes. The anionic dyes are of direct, acidic and reactive dyes [29].

The cationic dyes posesess several chemical structures based on their substituted aromatic groups and they are mostly applied in silk, wool, acrylic and nylon dyeing [30]. These dyes are mainly dependent on the positive ion. They are also known as basic dyes which are generally zinc chloride or hypochloride complexes [31]. They are positively charged, water soluble and provide coloured cations in the aqueous solution. The cationic groups were seen in different types of dyes including azo, anthraquinone, methane, di- and tri-arylcarbenium, phthalocyanine, several polycarbocyclic and solvent dyes. The anthraquinone dyes are weak and expensive. In addition, they have great properties, strong and low cost. Generally, the cationic dyes are visible and have brilliance and intensity of colours [29]. These cationic dyes are considered as harmful colourants causing serious health hazards such as cancer, genetic disorder, skin irritation and dermatitis [32].

The anionic dyes are mostly dependent on the negative ion [31]. These dyes belong to different types which show distinctive difference in their structure but they possess common feature such as ionic groups and water solubilizing properties. These dyes also include direct, reactive and acidic dyes [33]. The reactive groups of the reactive dyes interact with the wool and cotton and form strong covalent bonding with them. The release of reactive dyes into the ecosystem is not advisable because of their low degree of fixation due to the hydrolysis of reactive groups in water [34]. The acid dyes are applied with wool, silk, acrylic, polypropylene and polyamide fibres. They have good water soluble property. In addition, these are harmful to the humans because of the toxic organic sulphonic acids [35].

1.2. Hazards of industrial dye materials

The industrial dyes are considered hazardous to the environment because many dyes are toxic to living organisms either directly or through their absorption and reflection of sunlight entering the water which interferes with the growth of aquatic animals. These dyes not only provide harmful effects to the living environment but also damage the quality of the fresh water sources. The acidic, basic, reactive, azo, diazo, disperse, anthraquinone based and metal complex based dyes are used in the textile industries [36]. The higher intake of these dyes causes vomiting, shock, heart disorders, Heinz body formation, cyanosis, jaundice, quadriplegia and tissue necrosis in humans [37]. The availability of pigments in the aquatic system also leads to water coluring, oxygen reduction, thereby damaging plants and animals [38]. The most widely used basic or cationic dye is Malachite Green (MG), which was widely used as medical disinfectant, biocide and colouring agent to wool, silk, leather, jute, paper, cotton and acrylic materials. MG dye causes carcinogenic, mutagenic and teratogenic effects to mammalian cell. This provides potential harmful effects on kidneys, livers, gills, intestines and gonads in organisms [39–42]. Another most important basic dye is Methylene Blue (MB), which was widely used as a colouring agent for wool, cotton and silk. This MB dye is also utilized as a staining agent for making certain body fluids and tissues earlier to view during surgery and diagnostic assessments. This MB dye can also be utilized for the medical treatment of methaemoglobinemia and cyanide poisoning. In spite of several useful applications, this MB dye has a number of negative effects to the living environment which includes irritation of mouth, throat, oesophagus and stomach with symptoms of nausea, abdominal discomfort, vomiting and diarrhoea [22,43–45]. The skin contact to this MB dye can cause mechanical irritation which results in redness and itching. The Metanil Yellow dye is a tumour causing compound leading to cancer [46] and also cause enzymatic disorder in the human beings [47]. This dye generally does not provide mutagenic effect but it is capable of latering the gene expression [48]. During oral intake, this dye causes toxic methaemoglobinaemia [49] and cyanosis [50] in human beings and the skin contact causes allergic dermatitis [51]. The oral consumption of dyes in animal creates testicular lesions [52].

The removal of these toxic dyes from wastewater becomes globally essential activity because even a small concentration of pigment in water is noxious and highly conspicuous. As the elimination of these toxic dyes from aqueous solution is considered an environmental challenge, the government legislation needs the industrial wastewater to be treated, therefore there is a constant requirement to have an effective process that can potentially remove toxic dyes. Due to the increased consciousness provided to the significance of effluent treatment plant, the research scientists are insisted to formulate potential, eco-friendly and low-cost technologies which are capable of eliminating toxic contaminants present in the wastewater and also to defend the populace from dreadful health disorders. This is the reason why it is essential to remove pigments and colourants from the aqueous solution. A variety of treatment technologies such as coagulation, filtration, oxidation, advanced oxidation process, electrochemical, biological treatment, ion exchange and adsorption have been employed for the removal of dyes from wastewater.

2. Dye removal methods

Dyes are one of the most vital classes of organic macromoleclues. These dyes occupy an important place in our survival and are utilized in different industrial sectors that include textile, plastics, paints, leather, drugs, waxes, greases, cosmetics, optics, dye-sensitized solar cells, sensors, fur, hair, etc. The source, colour, molecular structure and colour index are some of the properties based on which the dyes are classified. Basically, they are distinguished depending on the chromophores available in these chemicals. In earlier days, the selection of dyes and its applications are not given a higher impact based on its effect on the environment because the industries failed to calculate the chemical composition of the dyes used in it. In 1980s, people started to provide much attention to the dye waste because of their health concern which is mainly based on aesthetic condition. Over this decade, more details on the deleterious consequences of dyes applications have been reviewed. In addition, the dye utilizing industries, government and other environmental organizations have enunciated certain permissible limits for the discharge of toxic colourants into the aqueous system and they take effective measures for the treatment of industrial dyes in the wastewater. In the beginning, the wastewater treatment was performed using some physical treatments including equalization and sedimentation to maintain the pH, total suspended solids and total dissolved solids of the discharged dye wastewater [53,54].

After that the secondary wastewater treatments such as filter beds were applied for the degradation of dye wastewater. In recent times, the introduction of the activated sludge processes was applied in the dye effluent treatment. Generally, the industrial effluent treatment includes preliminary, primary, secondary and tertiary treatment technologies. The various treatment technologies involved in the elimination of toxic dyes are depicted in Table 1. The preliminary treatment includes screening and gravity settling chamber to remove the large size and settleable solids from the wastewater, respectively. The primary treatment includes physical or chemical treatment to remove the suspended solids from the wastewater. The secondary treatment is the biological treatment to remove the biologically degradable organics in the wastewater. The important biological treatment techniques include attached and suspended growth systems. The waste sludge from the biological treatment units was further treated with the help of either by aerobic or anaerobic decompositions. The tertiary treatment is the physical–chemical treatment which includes adsorption, membrane, ion exchange, chemical oxidation and stripping. The above-mentioned methods are highly expensive than the other biological treatment methods but these methods are used in the removal of inorganic pollutants which are not removed easily by the biological methods [55]. However, these methods are generally applied in series with the biological treatment but sometimes they are also used as a separate treatment process. The industrial dye wastewater is also treated in more or similar procedures but no single treatment methodologies were applied for all types of dye wastewater. Though various treatment techniques are available for dye removal, some of them are not more suitable due to their drawbacks [56]. The different dye removal methods were shown in Fig. 1.

Table 1
Overview of wastewater treatment technologies utilized in the elimination of dye

Preliminary physical treatment technologies	Screening Filtration Gravity settling chamber
Physico-chemical treatment technologies	Coagulation Flocculation Adsorption Ion exchange Distillation Membrane technology
Chemical treatment methodologies	Advanced oxidation process Electrochemical techniques Photocatalytic techniques Oxidation Fenton reagent reaction
Biological treatment methodologies	Anaerobic degradation Aerobic degradation

2.1. Chemical coagulation/flocculation

The dye wastewater treatment with chemical coagulation/flocculation process is one of the effective methods to remove colour from the dye wastewater [57–59]. This method is a low cost, simple, reliable and low energy consuming process as compared with the other methods. This treatment process is a recognized method which effectively removes the colloidal, suspended and soluble solids through induced aggregation of both micro- and macro-particles into larger particles and followed by sedimentation. The conventional chemical coagulants used in the process include alum, ferric sulphate, ferric chloride, polyaluminium chloride, synthetic organic polymers, etc. [60–63].

Even though these types of coagulants have broad applications, they have also provided some shortcomings including relatively high costs, toxic effects to human beings and large volume of sludge production, which affects considerably the pH of the aquatic system [64–67]. Particularly, the alum, a common chemical coagulant which was worldwide applied in water and wastewater treatment, was reported to produce a large volume of sludge. These sludges react with natural alkalinity present in the water which leads to reduction in the pH [68]. In general, this process is economically viable for the removal of dyes from wastewater but sometimes becomes costly because of the cost of chemical coagulants. The major drawback of this treatment method is that the final sludge product is in large quantity as well as the removal of dye is pH dependent [69]. This treatment process is not suitable for highly soluble dyes such as reactive, azo, acid and basic dyes [70]. The synthetic polymer coagulants have also been reported to provide numerous environmental problems to the human beings. Some of the derivatives of these coagulants are non-biodegradable and their monomers are producing neurotoxic and carcinogenic effects [71].

2.2. Filtration

Filtration methods such as microfiltration, ultrafiltration, nanofiltration and reverse osmosis are important treatment methods for drinking water and wastewater applications [72–78]. These treatment methods have been studied for the removal of colour from dye wastewater [79,80]. They simultaneously remove BOD and COD of the wastewater. Each and every filtration techniques is most preferable for particular types of water/wastewater treatment facilities. Generally, the microfiltration technique is not prefereed in wastewater treatment because of its large pore size [81]. The ultrafiltration and nanofiltration techniques are effectively utilized for the removal of dyes from different industrial dye wastewater. The application of these treatment techniques was limited to the textile dye wastewater treatment because of the frequent clogging of dye molecules over the membrane pores. The selection of the membrane type and porosity of the filter mainly depends on the composition of the wastewater and optimum temperature required for the process; Chen et al. [82] investigated the dye removal using filtration process. The results from this study showed that the filtration membrane has given a good antifouling capacity while treatment time. The major drawback of this filtration technology includes high investment cost, generation of secondary waste streams and frequent membrane fouling [83].

2.3. Oxidation

Oxidation method is a type of treatment method for the removal of dyes from wastewater by utilizing oxidizing agents. In general, the two types such as chemical oxidation and UV-assisted oxidation using chlorine, ozone, Fenton's reagent, hydrogen peroxide (H_2O_2) and potassium permanganate ($KMnO_4$) have been employed for the removal of dyes from industrial wastewater, particularly those wastewater collected from primary wastewater treatment unit, that is, sedimentation process. These treatment methods are most commonly used methods for the treatment of dye wastewater because they required only less concentration and less time to react. These methods are used to partially or completely decompose the dye molecules. But, the complete degradation of dye compounds to carbon dioxide and water was studied theoretically. It is important to note that the catalyst and pH plays a vital role in the oxidation process for the removal of dyes from wastewater.

Generally, chlorine is most widely used as a disinfectant for water treatment because of its strong oxidizing power. This can be applied in the form of calcium hypochlorite and sodium hypochlorite. It is also widely used for the reduction of colour such as pulp and textile bleaching [10]. The water

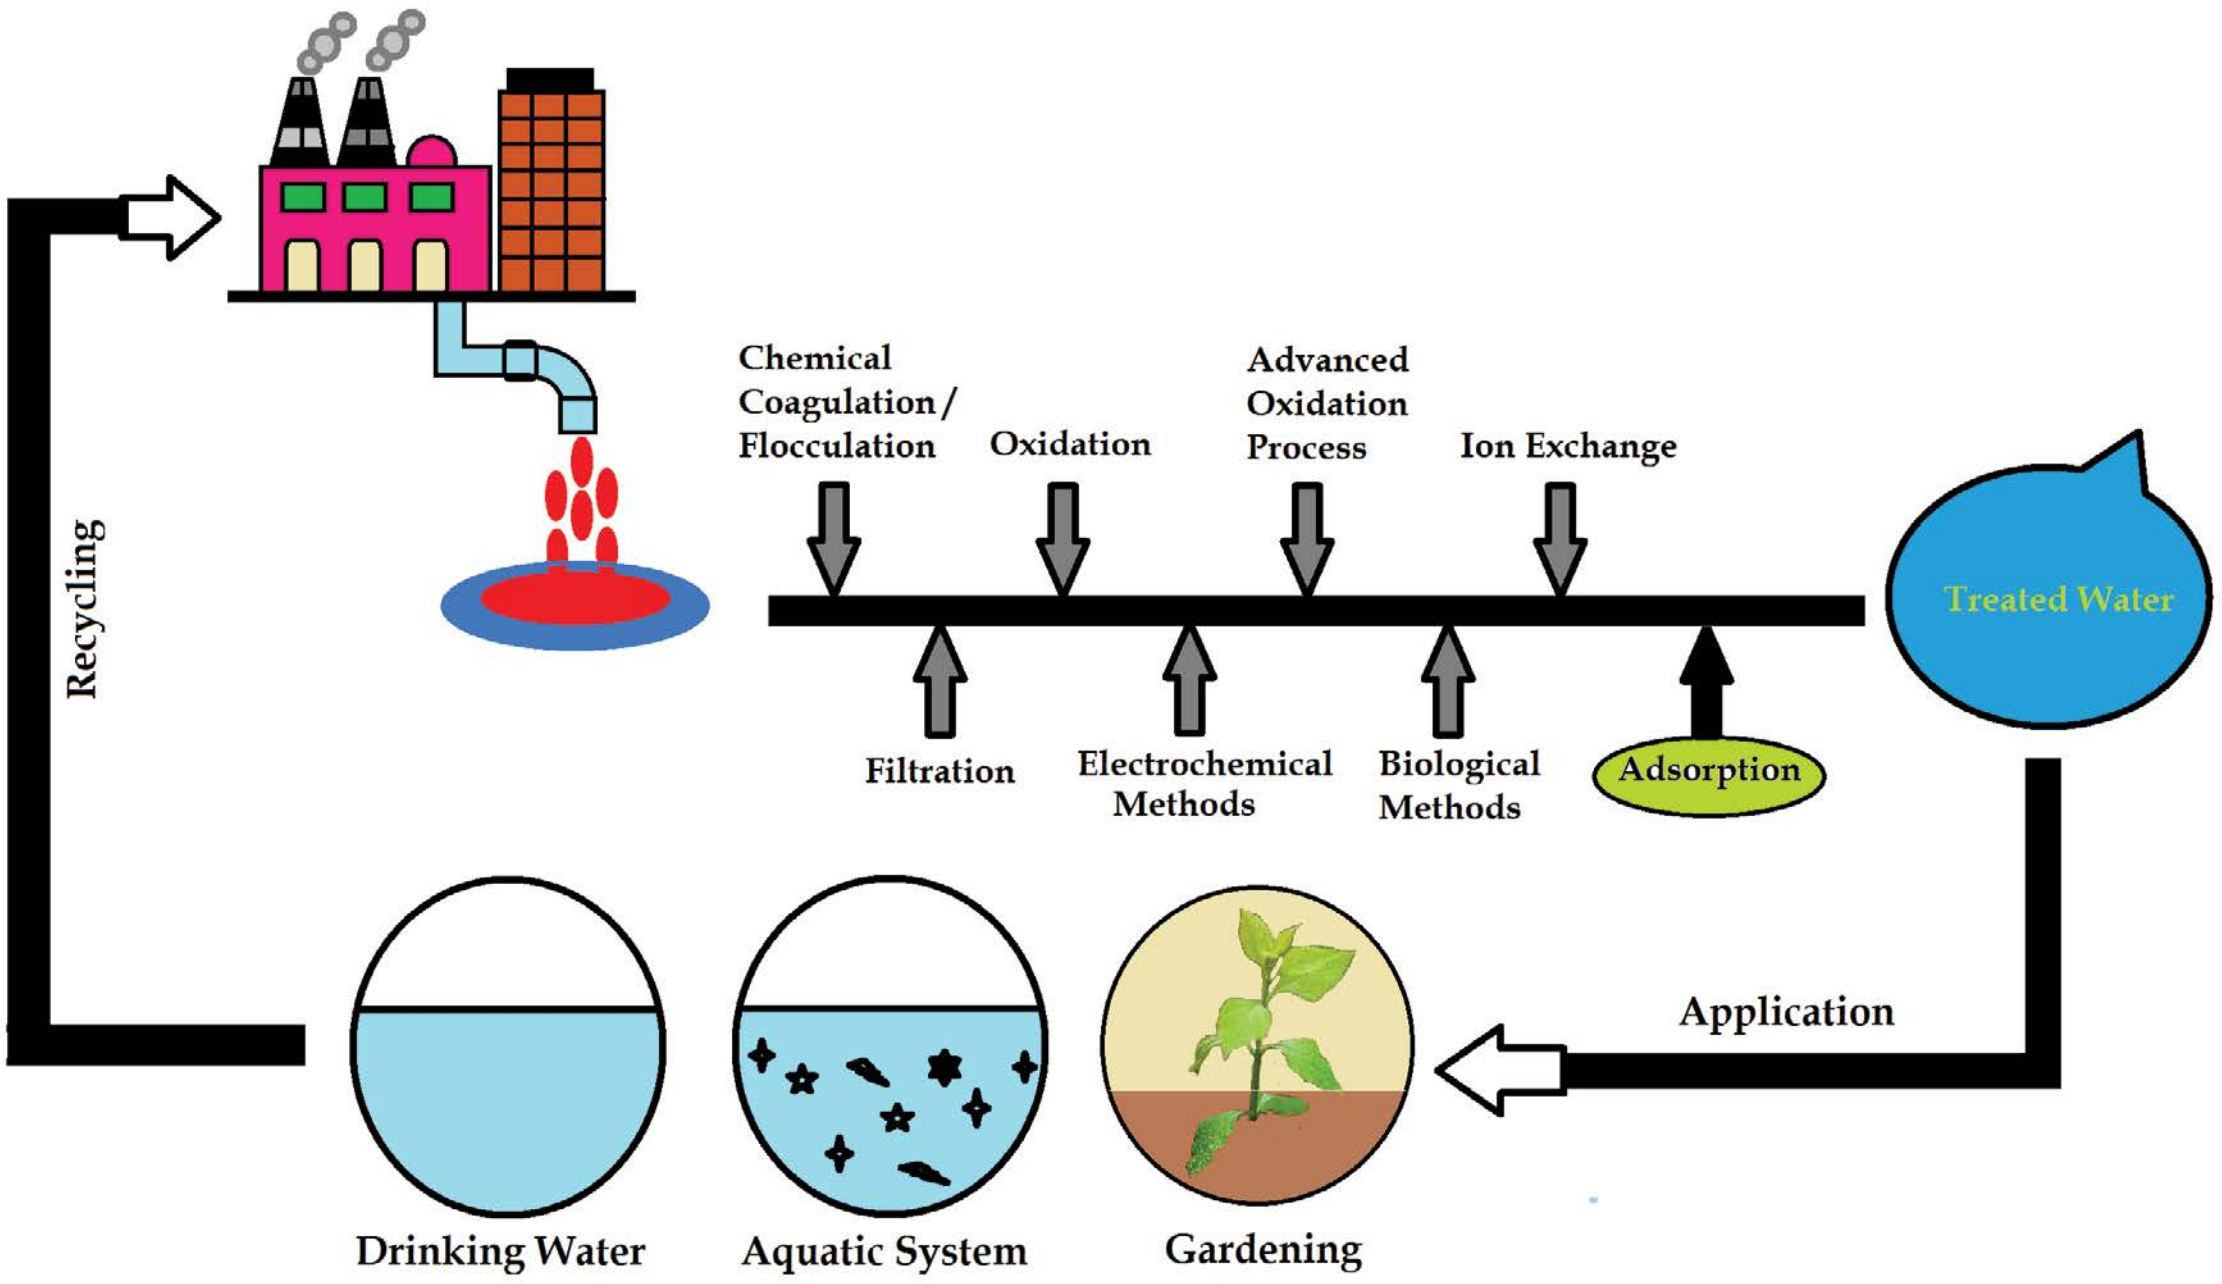

Fig. 1. Dye removal methods.

soluble dyes such as acid, reactive, direct and metal complex dyes are easily decolourized by hypochlorite but the water insoluble dyes include disperse and vat dyes are resistant to decolourization [10,84]. Generally, the reactive dyes need longer reaction time for its decolourization but the metal complexed dye wastewater remains halfway coloured even after the reaction time period was extended. The presence of amino or substituted amino groups on the naphthalene ring of the dye molecules is most vulnerable to chlorine and decolourize more easily than other dye molecules [85]. The oxidation of dye molecules can be improved by altering the pH of the system and also by providing the suitable catalysts. For example, the degradation of metal complex dyes liberates heavy metals such as copper, iron, nickel and chromium. These discharged metals are said to possess catalytic effects for improving the decolourization of the dye molecules. The use of chlorine gas is an inexpensive treatment technique for decolourizing the dye molecules but it leads to provide unavoidable side reactions. These side reactions generate organochlorine compounds, which include toxic trihalomethane that increases the absorbable organic halogens concentration of the treated water. The metals liberated after the degradation of metal complex dyes can cause corrosion in metallic vessels.

Ozone was seemed to be a potential agent for decolourizing the textile dye wastewater [86–93]. The ozonation for the removal of colour (reactive dyes) from the dye wastewater can be achieved in shorter contact time and it is an effective process for the harmful compounds discharged from the conventional reactive dyes [94]. The decolourization of reactive dye was studied and the ozonation effectively removed colour and chemical oxygen demand [88,95]. However, in some cases the ozonation does not influence the removal of chemical oxygen demand significantly [94,96]. The oxidation potential of ozone was observed as 1.5 times that of chlorine [97]. This treatment does not liberate the chlorinated disinfection by-products which are carcinogenic. Therefore, ozone technology was found to have high potential because of its high technical feasibility. However, the wide application of ozone in water and industrial effluent treatment was limited due to its high cost operation. This may be due to the mass transfer limitations stemming from the low solubility of the ozone and improper selection of the contactors without consideration of the operative reaction system. Ozone is normally generated in bulk quantities by high voltage electrical discharge across a thin gap of dry air or oxygen. The electrical discharge process can produce in addition to ozone, other short-lived species such as OH radicals, OH^+ ion, atomic hydrogen, electrons and oxygen atomic radicals [98–100]. The liberation of these species mainly depends on the reactor configuration and the voltage used. These reactive species can improve the rate of oxidation if they can react with the pollutants in the fluid before they decay [97].

Hydrogen peroxide is an extremely pale blue colour liquid and it gets converted to colourless liquid in a dilute solution. In addition, it is slightly more viscous than water. This hydrogen peroxide has potential oxidizing properties [10]. This is a powerful bleaching agent for bleaching paper besides other applications. In the year 1994, nearly 50% of the world's production of hydrogen peroxide was applied for paper and pulp bleaching [101]. This is also used for producing the peroxide enzymes, which are utilized for decolourization of dyes [102]. But this process depends on the pH and generates waste.

Fenton's reagent, a mixture of an iron catalyst and hydrogen peroxide, was applied to decolourize the coloured wastewater [103–107]. This reagent is stronger than hydrogen peroxide agent. Normally, this Fenton's reagent is effective in decolourization of both soluble and insoluble dye molecules. Some of the dyes including vat and disperse dyes are highly resistant against Fenton's reagent. The dyes such as remazol brilliant blue B, indanthrene blue GCD, sirrus supra blue BBR, helizarin blue BGT and irgalan blue FGL have been studied and reported that these dyes were significantly decolourized by Fenton's reagent [10]. It is also identified that the colour is not only removed but also observed that the total organic carbon, chemical oxygen demand (except for reactive dyes) and toxicity have been reduced. This treatment technique also applied for high suspended solids concentration and is suitable for wastewater treatment when the municipality allows the release of Fenton's sludge into sewage. In the aspect of biological point of view, the quality of the sludge is not only enhanced but the removal of phosphate was also observed. The major drawbacks of this treatment technique is that it is generally effective within the narrow pH range of less than 3.5 which involves the sludge production and required longer reaction time [108]. Advanced oxidation processes (AOPs), which include the generation of exceedingly responsive hydroxyl radical (HO·), have developed as outstanding water and wastewater treatment innovation for the decomposition or mineralization of a various scope of natural contaminants. A class of AOP comprises of photoactivated forms. The photoactivated responses are described by the free radical instrument started by the association of photons of a legitimate vitality level with the impetus photocatalytic oxidation). The present audit means to give a complete investigation on the system of UV-TiO_2 photocatalytic oxidation prepare, photocatalyst material, light sources and the sorts of photoreactors [109]. The proficiency of the framework is likewise influenced by the method of TiO_2 application as immobilized on surface or as suspension.

2.4. Electrochemical methods

Electrochemical treatment falls under tertiary treatment technique which also employed for the removal of colours from dye wastewater [110–112]. The main advantage of this treatment technology is its environmental compatibility due to the fact that its main reagent, that is, electron, is a clean reagent. Other advantages include its flexibility, high energy efficiency, amenability of automation and safety. The decolourization of the dye wastewater is attained either by electro-oxidation with non-soluble anodes or by electrocoagulation with soluble anodes [113–115]. The electrochemical treatment in dye removal is highly depending on the anode materials. Based on the anodic materials utilized, the efficiency will increase [116]. Some of the anodic materials include iron, boron-doped diamond electrode, etc., with various operating conditions have been employed for the electro-degradation of dye molecules [117–119]. The removal of colour from Direct Red 80 dye wastewater using three different electrode materials including iron, polypyrrole doped with chromium and boron-doped diamond electrode. This treatment method is active in the removal of colour from soluble and insoluble dyes with the reduction of chemical oxygen demand. It was observed that the extent of colour and organic load removal mainly depends on the types of anodic materials and the applied voltage. However, the main disadvantages are high cost for electricity, sludge production and pollution because of chlorinated organic and heavy metals due to indirect oxidation.

2.5. Advanced oxidation processes

AOPs are extremely efficient and novel treatment methods for the rapid elimination of many organic and inorganic substances [120–122]. Recently, AOPs have appeared as potentially effective treatment techniques for converting the organic pollutants into non-toxic substances [123–126]. This process is involving in the simultaneous utilization of more than a oxidation processes because in certain cases the single oxidation system is not enough for the total decomposition of the dye molecules. These AOPs utilize strong oxidizing agents such as hydroxyl radicals generated in situ which causes the series of reactions thereafter to convert the macromolecules into smaller and less harmful substances [125,126]. In most cases, the macromolecules are completely mineralized into carbon dioxide and water. The important advantage of AOPs as compared with the other treatment techniques is its easiness to handle and the generation of significantly less residues. The AOP techniques include ultraviolet (UV) photolysis, Fenton's reagent oxidation and sonolysis. Nidheesh et al. [127] conducted a study on advanced oxidation process in which they have explained about the anodic oxidation, electro-Fenton, peroxicoagulation, fered Fenton, anodic Fenton, photoelectro-Fenton, sonoelectro-Fenton, bioelectro-Fenton, etc. This study mentioned that complete oxidation of dyes is possible in the advanced oxidation process. This treatment technique has the capability of degrading the dye molecules at ambient temperature and pressure. These AOPs have an advantage over the biological wastewater treatment for waste effluents containing toxic or bioinhibitory contaminants. The different varieties of AOPs are used in chemical oxidation processes utilizing ozone, combined ozone and hydrogen peroxide, UV enhanced oxidation such as UV/hydrogen peroxide, UV/ozone, UV/air wet air oxidation and catalytic wet air oxidation (in this case, air is used as the oxidant). 10%–20% of colour was removed while using UV alone but when it was utilized along with hydrogen peroxide nearly 90% of the colour gets removed [128].

The combination of Fenton reaction and UV is called as photo-Fenton reaction [129]. The combination of these two treatment technologies is available to enhance the elimination of colourants from the dye wastewater [130–135]. The photo-Fenton reaction is highly effective than Fenton reaction at an optimum condition [130]. Photocatalysis is another AOP for the removal of pollutants from the waste stream [136–142]. In this treatment technique, the light energy from a light source triggers an electron from the valence band of the catalyst to the conduction band with a series of chemical reaction which results in the generation of hydroxyl radicals. The generated hydroxyl radicals have higher oxidizing potential which can easily oxidize most of the organic compounds. The different chalcogenides, that is, oxides such as TiO_2, CeO_2, ZrO_2, ZnO, etc. or sulphides such as ZnS, CdS, etc. have been utilized as a photocatalyst for the removal of different varieties of dyes including direct, reactive, vat and disperse dyes. Sonolysis is another treatment technique which utilizes the ultrasonic waves to decolourize and degrade the dye molecules [143–147]. The mechanism of sonolysis generally depends on the formation of short-lived radical species generated in violent cavitation events. The major drawbacks of AOPs are the generation of some unexpected by-products, complete mineralization is not possible and the process depends on the pH. The limitation of the process varies depending on the types of AOPs implemented for the particular type of wastewater. For example, the important operating parameters for the removal of colour by UV/H_2O_2 were hydrogen peroxide concentration, residential time, pH, UV radiation intensity, chemical structure of dye molecules and dye bath additives. However, the AOPs have proven to be effective and outstanding treatment technologies for the removal of colour from effluents but they are quite expensive especially for small-scale industries of developing countries.

2.6. Biological methods

Biological treatment technique is the most common and widely adopted treatment techniques for the removal of colour from the dye wastewater [148–158]. A variety of species have been employed for the decolourization and mineralization of the different dye molecules. The biological method provides significant advantages such as comparatively inexpensive, less operating costs and non-toxicity of the completely mineralized end products. These biological methods are classified into three categories, that is, aerobic, anaerobic, and combined effect of aerobic and anaerobic treatments.

The aerobic treatments are carried out in the presence of oxygen. The aerobic microorganisms such as bacteria and fungi are the two most important organisms that have been utilized for the effective treatment of dye wastewater. At aerobic situations, the enzymes secreted by the bacteria available in the wastewater breakdown the organic compounds. The identification, isolation and application of the aerobic bacteria are important steps in the biological treatment of different types of dye wastewater [158,159]. The different types of triphenylmethane dyes include malachite green, brilliant green, crystal violet, magenta, pararosaniline and ethyl violet have been effectively removed by the strain *Kurthia* sp. [160]. However, it is important to note that the synthetic dyes are not uniformly vulnerable to decomposition by activated sludge process in a conventional aerobic process. An attempt has been implemented to produce specific aerobic bacterial strains for the decolourization of the specific dye structure [161]. The fungal strains seemed to be capable of decolourizing the azo and triphenylmethane dyes [158–163]. Among the different fungi strains, *Phanerochaete chrysosporium* has been studied exclusively for the past two decades because of its ability to decolourize the different varieties of dyes [158,159,164,165]. Further, the microorganisms including *Cyathus bulleri*, *Rhyzopus oryzae*, *Funalia trogii*, *Coriolus versicolor*, *Streptomyces* sp., *Laetiporous sulphureus*, *Trametes versicolor* and other microorganisms have also been employed for the decolourization of dye wastewater [158,166–168]. The different operating parameters such as concentration of dye wastewater, initial pH and wastewater temperature affects the biological treatment of dye wastewater. The biological treatments are compatible for certain dyes and most of the dyes are recalcitrant to the biological breakdown or non-transformable under aerobic conditions [158,159,169]. The anaerobic treatments are carried out in the absence of oxygen. The anaerobic treatments have been applied for the decolourization of the different varieties of synthetic dyes [158,159,170–173]. In some cases, the anaerobic pre-treatment step is the cheapest and alternative to the aerobic system [171]. The expensive aeration and problems with the bulk sludge are avoided in the anaerobic system. However, the major drawbacks of this treatment techniques are biological oxygen demand removal is inadequate, incomplete mineralization of dyes, incomplete nutrient removal and sulphates are converted into sulphides [171]. The combined treatment of aerobic and anaerobic was implemented to effectively decolourize the textile industrial wastewater. The important advantage of this method is to provide complete mineralization which is frequently achieved due to the synergistic action of different organisms [158,174]. The reduction of azo bond was observed during the anaerobic conditions and the resulting colourless aromatic amines can be mineralized under aerobic conditions [175]. Hence, for the effective treatment of dye, the anaerobic decolourization followed by aerobic treatment was generally preferred [176]. Some of the major drawbacks of this biological treatment technologies are requirement of large land area, less flexibility in design and operation, prolonged time needed for decolourization–fermentation processes thereby making it unable to remove the dyes from wastewater on a continuous mode [158,177–179].

2.7. Ion exchange

Ion exchange is a reversible process where an ion from the solution is exchanged for a similarly charged ion attached to the solid resin [180]. This treatment was generally adopted for softening the salt water to provide drinking water [181]. Zeolites are one of the most important ion exchange materials used worldwide. This material is available naturally and also this was prepared synthetically. In 1934, Adams and Holmes found that the phenol–formaldehyde resin has cation exchange properties. This gives important information regarding the preparation of different types of resins including cationic and anionic ion exchange resins. Some of the polymeric materials holds an ion exchange mechanism which include polystyrene sulphonate, polystyrene phosphonate, polystyrene amidoxime, sulphonated phenolic resin, phenolic resin, polystyrene-based trimethyl benzyl ammonium, epoxy-polyamine and aminopolystyrene. The batch and fixed bed column studies have been employed for the elimination of contaminants from water.

The different experimental studies have been conducted for the removal of dyes from wastewater using the ion exchange resins [182–199]. The major drawbacks of ion exchange method are incapable of handling highly concentrated wastewater, matrix gets fouled by organics, non-selective and highly sensitive to pH of the wastewater.

2.8. Adsorption

Adsorption is a surface phenomenon and it is the process for the separation of mixtures on a laboratory and industrial scale which can be explained as the increase in concentration of a particular component at the interface between the two phases. The adsorption process has been effectively utilized for the removal of colour from wastewater [200–235].

The term 'adsorption' refers to process in which a material is concentrated over the solid surface from the liquid or gaseous surroundings. Adsorption on porous carbon was explained as early as 1550 B.C. in an ancient Egyptian papyrus and afterwards by Hippocrates and Pliny the Elder, which is importantly for medicinal applications. However, on scientific records the adsorption phenomenon was explained by Scheele in 1773 for gases exposed to carbon [200,236].

In 1785 it was continued by Lowitz for the reversible removal of colour and odourous compounds from water by wood charcoal. Larvitz in 1792 and Kehl in 1793 identified similar behaviour with vegetable and animal charcoals, respectively. However, for the first time in 1881, Kayser has introduced the term adsorption to differentiate the surface accumulation from intermolecular penetration. In addition, he explored that the adsorption process is a surface accumulation of material. Generally, it is important to differentiate the various types of adsorption process. If the attraction between the adsorbent and adsorbate is due to weak van der Waals forces, then this type of adsorption process is called as physical adsorption or physisorption. This type of adsorption process is a reversible process. Also, if the attractive forces are due to covalent bond then this type of adsorption process is called chemical adsorption or chemisorption. Because of the high bonding strength between the adsorbent and adsorbate in chemisorption process, it is very difficult to remove the adsorbed species from the solid surface. Generally, a good adsorbent should possess a porous structure. The time required to achieve the adsorption equilibrium should be as small as possible only then the dyes can be removed in lesser time.

Basically, adsorption of dyes mainly depends on the properties of the dyes and the surface properties of the adsorbent materials. Activated carbon (AC) is widely applied in the removal of dyes from wastewater. The commercial activated carbon produced from the different sources includes coal, coconut shells, charcoal, lignite, wood and sawdust. The two types of AC such as *H*-type and *L*-type have been produced. The *H*-type is the positive charge upon water and hydrophobic nature. The *L*-type is a negative charge upon water and hydrophilic in nature [202,237,238]. The activation of materials was carried out by partial oxidation for the purpose of developing pore structures in it. There are two types of activation which include physical and chemical activation.

Usually, the physical activation procedure needs high temperature and longer activation time as compared with the chemical activation. The AC requires a complete washing to remove the excess acids in the chemical activation method. AC can be in granular form, that is, granular activated carbon (GAC). The GAC can be produced from solid materials, which are used to remove the pollutants from wastewater because of its flexibility in continuous operation. Also there is no need to segregate the AC from bulk fluids. But, the slow intraparticle diffusion in GAC is a problem encountered in the application of the adsorption process in water treatment. AC can also be existing in the form of powdered activated carbon (PAC). Generally, PAC was added with fluids to be treated and then disposed off. The application of PAC presents some practical issues because of the requirement to separate the adsorbent from the fluid after usage.

PAC is also applied in the treatment of wastewater due to its low capital cost and less contact time, where it provides the large external surface area and a less diffusion resistance [239]. In addition to GAC and PAC, two other forms of activated carbons (ACs) also exist which include activated carbon pellet and activated carbon filter (ACF). The activated carbon pellet was generally produced using coal as a raw material. In this preparation procedure, the coal was pulverized and this was agglomerated with suitable binder and then physically activated. These pelletized ACs are generally available in the sizes of 1.5, 3 and 4 mm diameter. The ACF was generally produced from polymeric precursor such as polyacrylonitrile (PAN), pitch, cellulose and polyvinylchloride. The PAN-based carbon fibres predominately possess outstanding strength and modulus properties. The ACF can be prepared with a high modulus, albeit a lower strength using a pitch-based precursor. These carbon filters have been activated using the same procedures to produce the high surface area carbons [10].

The ACs are applied not only for dye removal [240–243] but also for other organic and inorganic pollutants removal such as heavy metals [244–248], phenols [249–253], pesticides [205,254,255], chlorinated hydrocarbons [256], humic substances [257], PCBs [258], detergents [259,260], organic compounds which cause taste and odour [261–263] and many other chemicals and organisms [263–270].

It is important to note that the AC is an effective and commercially applicable material for removing different kinds of dyes from water/wastewater. But its application is sometimes limited because of its high cost. The ACs after their application in the treatment of wastewater become saturated with the dye molecules and are no longer capable of further removal of dyes from wastewater. There are two possibilities of this spent AC may undergo: (i) disposal and (ii) regeneration. The spent AC will be available in more toxic form which increases the cost of disposal and also causes further pollution problem to the environment if it is directly disposed into the environment. The spent ACs have to be regenerated for further application in the treatment of dye wastewater. Some of the regeneration methods such as chemical, thermal, oxidation and electrochemical are available but the thermal method is the most common one [271–279]. It is also noted that the regeneration of ACs provided the additional cost for the treatment. The regeneration of spent ACs may lead to loss of carbon and also change in its properties as compared with the virgin AC. This creates awareness among the research scientists to work towards producing low-cost alternative adsorbents which may replace the existing ACs for the removal of dyes from wastewater.

Activated carbon (AC) has been widely used as adsorbent for the removal of dyes from wastewater but its high cost poses an economical problem. Hence, there is a need to produce cheap and easily available materials, which can be utilized more economically on large-scale operations. Owing to the economical problems, the research interest into the development of alternative adsorbents to substitute the costly AC has intensified in recent years. The attention has focussed on different natural solid materials, which are able to remove the dyes from wastewater at cheaper cost. Cost is an essential factor for comparison and selection of the suitable adsorbents. An adsorbent can be measured as a cheap materials if it requires the modest processing and available abundantly in nature. This may also be explained as an agricultural by-product or waste material from the industries and requires additional disposal cost. Some of the waste products from agricultural operations and industries, natural materials and biosorbents have been identified as potentially economical alternative adsorbents. Most of these materials have been employed for the removal of dyes from wastewater.

3. Adsorbent from agricultural wastes

Agricultural wastes are lignocellulosic compounds which mainly consist of cellulose, lignin and hemicelluloses [280,281]. Lignin is a polymeric compound that consists of aromatics and has a complex three-dimensional structure. The phenylpropane units in the lignin compounds are bound together to produce a very complex matrix. It consists of different functional groups including hydroxyl, methoxyl and carbonyl. The hemiceullose in the agricultural wastes is mostly soluble in alkali and more easily hydrolyzed. Also both hemicelluloses and cellulose consist of oxygen functional groups including hydroxyl, ether and carbonyl [282]. These functional groups play an essential part in the generation of adsorbents. Previously, some of the research scientists have utilized various precursors for the synthesis of ACs including waste plastics (polyethylene terephthalate and polyvinyl chloride), industrial wastes (polymeric residues, fly ash, pitch, etc.) and other wastes (sewage sludge, tires, etc.) [283]. Generally, it is an important task to produce AC with low cost for the commercial manufacturing industries.

Recently, some of the research groups have adopted agricultural wastes to produce AC because they contain high carbon content, low inorganics, require mechanical strength, low levels of ash content and low cost [281–285]. These materials are available in large amounts and are one of the most abundant renewable resources in the globe. These waste materials have small or no economical importance and often provide the disposal problem. Hence, there is an important requirement to valorize these low cost materials. The transformation of these waste materials into ACs would provide the significant economic value which helps to reduce the cost for the disposal of waste and most importantly which provides a potential low-cost alternative to the existing commercial ACs. These waste materials have been effectively utilized as raw materials for the preparation of AC with high adsorption capacity, required mechanical strength and low ash content [286,287]. Adsorption process utilizes the solid material as an adsorbent for the removal of different types of contaminants from wastewater. Among the different materials proposed as an adsorbent, AC is the most accepted material for the removal of pollutants from wastewater. AC is an amorphous material which is having high degree of porosity and these pores have been produced during its manufacture. The high porosity leads to removal of large amount of pollutants from wastewater [288–294]. The important factors considered for the selection of agricultural adsorbents are its low cost, availability and organic composition which provide higher affinity towards the specific dye wastewater. After utilized for wastewater treatment, these materials can be disposed to the environment without any complicated and expensive regeneration process because of their low cost.

The different types of agricultural waste materials have been utilized for the preparation of AC which includes corn straw [295], wheat straw [295], rice straw [296,297], sawdust [298–300], corncob [301,302], bagasse [301,303], cotton stalk [304], coconut husk [305], rice husks [298,306,307], tobacco stem [308], nut shells [309–311], soyabean oil cake [312], oil palm shell [313], oil palm fibre [314], vegetable residues [315], etc. Generally, there are two important steps in the synthesis of AC which include (i) carbonization of the materials below 1,000°C at an inert atmosphere and (ii) activation of the carbonized material (physical or chemical activation).

Physical activation is a method in which the forerunner is converted into AC utilizing gasses and is for the most part done in a two-stage handle [316]. Carbonization is the primary stage which involves the formation of a char (nonporous) by pyrolysis of the raw material at the temperature range of 400°C–850°C and sometimes it may be operated at 1,000°C in the nitrogen atmosphere. Activation is the second stage which includes making the contact of the char with an oxidizing gas, for example, carbon dioxide, steam, air or their blends, in the temperature of somewhere around 600°C and 900°C, which brings about the expulsion of the more complicated carbon and the arrangement of an all around created micro-pore structure. Generally, CO_2 is the activation gas because it is spotless, simple to handle and it encourages control of the activation process on account of the moderate reaction rate at temperatures around 800°C [316]. It is beneficial to note that the ACs prepared by physical activation did not have acceptable qualities to be utilized as adsorbents or as filters [284].

Chemical activation is a method, in which the carbonization and activation are happening simultaneously, with the precursor being blended with chemical activating agents as dehydrating agents and oxidants. This activation includes impregnation with chemicals, for example, H_3PO_4, $ZnCl_2$, NaOH, KOH and K_2CO_3 followed by heating under a nitrogen stream at temperatures in the scope of 450°C–900°C, contingent upon the impregnant utilized. This activation method was carried out in a single step and at lower temperatures. This method is available to prepare the superior porous structure in the adsorbent with the environmental concerns of using chemical agents for activation could also be produced. In addition, part of the utilized chemicals was easily recovered [285,316,317]. A two-stage process was available for the preparation of AC which includes physical and chemical processes [318]. It is also identified that an additional one more treatment step is available, that is, steam pyrolysis [319–323]. This treatment can be available in two forms: (i) the raw agricultural waste is heated at moderate temperatures between 500°C and 700°C under a flow of pure steam and (ii) the raw agricultural waste is heated at 700°C–800°C under a flow of steam. Numerous agricultural wastes include bagasse, straw, nut shell, grape seeds, almond shells, coconut husk, corn stover, oat hulls, peanut cherry, stones, apricot stones and hulls have been experimented with this procedure [324–337].

The recent review on literature indicates that the agricultural waste showed comparatively adequate removal efficiency as compared with the commercial materials. Dye decolourization method is not specific and depends on many parameters. There are many agricultural adsorbents available and which can act as alternatives to the existing AC but complete replacement is not possible. Generally, the selection of agricultural wastes is based on its low cost, availability and organic composition which shows the strong affinity for some identified dye wastewater.

3.1. Adsorbent produced from lignin

Lignin is a natural polymer composed mainly of aromatic compounds. It is available along with hemicelluloses goes about as a binding agent of cellulose strands in the structures of plants. The role of lignin is to give structural quality, give fixing of water directing framework that connects roots with leaves, and ensure plants against debasement [338]. It is a macromolecule, which comprises of alkylphenols and has an unpredictable three-dimensional structure. Lignin is covalently connected with xylans on account of hardwoods and with galactoglucomannans in softwoods [339]. The essential chemical phenylpropane units of lignin (principally syringyl, guaiacyl and *p*-hydroxy phenol) are fortified together by an arrangement of linkages to frame an extremely complex matrix. It contains an assortment of functional groups, for example, hydroxyl, methoxyl and carbonyl, which bestow a high extremity to the lignin macromolecule [340–345].

Lignin, a waste material or by-product released from paper mills in substantial amounts is utilized as a part of its raw state and also altered state for evacuation of contaminants by researchers/scientists. A spherical sulphonic lignin adsorbent was produced from a bamboo pulp mill by-product. This adsorbent was examined for the expulsion and recuperation of cationic dyes that include cationic turquoise GB, cationic red GTL and cationic yellow X-5GL from fluid arrangements [346]. Some of the research works are also available to explain the utilization of lignin as an effective adsorbent for the removal of dyes from wastewater [347–350].

3.2. Adsorbent produced from sawdust

Sawdust is a standout amongst the most engaging materials among agricultural waste materials, utilized for evacuating toxins, for example, colours, salts and overwhelming metals from water and wastewater [351]. The material comprises lignin, cellulose and hemicellulose, with polyphenolic groups assuming critical part to bind colours through various systems. By and large the adsorption happens by ion exchange, complexation and hydrogen bonding.

Different productive studies have been done on the expulsion of colours by sawdust [352–354]. Several researchers have used this saw dust in natural and its modified form for the removal of dyes from wastewater [355–363]. Many adsorption kinetics and isotherm models for the dye removal by sawdust have been reported by the researchers. Also the thermodynamics on the removal of dyes by the sawdust has been presented.

3.3. Adsorbent produced from rice husk

Rice husk is an agricultural waste which was obtained from the rice processing industry as a by-product. Generally, these industries are generating more than 100 million tonnes out of which 96% of the waste is being produced by the developing countries [286]. The usage of this wellspring of agricultural waste would take care of both a disposal issue and additionally access to a less expensive material for adsorption in water contaminations control framework [364–366]. The principle parts of rice husk are carbon and silica (15%–22% SiO_2), it can possibly be utilized as an adsorbent [37,367,368]. Many researchers have been using rice husk as an effective adsorbent for the removal of dyes from wastewater [366,369–378].

3.4. Adsorbent produced from waste peels

Among a few agricultural wastes that have been experimented on as adsorbents for wastewater treatment, the "waste peels" from fruits and vegetables are of awesome significance since the vast majority of the peels are disposed of as waste and discover no application anyplace, which here and there posture genuine transfer issues [2]. Most of the waste from homes mainly consist of these peel wastes. Additionally these wastes were generated from the fruits and vegetable industries during the process of selecting, sorting and boiling processes. Generally, these wastes are disposed into the environment or fed to the domesticated animals. The fruits and vegetable wastes and its by-products are produced in large quantity during the industrial operations which provide an impact over the environment and these wastes should be properly handled. Then again, they are extremely rich in bioactive segments that are considered to beneficially affect wellbeing [379]. These waste peels are natural, eco-friendly and monetary wellsprings of adsorbents. These wastes can be used in the expulsion of colours from wastewater.

Some of the waste peels include citrus peel waste (grapefruit peel waste, pomelo peel waste, orange peel waste and lemon peels), banana peel waste, cassava peel waste, jackfruit peel waste, pomegranate peel waste and garlic peel wastes have been applied for the removal of different kinds of pollutants from aqueous solution [2,380–398]. Adsorption influencing parameters for the removal of dyes from wastewater have been studied by the researchers. Adsorption equilibrium, kinetics and thermodynamics for the removal of colour from wastewater have also been investigated.

3.5. Adsorbent produced from other agricultural wastes

The numerous endeavours to discover cheap and effortlessly accessible adsorbents to evacuate the toxic pollutants from wastewater, for example, the agricultural wastes whereas per their physical–chemical attributes and ease they might be great potential adsorbents [11,217]. Agricultural preparations are accessible in expansive amounts the world over. Because of this, the huge amounts of agricultural wastes are rejected. These agricultural wastes are not only utilized in the removal of toxic dye from wastewater but also employed for the removal of various organic and inorganic toxic pollutants from wastewater.

Lignocellulosic materials comprise of three principle basic parts which are lignin, cellulose and hemicelluloses. Lignocellulosic materials additionally contain extractive basic segments which have small molecular size. Distinctive adsorbents obtained from agricultural wastes have been utilized for colour expulsion from wastewater and numerous investigations of colour adsorption by agricultural wastes are available. Agricultural and industrial processing units discard a lot of untreated waste which may contaminate the land, water and air, and accordingly harm the environment.

Then again, ill-advised treatment of these wastes causes comparable issues. Along these lines, administrative control of contaminations ought to be established to forestall or to minimize the exchange of unsafe material to different territories. Hence inside the most recent couple of years numerous thoughts have been acquainted all together with appropriately discard these wastes, for example, serious use as adsorbents for poison expulsion particularly for colour evacuation where it demonstrated high adsorption limit. These are renewable, accessible in vast sums and low cost when contrasted with different materials utilized as adsorbents. These wastes are superior to different adsorbents in light of the fact that the agricultural wastes are generally utilized without or with at least handling (washing, drying, crushing) and in this way lessen generation costs by utilizing a shoddy crude material and disposing of vitality expenses connected with warm treatment.

Some of the agricultural wastes derived from low cost and readily available resources such as grass waste, rice straw, barley straw, guava leaves, papaya seeds, plant leaf powder, banana waste, pumpkin seed palm kernel fibre, castor seed shell, pineapple stem, pumpkin seed hull, coffee husks, coconut husk, dehydrated peanut hull, *Parthenium hysterophorus*, coconut bunch waste, hazelnut shells, peanut hull, soy meal hull, yellow passion fruit waste, fruit juice residue, *Luffa cylindrica* fibres, jute waste, cereal chaff, wheat straw, bagasse, rubber seed shell, wheat shells, apricot shell, walnut shell, almond shell, cashew nut shell, coconut shells, citric acid, cotton and gingelly seed shell, lentil shell, rice shell, pine sawdust, groundnut shell, pongam seed shell, olive stone, coir pith, cane pith, plum kernel, sunflower stalk, white rice husk ash, white ash, wood-derived biochar, pinewood, neem bark, sky fruit husk, carbon cloth, sunflower hull, wheat stem, etc. have also been successfully adopted for the removal of colour from wastewater [287,399–411].

4. Adsorbent from industrial wastes

Generally industrial exercises create enormous measure of strong waste materials as by-products. Some of the by-products are reused and the remaining are disposed as landfills. In this manner, the likelihood of reuse in adsorption forms speak to a fascinating arrangement primarily in light of the fact that these industrial waste materials are accessible free of cost and cause significant disposal issue. As of late, various industrial wastes have been examined with or without treatment as adsorbents for the expulsion of poisons from wastewaters. Some of the industrial wastes include fertilizer industry wastes, fly ash, leather industry wastes, steel industry wastes, aluminium industry wastes and paper industry wastes [412]. Fly ash is a waste material generating from ignition operations. The primary employments of fly ash incorporate development of streets, blocks, concrete and so forth. The high concentration of silica and alumina in fly ash debris makes it decent contenders for use as a modest adsorbent for mass use [411,412]. The blast furnace slag, sludge and dust (steel industrial wastes) are the most experimented materials in the adsorption process. Red mud (aluminium industry waste) is a waste material framed amid the generation of alumina when the bauxite mineral is subjected to caustic leaching [413]. The poisonous quality and colloidal nature of red mud particles make a genuine contamination peril. Numerous propositions for the red mud use, for example, in the preparation of red mud blocks, as filler in black-top street development, as iron metal, and as a wellspring of different minerals [412]. After pre-treatment, the red mud is appropriate for the removal of Congo red from aqueous solution [413]. Rather, fertilizer industry additionally delivers various by-products in substantial concentrations which make genuine transfer issues and debase the encompassing environment. The industrial wastes have been successfully employed for the removal of dye pollutants from wastewater [414–435]. Because of the minimal effort and high accessibility of these wastes, it is not vital to have complicated regeneration operations. This type of low-cost adsorption methods have been attracted by many researchers/scientists. Be that as it may, the majority of the times the adsorption capacities of such adsorbents are not high, and thus, the study and investigation of more new adsorbents are still under advance. Diverse innovative absorbents used nowadays in the elimination of dyes and other toxic pollutants from aqueous solutions are depicted in Table 2. The objective of the present research is to create modest and viable adsorbents from agricultural waste, as another option to the current adsorbents.

5. Conclusion and future perspectives

This review article clarifies the various methodologies involved in the elimination of toxic dyes. This article mainly concentrates on the various economically feasible treatment technologies available for the treatment of dyes. Various methods such as filtration, coagulation, flocculation, oxidation, advanced oxidation process, electrochemical methods, ion exchange, biological methods and adsorption methods have been used in the treatment of industrial dye effluents. On analyzing all the above methodologies the physicochemical methods ate seemed to be somewhat effective but they are not used often due to their complexity and high cost. The chemical methods involve some more chemicals in the process and create secondary pollution which cannot be treated easily. Eventhough, the biological methods are

Table 2
Various biosorbents used in the elimination of harmful industrial dyes and other toxic pollutants

Dyes	Biosorbent	Adsorption capacity (mg g^{-1})	Reference
Chromium (VI)	Mixed waste tea	94.34	[436]
	Coffee ground	87.72	
Diamine Green B	Rice husk cellulose	207.15	[437]
Acid Black 24		268.88	
Congo Red		580.09	
2-Picoline	Almond shell and orange peels	166.7	[438]
	activated carbon	288.57	
Crystal violet	Peanut hull waste	100.6	[439]
Methylene blue	Cotton waste activated carbon	369.48	[440]
Eriochrome black T			
Rhodamine B	*Chlorella pyrenoidosa*	63.14	[441]
Methylene blue	*Phragmites australis*	41.2	[442]
Procion red H-E7B	*Nigrospora* biomass	188.79	[443]
Reactive blue BF-5G	Malt bagasse	42.58	[444]
Sulphur blue 15	Acidithiobacillus	1,428.6	[445]
Congo red	*Aspergillus carbonarius*	99.01	[446]
	Peniciliium glabrum	101.01	
Methylene blue	*Eucheuma spinosum*	833.33	[447]
Reactive red 198	*Nostoc linckia* HA 46 biomass	93.5	[448]
Amaranth dye	Water hyacinth	70	[449]
BEZAKTIV Red S-Max	*Phoenix dactylifera* rachis	196.08	[450]

economically feasible, this process is not preferred as it is time consuming and skilled labour. In midst of all the treatment technologies used in the wastewater treatment, the adsorption process is seemed to be the efficient technique in the elimination of the industrial dyes. This technique is simple, feasible, effective, efficient and eco-friendly in dye removal. The adsorbents used in this process are prepared from simple sources such as saw dust, agricultural wastes, lignin, waste peels, activated carbon and industrial waste which are all easily affordable and available in nature. These adsorbents possess high adsorption capacity and it is easily rejuvenated using simple chemicals. More research works have to be carried in this sector to lower the harmful effects of this textile dyes. The different surface modification methods must be optimized to prepare the efficient adsorbent for the elimination of dyes from industrial wastewater. Most of the researches on dye removal using low cost methods are dealt with batch adsorption process and this information must be designed for the scale up studies. The life cycle analysis of the prepared material must be evaluated to check the repeatability of the adsorbent usage and its disposal scenario. The regeneration procedure for the spent adsorbent must be properly deviced to predict the proper regenerating methods.

References

[1] I. Anastopoulos, G.Z. Kyzas, Agricultural peels for dye adsorption: a review of recent literature, J. Mol. Liq., 200 (2014) 381–389.

[2] A. Bhatnagar, M. Sillanpää, A. Witek-Krowiak, Agricultural waste peels as versatile biomass for water purification – a review, Chem. Eng. J., 270 (2015) 244–271.

[3] A. Ayati, M.N. Shahrak, B. Tanhaei, M. Sillanpää, Emerging adsorptive removal of azo dye by metal–organic frameworks, Chemosphere, 160 (2016) 30–44.

[4] C. Santhosh, V. Velmurugan, G. Jacob, S.K. Jeong, A.N. Grace, A. Bhatnagar, Role of nanomaterials in water treatment applications: a review, Chem. Eng. J., 306 (2016) 1116–1137.

[5] H.M. Raghunath, Hydrology: Principles, Analysis, Design, New Age International Publishers, India, 2006.

[6] Water Pollution, August, National Water Awareness Campaign, Gaia Atlas of Planet Management, The Guardian, 2003.

[7] R. Sivashankar, A.B. Sathya, K. Vasantharaj, V. Sivasubramanian, Magnetic composite an environmental super adsorbent for dye sequestration – a review, Environ. Nanotechnol. Monit. Manage., 1–2 (2014) 36–49.

[8] P.A. Carneiro, G.A. Umbuzeiro, D.P. Oliveira, M.V.B. Zanoni, Assessment of water contamination caused by a mutagenic textile effluent/dyehouse effluent bearing disperse dyes, J. Hazard. Mater., 174 (2010) 694–699.

[9] S. Natarajan, H.C. Bajaj, R.J. Tayade, Recent advances based on the synergetic effect of adsorption for removal of dyes from waste water using photocatalytic process, J. Environ. Sci., 65 (2018) 201–222.

[10] V.K. Gupta, Suhas, Application of low-cost adsorbents for dye removal – a review, J. Environ. Manage., 90 (2009) 2313–2342.

[11] M. Rafatullah, O. Sulaiman, R. Hashim, A. Ahmad, Adsorption of methylene blue on low-cost sorbents: a review, J. Hazard. Mater., 177 (2010) 70–80.

[12] M. Ghaedi, S. Heidarpour, S.N. Kokhdan, Y.Z. SahFu, T. Viraraghavan, Fungal decolorization of dye wastewaters: a review, Bioresour. Technol., 79 (2001) 251–262.

[13] K.A.G. Gusmao, L.V.A. Gurgel, T.M.S. Melo, L.F. Gil, Adsorption studies of methylene blue and gentian violet on sugarcane bagasse modified with EDTA dianhydride (EDTAD) in aqueous solutions: kinetic and equilibrium aspects, J. Environ. Manage., 118 (2013) 135–143.

[14] L. Cottet, C.A.P. Almeida, N. Naidek, M.F.Viante, M.C. Lopes, N.A. Debacher, Adsorption characteristics of montmorillonite clay modified with iron oxide with respect to methylene blue in aqueous media, Appl. Clay Sci., 95 (2014) 25–31.

[15] X. Liu, J. Luo, Y. Zhu, Y. Yang, S. Yang, Removal of methylene blue from aqueous solutions by an adsorbent based on metal-organic framework and polyoxometalate, J. Alloys Comp., 648 (2015) 986–993.

[16] H. Aysan, S. Edebali, C. Ozdemir, M.C. Karakaya, N. Karakaya, Use of chabazite, a naturally abundant zeolite, for the investigation of the adsorption kinetics and mechanism of methylene blue dye, Microporous. Mesoporous. Mater., 235 (2016) 78–86.

[17] A. Mittal, J. Mittal, A. Malviya, D. Kaur, V.K. Gupta, Decoloration treatment of a hazardous triarylmethane dye, Light Green SF (Yellowish) by waste material adsorbents, J. Colloid Interface Sci., 342 (2010) 518–527.

[18] A.K. Verma, R.R. Dash, P. Brunia, A review on chemical coagulation/flocculation technologies for removal of colour from textile wastewaters, J. Environ. Manage., 93 (2012) 154–168.

[19] M. Auta, B.H. Hameed, Acid modified local clay beads as effective low-cost adsorbent for dynamic adsorption of methylene blue, J. Ind. Eng. Chem., 19 (2013) 1153–1161.

[20] A.N. Kabra, R.V. Khandare, S.P. Govindwar, Development of a bioreactor for remediation of textile effluent and dye mixture: a plant–bacterial synergistic strategy, Water Res., 47 (2010) 1035–1048.

[21] M. Dastkhoon, M. Ghaedi, A. Asfaram, A. Goudarzi, S.M. Langroodi, I. Tyagi, S. Agarwal, V.K. Gupta, Ultrasound assisted adsorption of malachite green dye onto ZnS:Cu-NPAC: equilibrium isotherms and kinetic studies - response surface optimization, Sep. Purif. Technol., 156 (2015) 780–788.

[22] A. Elhalil, H. Tounsadi, R. Elmoubarki, F.Z. Mahjoubi, M. Farnane, M. Sadiq, M. Abdennouri, S. Qourzal, N. Barka, Factorial experimental design for the optimization of catalytic degradation of malachite green dye in aqueous solution by Fenton process, Water Res. Ind., 15 (2016) 41–48.

[23] D. Robati, M. Rajabi, O. Moradi, F. Najafi, I. Tyagi, S. Agarwal, V.K. Gupta, Kinetics and thermodynamics of malachite green dye adsorption from aqueous solutions on graphene oxide and reduced graphene oxide, J. Mol. Liq., 214 (2016) 259–263.

[24] B. Amith, D. Sivanesan, K. Kannan, C. Tapan, Kinetics of decolorization and biotransformation of Direct Black 38 by *C. hominis* and *P. Stutzeri*', Appl. Microbiol. Biotechnol., 74 (2007) 1145–1152.

[25] P. Monash, G. Pugazhenthi, Adsorption of crystal violet dye from aqueoussolution using mesoporous materials synthesized at room temperature, Adsorption, 15 (2009) 390–405.

[26] A.K. Samanta, P. Agarwal, Application of natural dyes on textiles, Indian J. Fibre Tex. Res., 34 (2009) 384–399.

[27] Demirbas, Agricultural based activated carbons for the removal of dyes from aqueous solutions: a review, J. Hazard. Mater., 167 (2009) 1–9.

[28] Forgacs, T. Cserhati, G. Oros, Removal of synthetic dyes from wastewaters: a review, Environ. Int., 30 (2004) 953–971.

[29] G. Mishra, M. Tripathy, A critical review of the treatment for decolorization of textile effluent, Colourage, 40 (1993) 35–38.

[30] E. Eren, B. Afsin, Investigation of a basic dye adsorption from aqueous solution onto raw and pre-treated sepiolite surfaces, Dyes Pigm., 73 (2007) 162–167.

[31] O.D. Tyagi, M.S. Yadav, M. Yadav, A Textbook of Synthetic Dyes, Vol. 67, Anmol Private Limited, India, 2002.

[32] E. Eren, Investigation of a basic dye removal from aqueous solution onto chemically modified *Unye bentonite*, J. Hazard. Mater., 166 (2009) 88–93.

[33] K. Hunger, Industrial Dyes, Chemistry, Properties, Applications, Wiley-VCH. Weinheim, Germany, 2003.

[34] A. Tabak, E. Eren, B. Afsin, B. Caglar, Determination of adsorptive properties of a Turkish Sepiolite for removal of Reactive Blue 15 anionic dye from aqueous solutions, J. Hazard. Mater., 16 (2009) 1087–1094.

[35] A.A. Attia, W.E. Rashwan, S.A. Khedr, Capacity of activated carbon in the removal of acid dyes subsequent to its thermal treatment, Dyes Pigm., 69 (2006) 128–136.

[36] I.M. Banat, P. Nigam, D. Singh, R. Marchant, Microbial decolorization oftextile-dye containing effluents: a review, Bioresour. Technol., 58 (1996) 217–227.

[37] V. Vadivelan, K.V. Kumar, Equilibrium, kinetics, mechanism, and process design for the sorption of methylene blue onto rice husk, J. Colloid Interface Sci., 286 (2005) 90–100.

[38] L. Bulgariu, L.B. Escudero, O.S. Bello, M. Iqbal, J. Nisar, K.A. Adegoke, F. Alakhras, M. Kornaros, I. Anastopoulos, The utilization of leaf-based adsorbents for dyes removal: a review, J. Mol. Liq., 276 (2019) 728–747.

[39] M. Ghaedi, F.N. Azad, K. Dashtian, S. Hajati, A. Goudarzi, M. Soylak, Central composite design and genetic algorithm applied for the optimization of ultrasonic-assisted removal of malachite green by ZnO Nanorod-loaded activated carbon, Spectrochim. Acta. Part A, 167 (2016) 157–164.

[40] M. Ghasemi, S. Mashhadi, M. Asif, I. Tyagi, S. Agarwal, V.K. Gupta, Microwave-assisted synthesis of tetraethylenepentamine functionalized activated carbon with high adsorption capacity for malachite green dye, J. Mol. Liq., 213 (2016) 317–325.

[41] M. Rajabi, B. Mirza, K. Mahanpoor, M. Mirjalili, F. Najafi, O. Moradi, H. Sadegh, R. Shahryari-ghoshekandi, M. Asif, I. Tyagi, S. Agarwal, V.K. Gupta, Adsorption of malachite green from aqueous solution by carboxylate group functionalized multi-walled carbon nanotubes: determination of equilibrium and kinetics parameters, J. Ind. Eng. Chem., 34 (2016) 130–138.

[42] F. Zhang, X. Chen, F. Wu, Y. Ji, High adsorption capability and selectivity of ZnO nanoparticles for dye removal, Colloids Surf. A, 509 (2016) 474–483.

[43] Y. Li, Q. Du, T. Liu, X. Peng, J. Wang, J. Sun, Y. Wang, S. Wu, Z. Wang, Y. Xia, L. Xia, Comparative study of Methylene Blue dye adsorption onto activated carbon, graphene oxide, and carbon nanotubes, Chem. Eng. Res. Des., 91 (2013) 361–368.

[44] U. Pal, A. Sandoval, S.I. U Madrid, G. Corro, V. Sharma, P. Mohanty, Mixed titanium, silicon, and aluminum oxide nanostructures as novel adsorbent for removal of rhodamine 6G and methylene blue as cationic dyes from aqueous solution, Chemosphere, 163 (2016) 142–152.

[45] H.D. Setiabudi, R. Jusoh, S.F.R.M. Suhaimi, S.F. Masrur, Adsorption of methylene blue onto oil palm (*Elaes guineensis*) leaves: process optimization, isotherm, kinetics and thermodynamic studies, J. Taiwan. Inst. Chem. Eng., 63 (2016) 363–370.

[46] S. Ramachandani, M. Das, A. Joshi, S.K. Khanna, Effect of oral and parental administration of metanil yellow on some hepatic and intestinal biochemical parameters, J. Appl. Toxicol., 17 (1997) 85–91.

[47] M. Das, S. Ramchandani, R.K. Upreti, S.K. Khanna, Metanil Yellow: a biofunctional inducer of hepatic phase I and phase II xenoblastic-metabolising enzymes, Food Chem. Toxicol., 35 (1997) 835–838.

[48] S. Gupta, M. Sundarrajan, K.V.K. Rao, Tumour promotion by metanil yellow and malachite green during rat hepatocarcinogenesis is associated with dys-regulated expression of cell cycle regulatory proteins, Teratog. Carcinog. Mutagen., 1 (2003) 301–312.

[49] S.M. Sachdeva, K.V. Mani, S.K. Adval, V.P. Jalpota, K.C. Rasela, D.S. Chadha, Acquired toxic methaemoglobinaemia, J. Assoc. Physicians India, 40 (1992) 239–240.

[50] S.S. Chandro, T. Nagaraja, A food-poisoning outbreak with chemical dye, an investigation report, Med. J. Armed Forces India, 43 (1987) 291–300.

[51] B.M. Hausen, A case of allergic contact dermatitis due to metanil yellow, Contact Dermatitis, 31 (1994) 117–118.

[52] H. Tiwari, Assessment of teratogenecity and embryo toxicity of dye wastewater untreated sludge from sanganer on swiss albino mice when administered during growth period of gestation, J. Health Med. Inf., 3 (2012) 1–5.

[53] S. Sivamani, B.L. Grace, Removal of dyes from wastewater using adsorption – a review, Int. J. Biosci. Technol., 2 (2009) 47–51.

[54] M.T. Yagub, T.K. Sen, S. Afroze, H.M. Ang, Dye and its removal from aqueous solution by adsorption: a review, Adv. Colloid Interface Sci., 209 (2014) 172–184.

[55] A.R. Warade, R.W. Gaikwad, R.S. Sapkal, V.S. Sapkal, Study of removal techniques for dyes by adsorption: a review, Int. J. Adv. Res. Innovat. Ideas Educ., 2 (2016) 3851–3868.

[56] V. Katheresan, J. Kansedo, S.Y. Lau, Efficiency of Various Recent Wastewater Dye Removal Methods: A Review, Biochem. Pharmacol., 6 (2018) 4676–4679.

[57] B.Y. Shi, G.H. Li, D.S. Wang, C.H. Feng, H.X. Tang, Removal of direct dyes by coagulation: the performance of preformed polymeric aluminum species, J. Hazard. Mater., 143 (2007) 567–574.

[58] Y. Zhou, Z. Liang, Y. Wang, Decolorization and COD removal of secondary yeast wastewater effluents by coagulation using aluminum sulphate, Desalination, 225 (2018) 301–311.

[59] N.A. Oladoja, Headway on natural polymeric coagulants in water and wastewater treatment operations, J. Water Process. Eng., 6 (2015) 174–192.

[60] A. Mishra, M. Bajpai, The flocculation performance of *Tamarindus mucilage* in relation to removal of vat and direct dyes, Bioresour. Technol., 97 (2006) 1055–1059.

[61] A. Mishra, M. Bajpai, S. Pandey, Removal of dyes by biodegradable flocculants: a lab scale investigation, Sep. Sci. Technol., 41 (2006) 583–593.

[62] Q.Y. Yue, B.Y. Gao, Y. Wang, H. Zhang, X. Sun, S.G. Wang, R.R. Gu, Synthesis of polyamine flocculants and their potential use in treating dye wastewater, J. Hazard. Mater., 152 (2008) 221–227.

[63] X. Huang, B. Gao, Q. Yue, Y. Zhang, S. Sun, Compound bioflocculant used as a coagulation aid in synthetic dye wastewater treatment: the effect of solution pH, Sep. Purif. Technol., 154 (2015) 108–114.

[64] G. Vijayaraghavan, T. Sivakumar, A. Vimal Kumar, Application of plant based coagulants for wastewater treatment, Int. J. Adv. Eng. Res. Stud., 1 (2011) 88–92.

[65] Y. Wei, A. Ding, L. Dong, Y. Tang, F. Yu, X. Dong, Characterisation and coagulation performance of an inorganic coagulant - poly-magnesium-silicate-chloride in treatment of simulated dyeing wastewater, Colloids Surf. A, 470 (2015) 137–141.

[66] S. Jorfi, G. Barzegar, M. Ahmadi, R.D.C. Soltani, N.A.J. Haghighifard, A. Takdastan, R. Saeedi, M. Abtahif, Enhanced coagulation-photocatalytic treatment of Acid red 73 dye and real textile wastewater using UVA/synthesized MgO nanoparticles, J. Environ. Manage., 171 (2016) 111–118.

[67] H. Li, S. Liu, J. Zhao, N. Feng, Removal of reactive dyes from wastewater assisted with kaolin clay by magnesium hydroxide coagulation process, Colloids Surf. A, 494 (2016) 222–227.

[68] A. Ndabigengesere, K.S. Narasiah, Quality of water treated by coagulation using *Moringa oleifera* seeds, Water Res., 32 (1998) 781–791.

[69] J.W. Lee, S.P. Choi, R. Thiruvenkatachari, W.G. Shim, H. Moon, Evaluation of the performance of adsorption and coagulation processes for the maximum removal of reactive dyes, Dyes Pigm., 69 (2006) 196–203.

[70] F.I. Hai, K. Yamamoto, K. Fukushi, Hybrid treatment systems for dye wastewater, Crit. Rev. Environ. Sci. Technol., 37 (2007) 315–377.

[71] C. Ruden, Acrylamide and cancer risk - expert risk assessments and the public debat, J. Food Chem. Toxicol., 42 (2007) 335–349.

[72] N. Al-Bastaki, Removal of methyl orange dye and Na_2SO_4 salt from synthetic waste water using reverse osmosis, Chem. Eng. Process. Process Intensif., 43 (2004) 1561–1567.

[73] G. Capar, L. Yilmaz, U. Yetis, Reclamation of acid dye bath wastewater: effect of pH on nanofiltration performance, J. Membr. Sci., 281 (2006) 560–569.

[74] M. Amini, M. Arami, N.M. Mahmoodi, A. Akbari, Dye removal from colored textile wastewater using acrylic grafted nanomembrane, Desalination, 267 (2011) 107–113.

[75] A.Y. Zahrim, N. Hilal, Treatment of highly concentrated dye solution by coagulation/flocculation-sand filtration and nanofiltration, Water Res. Ind., 3 (2013) 23–34.

[76] Y. Zheng, G. Yao, Q. Cheng, S. Yu, M. Liu, C. Gao, Positively charged thin-film composite hollow fiber nanofiltration membrane for the removal of cationic dyes through submerged filtration, Desalination, 328 (2013) 42–50.

[77] G. Jie, Z. Kongyin, Z. Xinxin, C. Zhijiang, C. Min, C. Tian, W. Junfu, Preparation and characterization of carboxyl multi-walled carbon nanotubes/calcium alginate composite hydrogel nano-filtration membrane, Mater. Lett., 157 (2015) 112–115.

[78] J. Guo, Q. Zhang, Z. Cai, K. Zhao, Preparation and dye filtration property of electrospun polyhydroxybutyrate–calcium alginate/carbon nanotubes composite nanofibrous filtration membrane, Sep. Purif. Technol., 161 (2016) 69–79.

[79] N.P. Cheremisinoff, Handbook of Water and Wastewater Treatment Technologies, Butterworth-Heinemann, Boston, 2002.

[80] S.A. Avlonitis, I. Poulios, D. Sotiriou, M. Pappas, K. Moutesidis, Simulated cotton dye effluents treatment and reuse by nanofiltration, Desalination, 221 (2008) 259–267.

[81] O. Marmagne, C. Coste, Color removal from textile plant effluents, Am. Dyestuff. Rep., 85 (1996) 15–20.

[82] W. Chen, J. Mo, X. Du, Z. Zhang, W. Zhang, Biomimetic dynamic membrane for aquatic dye removal, Water Res., 151 (2019) 243–251.

[83] W.J. Lau, A.F. Ismail, Polymeric nanofiltration membranes for textile dye wastewater treatment: preparation, performance evaluation, transport modelling, and fouling control: a review, Desalination, 245 (2009) 321–348.

[84] C.G. Namboodri, W.S. Perkins, W.K. Walsh, Decolorizing dyes with chlorine and ozone, Am. Dyest. Rep., 83 (1994) 17–22.

[85] T. Omura, Design of chlorine-fast reactive dyes: Part 4: degradation of amino containing azo dyes by sodium-hypochlorite, Dyes Pigm., 26 (1994) 33–50.

[86] C. Frijters, R. Vos, G. Scheffer, R. Mulder, Decolorizing and detoxifying textile wastewater, containing both soluble and insoluble dyes, in a full scale combined anaerobic/aerobic system, Water Res., 40 (2006) 1249–1257.

[87] O.S.G.P. Soares, J.J.M. Orfao, D. Portela, A. Vieira, M.F.R. Pereira, Ozonation of textile effluents and dye solutions under continuous operation: influence of operating parameter, J. Hazard. Mater., 137 (2006) 1664–1673.

[88] A.B. dos Santos, F.J. Cervantes, J.B. van Lier, Review paper on current technologies for decolourisation of textile wastewaters: perspectives for anaerobic biotechnology, Bioresour. Technol., 98 (2007) 2369–2385.

[89] J. Wu, H. Doan, S. Upreti, Decolorization of aqueous textile reactive dye by ozone, Chem. Eng. J., 142 (2008) 156–160.

[90] A.C. Gomes, L.R. Fernandes, R.M.S. Simoes, Oxidation rates of two textile dyes by ozone: effect of pH and competitive kinetics, Chem. Eng. J., 189–190 (2012) 175–181.

[91] J.B. Parsa, S.H. Negahdar, Treatment of wastewater containing Acid Blue 92 dye by advanced ozone-based oxidation methods, Sep. Purif. Technol., 98 (2012) 315–320.

[92] S. Sharma, J. Buddhdev, M. Patel, J.P. Ruparelia, Studies on Degradation of Reactive Red 135 Dye in Wastewater using Ozone, Procedia Eng., 51 (2013) 451–455.

[93] D. Ge, Z. Zeng, M. Arowo, H. Zou, J. Chen, L. Shao, Degradation of methyl orange by ozone in the presence of ferrous and persulfate ions in a rotating packed bed, Chemosphere, 146 (2016) 413–418.

[94] M. Sundrarajan, G. Vishnu, K. Joseph, Ozonation of light-shaded exhausted reactive dye bath for reuse, Dyes Pigm., 75 (2007) 273–278.

[95] M. Senthilkumar, M. Muthukumar, Studies on the possibility of recycling reactive dye bath effluent after decolouration using ozone, Dyes Pigm., 72 (2007) 251–255.

[96] E.H. Snider, J.J. Porter, Ozone treatment of dye waste, J. Water Pollut. Control Fed., 46 (1974) 886–894.

[97] K.K. Panda, A.P. Mathews, Ozone oxidation kinetics of Reactive Blue 19 anthraquinone dye in a tubular in situ ozone generator and reactor: modeling and sensitivity analyses, Chem. Eng. J., 255 (2014) 553–567.

[98] W.F.L.M. Hoeben, E.M. van Veldhuizen, G.M.W. Kroesen, Gas phase corona discharge for oxidation of phenol in an aqueous solution, J. Phys., 32 (1999) 133–137.

[99] W.T. Shin, S. Yiacoumi, C. Tsouris, S. Dai, A pulseless corona-discharge process for the oxidation of organic compounds in water, Ind. Eng. Chem. Res., 39 (2000) 4408–4414.

[100] N. Sano, T. Kawashima, J. Fujikawa, T. Fujimoto, T. Kitai, T. Kanki, Decomposition of organic compounds in water by direct contact of corona discharge: influence of discharge conditions, Ind. Eng. Chem. Res., 41 (2002) 5906–5911.

[101] R. Hage, A. Lienke, Applications of transition-metal catalysts to textile and wood-pulp bleaching, Angew. Chem. Int. Ed., 23 (2005) 206–222.

[102] M. Morita, R. Ito, T. Kamidate, H. Watanabe, Kinetics of peroxidase catalyzed decoloration of Orange II with hydrogen peroxide, Tex. Res. J., 66 (1996) 470–473.

[103] S. Meric, D. Kaptan, C. Tunay, Removal of color and COD from a mixture of four reactive azo dyes using Fenton oxidation process, J. Environ. Sci. Health A, 38 (2003) 2241–2250.

[104] S. Wang, A Comparative study of Fenton and Fenton-like reaction kinetics in decolourisation of wastewater, Dyes Pigm., 76 (2008) 714–720.

[105] D.H. Khandelwal, R. Ameta, Use of photo-Fenton reagent in the degradation of basic yellow 2 in aqueous medium, Res. J. Recent. Sci., 2 (2013) 39–43.

[106] M.E. Haddad, A. Regti, M.R. Laamari, R. Mamouni, N. Saffaj, Use of Fenton reagent as advanced oxidative process for removing textile dyes from aqueous solutions, J. Mater. Environ. Sci., 5 (2014) 667–674.

[107] N.A. Youssef, S.A. Shaban, F.A. Ibrahim, A.S. Mahmoud, Degradation of methyl orange using Fenton catalytic reaction, Egypt. J. Petrol., 5 (2016) 317–321.

[108] M.M. Cheng, W.H. Ma, J. Li, Y.P. Huang, J.C. Zhao, Visible-light-assisted degradation of dye pollutants over Fe(III)-loaded resin in the presence of H_2O_2 at neutral pH values, Environ. Sci. Technol., 38 (2004) 1569–1575.

[109] R. Thiruvenkatachari, S. Vigneswaran, I.S. Moon, A review on UV/TiO_2 photocatalytic oxidation process, Korean J. Chem. Eng., 25 (2008) 64–72.

[110] S.H. Lin, C.F. Peng, Treatment of textile wastewater by electrochemical method, Water Res., 28 (1994) 277–282.

[111] V.K. Gupta, R. Jain, S. Varshney, Electrochemical removal of the hazardous dye Reactofix Red 3 BFN from industrial effluents, J. Colloid Interface Sci., 312 (2007) 292–296.

[112] S. Zodi, B. Merzouk, O. Potier, F. Lapicque, J.P. Leclerc, Direct red 81 dye removal by a continuous flow electrocoagulation/flotation reactor, Sep. Purif. Technol., 108 (2007) 215–222.

[113] B. Merzouk, B. Gourich, K. Madani, C.H. Vial, A. Sekki, Removal of a disperse red dye from synthetic wastewater by chemical coagulation and continuous electrocoagulation. A comparative study, Desalination, 272 (2012) 246–253.

[114] E. Pajootan, M. Arami, N.M. Mahmood, Binary system dye removal by electrocoagulation from synthetic and real colored wastewaters, J. Taiwan. Inst. Chem. Eng., 43 (2012) 282–290.

[115] M.K. Mbacke, C. Kane, N.O. Diallo, C.M. Diop, F. Chauvet, M. Comtat, T. Tzedakis, Electrocoagulation process applied on pollutants treatment-experimental optimization and fundamental investigation of the crystal violet dye removal, J. Environ. Chem. Eng., 4 (2016) 4001–4011.

[116] X. Gao, W. Li, R. Mei, C. Zhu, B. Zhou, L. Ma, Q. Wei, Effect of the $B_2H_6/CH_4/H_2$ ratios on the structure and electrochemical properties of boron-doped diamond electrode in the electrochemical oxidation process of azo dye, J. Electroanal. Chem., 832 (2019) 247–253.

[117] D. Dogan, H. Turkdemir, Electrochemical oxidation of textile dye indigo, J. Chem. Technol. Biotechnol., 80 (2005) 916–923.

[118] A.M. Faouzi, B. Nasr, G. Abdellatif, Electrochemical degradation of anthraquinone dye Alizarin Red S by anodic oxidation on boron-doped diamond, Dyes Pigm., 73 (2007) 86–89.

[119] F.H. Oliveira, M.E. Osugi, F.M.M. Paschoal, D, Profeti, P. Olivi, M.V.B. Zanoni, Electrochemical oxidation of an acid dye by active chlorine generated using Ti/Sn(1-x)Ir O-x(2) electrodes, J. Appl. Electrochem., 37 (2007) 583–592.

[120] N. Remya, J.G. Lin, Current status of microwave application in wastewater treatment - a review, Chem. Eng. J., 166 (2011) 797–813.

[121] L. Bilinska, M. Gmurek, S. Ledakowicz, Comparison between industrial and simulated textile wastewater treatment by AOPs - biodegradability, toxicity and cost assessment, Chem. Eng. J., 306 (2016) 550–559.

[122] Y. Liu, X. He, X. Duan, Y. Fu, D. Fatta-Kassinos, D.D. Dionysiou, Significant role of UV and carbonate radical on the degradation of oxytetracycline in UV-AOPs: kinetics and mechanism, Water Res., 95 (2016) 195–204.

[123] P. Klan, M. Vavrik, Non-catalytic remediation of aqueous solutions by microwave-assisted photolysis in the presence of H_2O_2, J. Photochem. Photobiol. A, 177 (2006) 24–33.

[124] S. Hisaindee, M.A. Meetani, M.A. Rauf, Application of LC-MS to the analysis of advanced oxidation process (AOP) degradation of dye products and reaction mechanisms, Trends Anal. Chem., 49 (2013) 31–44.

[125] M. Cheng, G. Zeng, D. Huang, C. Lai, P. Xu, C. Zhang, Y. Liu, Hydroxyl radicals based advanced oxidation processes (AOPs) for remediation of soils contaminated with organic compounds: a review, Chem. Eng. J., 284 (2016) 582–598.

[126] F. Lelario, M. Brienza, S.A. Bufo, L. Scrano, Effectiveness of different advanced oxidation processes (AOPs) on the abatement of the model compound mepanipyrim in water, J. Photochem. Photobiol. A, 321 (2016) 187–201.

[127] P.V. Nidheesh, M. Zhou, M.A. Oturan, Chemosphere An overview on the removal of synthetic dyes from water by electrochemical advanced oxidation processes, Chemosphere, 197 (2018) 210–227.

[128] M. Izadifard, G. Achari, C.H. Langford, Degradation of sulfolane using activated persulfate with UV and UV-Ozone, Water Res., 125 (2017) 325–331.

[129] G. Subramanian, G. Madras, Introducing saccharic acid as an efficient iron chelate to enhance photo-Fenton degradation of organic contaminants, Water Res., 104 (2016) 168–177.

[130] M. Muruganandham, M. Swaminathan, Decolourisation of Reactive Orange 4 by Fenton and Photo-Fenton Oxidation Technology, Dyes Pigm., 63 (2004) 315–321.

[131] V.M. Bandala, L. Montoya, M. Mata, New species and records of Crepidotus from costa rica and mexico, Fungal Divers., 32 (2008) 9–29.

[132] J. Macias-Sanchez, L. Hinojosa-Reyes, J.L. Guzman-Mar, J.M. Peralta-Hernandez, A. Hernandez-Ramírez, Performance of the photo-Fenton process in the degradation of a model azo dye mixture, Photochem. Photobiol. Sci., 10 (2011) 332–337.

[133] Y.J. Shih, C.H. Ho, Y.H. Huang, Photo-Fenton oxidation of azo dye Reactive Black B using an immobilized iron oxide as heterogeneous catalyst, Water Environ. Res., 85 (2013) 340–345.

[134] L.A. de Luna, T.H. da Silva, R.F. Nogueira, F. Kummrow, G.A. Umbuzeiro, Aquatic toxicity of dyes before and after photo-Fenton treatment, J. Hazard. Mater., 276 (2014) 332–338.

[135] A.G. Trovo, A.K. Hassan, M. Sillanpaa, W.Z. Tang, Degradation of Acid Blue 161 by Fenton and photo-Fenton processes, Int. J. Environ. Sci. Technol., 13 (2016) 147–158.

[136] I. Arslan-Alaton, A review of the effects of dye-assisting chemicals on advanced oxidation of reactive dyes in wastewater, Coloration, 119 (2003) 345–353.

[137] A. Akyol, H.C. Yatmaz, M. Bayramoglu, Photocatalytic decolorization of Remazol Red RR in aqueous ZnO suspensions, Appl. Catal. B, 54 (2004) 19–24.

[138] A. Aguedach, S. Brosillon, J. Morvan, E.K. Lhadi, Photocatalytic degradation of azo-dyes reactive black 5 and reactive yellow 145 in water over a newly deposited titanium dioxide, Appl. Catal. B, 57 (138) 55–62.

[139] M.A. Behnajady, N. Modirshahla, R. Hamzavi, Kinetic study on photocatalytic degradation of C.I. Acid Yellow 23 by ZnO photocatalyst, J. Hazard. Mater., 133 (2006) 226–232.

[140] T.K. Ghorai, D. Dhak, S.K. Biswas, S. Dalai, P. Pramanik, Photocatalytic oxidation of organic dyes by nano-sized metal molybdate incorporated titanium dioxide ($M_xM_{ox}Ti_{1-x}O6$) (M=Ni, Cu, Zn) photocatalysts, J. Mol. Catal A: Chem., 273 (2007) 224–229.

[141] F. Han, V.S.R. Kambala, M. Srinivasan, D. Rajarathnam, R. Naidu, Tailored titanium dioxide photocatalysts for the degradation of organic dyes in wastewater treatment: a review, Appl. Catal. A, 359 (2009) 25–40.

[142] C.D. Raman, S. Kanmani, Textile dye degradation using nano zero valent iron: a review, J. Environ. Manage., 177 (2016) 341–355.

[143] K. Vinodgopal, J. Peller, Hydroxyl radical-mediated advanced oxidation processes for textile dyes: a comparison of the radiolytic and sonolytic degradation of the monoazo dye Acid Orange 7, Res. Chem. Intermed., 29 (2003) 307–316.

[144] O. Martins Ad, V.M. Canalli, C.M.N. Azevedo, M. Pires, Degradation of pararosaniline (C.I. Basic Red 9 monohydrochloride) dye by ozonation and sonolysis, Dyes Pigm., 68 (2006) 227–234.

[145] G. Ameta, P. Vaishnav, R.K. Malkani, S.C. Ameta, Sonolytic, Photocatalytic and sonophotocatalytic degradation of toluidine blue, J. Indian Council Chem., 26 (2009) 100–105.

[146] R.R. Nair, R.L. Patel, Treatment of dye wastewater by sonolysis process, Int. J. Res. Modern Eng. Emerg. Technol., 2 (2014) 1–6.

[147] S. Chakma, L. Das, V.S. Moholkar, Dye decolorization with hybrid advanced oxidation processes comprising sonolysis/Fenton-like/photo-ferrioxalate systems: a mechanistic investigation, Sep. Purif. Technol., 156 (2015) 596–607.

[148] C.I. Pearce, J. Lloyd, J.T. Guthrie, The removal of colour from textile wastewater using whole bacterial cells: a review, Dyes Pigm., 58 (2003) 179–196.

[149] S. Jeevanantham, A. Saravanan, R.V. Hemavathy, P.S. Kumar, P.R. Yaashikaa, D. Yuvaraj, Removal of toxic pollutants from water environment by phytoremediation: a survey on application and future prospects, Environ. Technol. Innovat., 13 (2019) 264–276.

[150] B.E. Barragan, C. Costa, M. Carmen Marquez, Biodegradation of azo dyes by bacteria inoculated on solid media, Dyes Pigm., 75 (2007) 73–81.

[151] E. Kalmis, N. Azbar, F. Kalyoncu, Evaluation of two wild types of *Pleurotus ostreatus* (MCC07 and MCC20) isolated from nature for their ability to decolorize Benazol Black ZN textile dye in comparison to some commercial types of white rot fungi: *Pleurotus ostreatus*, *Pleurotus djamor*, and *Pleurotus citrinopileatus*, Can. J. Microbiol., 54 (2008) 366–370.

[152] P. Kaushik, A. Malik, Fungal dye decolorization: recent advances and future potential, Environ. Int., 35 (2009) 127–141.

[153] Y. Qu, S. Shi, F. Ma, B. Yan, Decolorization of reactive dark blue K-R by the synergism of fungus and bacterium using response surface methodology, Bioresour. Technol., 101 (2010) 8016–8023.

[154] N. Gomi, S. Yoshida, K. Matsumoto, M. Okudomi, H. Konno, T. Hisabori, Y. Sugano, Degradation of the synthetic dye amaranth by the fungus *Bjerkandera adusta* Dec 1: inference of the degradation pathway from an analysis of decolorized products, Biodegradation, 22 (2011) 1239–1245.

[155] Y. Qu, X. Cao, Q. Ma, S. Shi, L. Tan, X. Li, H. Zhou, X. Zhang, J. Zhou, Aerobic decolorization and degradation of Acid Red B by a newly isolated *Pichia* sp. TCL, J. Hazard. Mater., 223–224 (2012) 31–38.

[156] C. Miranda Rde, B. Gomes Ede, N. Pereira Jr., M.A. Marin-Morales, K.M. Machado, N.B. Gusmao, Biotreatment of textile effluent in static bioreactor by *Curvularia lunata* URM 6179 and *Phanerochaete chrysosporium* URM 6181, Bioresour. Technol., 142 (2013) 361–367.

[157] L. Tan, S. Ning, X. Zhang, S. Shi, Aerobic decolorization and degradation of azo dyes by growing cells of a newly isolated yeast *Candida tropicalis* TL-F1, Bioresour. Technol., 138 (2013) 307–313.

[158] S.K. Sen, S. Raut, P. Bandyopadhyay, S. Raut, Fungal decolouration and degradation of azo dyes: a review, Fungal Biol. Rev., 30 (2016) 112–133.

[159] H.S. Rai, M.S. Bhattacharyya, J. Singh, T.K. Bansal, P. Vats, U.C. Banerjee, Removal of dyes from the effluent of textile and dyestuff manufacturing industry: a review of emerging techniques with reference to biological treatment, Crit. Rev. Environ. Sci. Technol., 35 (2005) 219–238.

[160] R. Sani, U. Banerjee, Decolorization of triphenylmethane dyes and textile and dye-stuff effluent by *Kurthia* sp., Enzyme Microbial. Technol., 24 (1999) 433–437.

[161] H.G. Kulla, Aerobic bacterial degradation of azo dyes, FEMS Microbiol. Lett., 12 (1981) 387–399.

[162] J.A. Bumpus, B.J. Brock, Biodegradation of crystal violet by the white rot fungus *Phanerochaete chrysosporium*, Appl. Environ. Microbiol., 54 (1988) 1143–1150.

[163] K. Vasdev, R.C. Kuhad, R.K. Saxena, Decolorization of triphenylmethane dyes by a bird's nest fungus *Cyathus bulleri*, Current Microbiol., 30 (1995) 269–272.

[164] Y. Fu, T. Viraraghavan, Fungal decolorization of dye wastewaters: a review, Bioresour. Technol., 79 (2001) 251–262.

[165] N.K. Pazarlioglu, R.O. Urek, F. Ergun, Biodecolourization of Direct Blue 15 by immobilized *Phanerochaete chrysosporium*, Process Biochem., 40 (2005) 1923–1929.

[166] F.M. Zhang, J.S. Knapp, K.N. Tapley, Decolourisation of cotton bleaching effluent with wood rotting fungus, Water Res., 33 (1999) 919–928.

[167] P. Nigam, G. Armour, I.M. Banat, D. Singh, R. Marchant, Physical removal of textile dyes from effluents and solid-state fermentation of dye-adsorbed agricultural residues, Bioresour. Technol., 72 (2000) 219–226.

[168] Salony, S. Mishra, V.S. Bisaria, Production and characterization of laccase from *Cyathus bulleri* and its use in decolourization of recalcitrant textile dyes, Appl. Microbiol. Biotechnol., 71 (2006) 646–653.

[169] U. Pagga, D. Brown, The degradation of dyestuffs: Part II. Behaviour of dyestuffs in aerobic biodegradation tests, Chemosphere, 15 (1986) 479–491.

[170] E. Razo-Flores, M. Luijten, B. Donlon, G. Lettinga, J. Field, Biodegradation of selected azo dyes under methanogenic conditions, Water Sci. Technol., 36 (1997) 65–72.

[171] W. Delee, C. O'Neill, F.R. Hawkes, H.M. Pinheiro, Anaerobic treatment of textile effluents: a review, J. Chem. Technol. Biotechnol., 73 (1998) 323–335.

[172] F.P. Zee van der, G. Lettinga, J.A. Field, Azo dye decolourisation by anaerobic sludge, Chemosphere, 44 (2001) 1169–1176.

[173] M. Jayapal, H. Jagadeesan, M. Shanmugam, J.P. Danisha, S. Murugesan, Sequential anaerobic-aerobic treatment using plant microbe integrated system for degradation of azo dyes and their aromatic amines by-products, J. Hazard. Mater., 354 (2018) 231–243.

[174] A. Stolz, Basic and applied aspects in the microbial degradation of azo dyes, Appl. Microbiol. Biotechnol., 56 (2001) 69–80.

[175] D. Brown, P. Laboureur, The degradation of dyestuffs: part I. Primary biodegradation under anaerobic conditions, Chemosphere, 12 (1983) 397–404.

[176] D. Brown, B. Hamburger, The degradation of dye stuffs. Part III. Investigations of their ultimate degradability, Chemosphere, 16 (1987) 1539–1553.

[177] T. Robinson, G. McMullan, R. Marchant, P. Nigam, Remediation of dyes in textile effluent: a critical review on current treatment technologies with a proposed alternative, Bioresour. Technol., 77 (2001) 247–255.

[178] K.G. Bhattacharyya, A. Sarma, Adsorption characteristics of the dye, Brilliant Green, on Neem leaf powder, Dyes Pigm., 57 (2003) 211–222.

[179] G. Crini, Non-conventional low-cost adsorbents for dye removal: a review, Bioresour. Technol., 97 (2006) 1061–1085.

[180] M.D. LeVan, G. Carta, C.M. Yon, In: R.H. Perry, D.W. Green, J.O. Maloney, Eds., Adsorption and Ion Exchange, 7th ed. Perry's Chemical Engineers, Handbook McGraw-Hill, New York, 1997.

[181] D.A. Clifford, Ion Exchange and Inorganic Adsorption, In: R.D. Letterman, Ed., Water Quality and Treatment, 5th ed., McGraw-Hill, New York, 1999.

[182] G.P. Handreck, T.D. Smith, Adsorption of methylene blue from aqueous solution by ZSM-5-type zeolites and related silica polymorphs, J. Chem. Soc., 84 (1988) 4191–4201.

[183] S. Karcher, A. Kornmuller, M. Jekel, Screening of commercial sorbents for the removal of reactive dyes, Dyes Pigm., 51 (2001) 111–125.

[184] V. Meshko, L. Markovska, M. Mincheva, A.E. Rodrigues, Adsorption of basic dyes on granular acivated carbon and natural zeolite, Water Res., 35 (2001) 3357–3366.

[185] Y. Yu, Y.Y. Zhuang, Z.H. Wang, M.Q. Qiu, Adsorption of water-soluble dyes onto modified resin, Chemosphere, 54 (2004) 425–430.

[186] B. Armagan, O. Ozdemir, M. Turan, M.S. Celik, The removal of reactive azo dyes by natural and modified zeolites, J. Chem. Technol. Biotechnol., 78 (2003) 725–732.

[187] O. Ozdemir, B. Armagan, M. Turan, M.S. Celik, Comparison of the adsorption characteristics of azo-reactive dyes on mezoporous minerals, Dyes Pigm., 62 (2004) 49–60.

[188] X. Yuan, S.P. Zhuo, W. Xing, H.Y. Cui, X.D. Dai, X.M. Liu, Z.F. Yan, Aqueous dye adsorption on ordered mesoporous carbons, J. Colloid Interface Sci., 310 (2007) 83–89.

[189] H. Nur, A.F.N.A. Manan, L.K. Wei, M.N.M. Muhid, H. Hamdan, Simultaneous adsorption of a mixture of paraquat and dye by NaY zeolite covered with alkylsilane, J. Hazard. Mater., 117 (2005) 5–40.

[190] J. Fan, A. Li, W. Yang, L. Yang, Q. Zhang, Adsorption of water-soluble dye XBR onto styrene and acrylic ester resins, Sep. Purif. Technol., 51 (2006) 338–344.

[191] X. Zhang, A. Li, Z. Jiang, Q. Zhang, Adsorption of dyes and phenol from water on resin adsorbents: effect of adsorbate size and pore size distribution, J. Hazard. Mater., 137 (2006) 1115–1122.

[192] C.-H. Liu, J.-S. Wu, H.-C. Chiu, S.-Y. Suen, K.H. Chu, Removal of anionic reactive dyes from water using anion exchange membranes as adsorbers, Water Res., 41 (2007) 1491–1500.

[193] S. Raghu, C. Ahmed Basha, Chemical or electrochemical techniques, followed by ion exchange, for recycle of textile dye wastewater, J. Hazard. Mater., 149 (2007) 324–330.

[194] S. Wang, E. Ariyanto, Competitive adsorption of malachite green and Pb ions on natural zeolite, J. Colloid Interface Sci., 314 (2007) 25–31.

[195] P.S. Kumar, K. Ramakrishnan, R. Gayathri, Removal of nickel (II) from aqueous solutions by ceralite IR 120 cationic exchange resins, J. Eng. Sci. Technol., 5 (2010) 232–243.

[196] S.K. Alpat, O. Ozbayrak, S. Alpat, H. Akcay, The adsorption kinetics and removal of cationic dye, Toluidine Blue O, from aqueous solution with Turkish zeolite, J. Hazard. Mater., 151 (2008) 213–220.

[197] S.D. Alexandratos, Ion-exchange resins: a retrospective from industrial and engineering chemistry research, Ind. Eng. Chem. Res., 48 (2009) 388–398.

[198] O.B. Akpor, M. Muchie, Remediation of heavy metals in drinking water and wastewater treatment systems: processes and applications, Int. J. Phys. Sci., 5 (2010) 1807–1817.

[199] M. Wawrzkiewicz, Removal of C.I. Basic Blue 3 dye by sorption onto cation exchange resin, functionalized and non-functionalized polymeric sorbents from aqueous solutions and wastewaters, Chem. Eng. J., 217 (2013) 414–425.

[200] C.L. Mantell, Adsorption, McGraw-Hill Book Company, New York, 1951.

[201] K.G. Pavithra, P.S. Kumar, V. Jaikumar, Removal of colorants from wastewater: a review on sources and treatment strategies, J. Ind. Eng. Chem., 75 (2019) 1–19.

[202] J.S. Mattson, H.B.J. Mark, Activated Carbon Surface Chemistry and Adsorption from Solution, Marcel Dekker, New York, 1971.

[203] A.I. Liapis, Fundamentals of Adsorption, Engineering Foundation, New York, 1987.

[204] H.M. Freeman, Standard Handbook of Hazardous Waste Treatment and Disposal, McGraw-Hill, New York, 1989.

[205] M. Pirbazari, B.N. Badriyha, R.J. Miltner, GAC adsorber design for removal of chlorinated pesticide, J. Environ. Eng., 117 (1991) 80–100.

[206] F. Quignon, F. Thomas, C. Gantzer, A. Huyard, L. Schwartzbrod, Virus adsorption in a complex system: an experimentally designed study, Water Res., 32 (1998) 1222–1230.

[207] K. Imamura, E. Ikeda, T. Nagayasu, T. Sakiyama, K. Nakanishi, Adsorption behavior of methylene blue and its congeners on a stainless steel surface, J. Colloid Interface Sci., 245 (2002) 50–57.

[208] R.C. Bansal, M. Goyal, Activated Carbon Adsorption, Taylor & Francis Group, Boca Raton, 2005.

[209] L.-C. Juang, C.-C. Wang, C.-K. Lee, Adsorption of basic dyes onto MCM-41, Chemosphere, 64 (2006) 1920–1928.

[210] Y. Onal, Kinetics of adsorption of dyes from aqueous solution using activated carbon prepared from waste apricot, J. Hazard. Mater., 137 (2006) 1719–1728.

[211] M.J. Iqbal, M.N. Ashiq, Adsorption of dyes from aqueous solutions on activated charcoal, J. Hazard. Mater., 139 (2007) 57–66.

[212] G. Wang, W. Li, H. Chen, B. Li, The direct liquefaction of sawdust in tetralin, Energy Sources Part A, 29 (2007) 1221–1231.

[213] M. Turabik, Adsorption of basic dyes from single and binary component systems onto bentonite: simultaneous analysis of Basic Red 46 and Basic Yellow 28 by first order derivative spectrophotometric analysis method, J. Hazard. Mater., 158 (2008) 52–64.

[214] W. Yang, D. Wu, R. Fu, Effect of surface chemistry on the adsorption of basic dyes on carbon aerogels, Colloids Surf. A, 312 (2008) 118–124.

[215] G. Bayramoglu, B. Altintas, M.Y. Arica, Adsorption kinetics and thermodynamic parameters of cationic dyes from aqueous solutions by using a new strong cation-exchange resin, Chem. Eng. J., 152 (2009) 339–346.

[216] S.D. Khattri, M.K. Singh, Removal of malachite green from dye wastewater using neem sawdust by adsorption, J. Hazard. Mater., 167 (2009) 1089–1094.

[217] A.A. Ahmad, B.H. Hameed, Fixed-bed adsorption of reactive azo dye onto granular activated carbon prepared from waste, J. Hazard. Mater., 175 (2010) 298–303.

[218] K. Nuithitikul, S. Srikhun, S. Hirunpraditkoon, Kinetics and equilibrium adsorption of Basic Green 4 dye on activated carbon derived from durian peel: effects of pyrolysis and post-treatment conditions, J. Taiwan. Inst. Chem. Eng., 41 (2010) 591–598.

[219] Y. Kismir, A.Z. Aroguz, Adsorption characteristics of the hazardous dye Brilliant Green on Saklıkent mud, Chem. Eng. J., 172 (2011) 199–206.

[220] G. Moussavi, R. Khosravi, The removal of cationic dyes from aqueous solutions by adsorption onto pistachio hull waste, Chem. Eng. Res. Des., 89 (2011) 2182–2189.

[221] I.M. Ahmed, M.S. Gasser, Adsorption study of anionic reactive dye from aqueous solution to Mg–Fe–CO_3 layered double hydroxide (LDH), Appl. Surf. Sci., 259 (2012) 650–656.

[222] M. Paul, N. Pal, A. Bhaumik, Selective adsorption and release of cationic organic dye molecules on mesoporous borosilicates, Mater. Sci. Eng. C, 32 (2012) 1461–1468.

[223] L. Chen, B. Bai, Equilibrium kinetic, thermodynamic, and in situ regeneration studies about methylene blue adsorption by the raspberry-like TiO_2@yeast microspheres, Ind. Eng. Chem. Res., 52 (2013) 15568–15577.

[224] A.S. Elsherbiny, Adsorption kinetics and mechanism of acid dye onto montmorillonite from aqueous solutions: stopped-flow measurements, Appl. Clay. Sci., 83–84 (2013) 56–62.

[225] M. Wang, L. Wang, Synthesis and characterization of carboxymethyl cellulose/organic montmorillonite nanocomposites and its adsorption behavior for congo red dye, Water Sci. Eng., 6 (2013) 272–282.

[226] R. Shukla, G. Madras, Facile synthesis of aluminium cobalt oxide for dye adsorption, J. Environ. Chem. Eng., 2 (2014) 2259–2268.

[227] B. Yahyaei, S. Azizian, Rapid adsorption of binary dye pollutants onto the nanostructured mesoporous alumina, J. Mol. Liq., 199 (2014) 88–95.

[228] R. Hazzaa, M. Hussein, Adsorption of cationic dye from aqueous solution onto activated carbon prepared from olive stones, Environ. Technol. Innovation, 4 (2015) 36–51.

[229] R. Sivashankar, A.B. Sathya, U. Krishnakumar, V. Sivasubramanian, Synthesis of magnetic biocomposite for efficient adsorption of azo dye from aqueous solution, Ecotoxicol. Environ. Saf., 121 (2015) 149–153.

[230] S.O. Akpotu, B. Moodley, Synthesis and characterization of citric acid grafted MCM-41 and its adsorption of cationic dyes, J. Environ. Eng., 4 (2016) 4503–4513.

[231] F. Zhang, B. Ma, X. Jiang, Y. Ji, Dual function magnetic hydroxyapatite nanopowder for removal of malachite green and Congo red from aqueous solution, Powder Technol., 302 (2016) 207–214.

[232] Z. Liang, Z. Zhao, T. Sun, W. Shi, F. Cui, Enhanced adsorption of the cationic dyes in the spherical CuO/meso-silica nano composite and impact of solution chemistry, J. Colloid Interface Sci., 485 (2017) 192–200.

[233] Y. Qi, M. Yang, W. Xu, S. He, Y. Men, Natural polysaccharides-modified graphene oxide for adsorption of organic dyes from aqueous solutions, J. Colloid Interface Sci., 486 (2017) 84–96.

[234] R. Rakhshaee, Y. Noorani, Comparing three methods of simultaneous synthesis and stabilization of Fe_3O_4 nanoparticles: changing physicochemical properties of products to improve kinetic and thermodynamic of dye adsorption, J. Magn. Magn. Mater., 422 (2017) 128–140.

[235] C. Pelekani, V.L. Snoeyink, Competitive adsorption between atrazine and Methylene Blue on activated carbon: the importance of pore size distribution, Carbon, 38 (2000) 1423–1436.

[236] C. Tien, Adsorption Calculations and Modeling, Butterworth-Heinemann, Boston, 1994.

[237] T. Van der Plas, The Texture and the Surface Chemistry of Carbons, in: B.G. Linsen, Ed., Physical and Chemical Aspects of Adsorbens and Catalysts, Academic Press, London, 1970.

[238] M.O. Corapcioglu, C.P. Huang, The surface acidity and characterization of some commercial activated carbons, Carbon, 25 (1987) 569–578.

[239] I.N. Najm, V.L. Snoeyink, B.W.J. Lykins, J.Q. Adams, Using powdered activated carbon: a critical review, Am. Water Works Assoc., 83 (1991) 65–76.

[240] F.A. Di Giano, A.S. Natter, Disperse dye-carrier interactions on activated carbon, J. Water Pollut. Control. Fed., 49 (1977) 235–244.

[241] G.M. Walker, L.R. Weatherley, Kinetics of acid dye adsorption on GAC, Water Res., 33 (1999) 1895–1899.

[242] S. Suganya, P.S. Kumar, Influence of ultrasonic waves on preparation of active carbon from coffee waste for the reclamation of effluents containing Cr(VI) ions, J. Ind. Eng. Chem., 60 (2018) 418–430.

[243] Y. Al-Degs, M.A.M. Khraisheh, S.J. Allen, M.N.A. Ahmad, Sorption behaviour of cationic and anionic dyes from aqueous solution on different types of activated carbons, Sep. Sci. Technol., 36 (2001) 91–102.

[244] P.J.M. Carrott, M.M.L. Ribeiro Carrott, J.M.V. Nabais, J.P.P. Ramalho, Influence of surface ionization on the adsorption of aqueous zinc species by activated carbons, Carbon, 35 (1997) 403–410.

[245] P.J.M. Carrott, M.M.L. Ribeiro Carrott, J.M.V. Nabais, Influence of surface ionization on the adsorption of aqueous mercury chlorocomplexes by activated carbons, Carbon, 36 (1998) 11–17.

[246] C. Gabaldon, P. Marzal, A. Seco, J.A. Gonzalez, Cadmium and copper removal by a granular activated carbon in laboratory column systems, Sep. Sci. Technol., 35 (2000) 1039–1053.

[247] R.W. Kuennen, R.M. Taylor, K. Van Dyke, K. Groenevelt, Removing lead from drinking water with a point-of-use GAC fixed-bed adsorber, J. Am. Water Works Assoc., 84 (1992) 91–101.

[248] A. Macias-Garcia, C. Valenzuela-Calahorro, V. Gomez-Serrano, A. Espinosa-Mansilla, Adsorption of Pb^{2+} by heat-treated acid sulfurized activated carbon, Carbon, 31 (1993) 1249–1255.

[249] J.S. Zogorski, S.D. Faust, J.H. Haas, The kinetics of adsorption of phenols by granular activated carbon, J. Colloid Interface Sci., 55 (1976) 329–341.

[250] F. Caturla, J.M. Martin-Martinez, M. Molina-Sabio, F. Rodriguez-Reinoso, R. Torregrosa, Adsorption of substituted phenols on activated carbon, J. Colloid Interface Sci., 124 (1988) 528–534.

[251] J.T. Paprowicz, Activated carbons for phenols removal from wastewaters, Environ. Technol., 11 (1990) 71–82.
[252] P.J.M. Carrott, P.A.M. Mourao, M.M.L. Ribeiro Carrott, E.M. Goncalves, Separating surface and solvent effects and the notion of critical adsorption energy in the adsorption of phenolic compounds by activated carbons, Langmuir, 21 (2005) 11863–11869.
[253] P.A.M. Mourao, P.J.M. Carrott, M.M.L. Ribeiro Carrott, Application of different equations to adsorption isotherms of phenolic compounds on activated carbons prepared from cork, Carbon, 44 (2006) 2422–2429.
[254] M. Pirbazari, W.J. Weber Jr., Removal of Dieldrin from water by activated carbon, J. Environ. Eng., 110 (1984) 656–669.
[255] J. Hu, T. Aizawa, Y. Ookubo, T. Morita, Y. Magara, Adsorptive characteristics of ionogenic aromatic pesticides in water on powdered activated carbon, Water Res., 32 (1988) 2593–2600.
[256] K. Urano, E. Yamamoto, M. Tonegawa, K. Fujie, Adsorption of chlorinated organic compounds on activated carbon from water, Water Res., 25 (1991) 1459–1464.
[257] M.C. Lee, J.C. Crittenden, V.L. Snoeyink, M. Ari, Design of carbon beds to remove humic substances, J. Environ. Eng., 109 (1983) 631–645.
[258] M. Pirbazari, B.N. Badriyha, S.H. Kim, R.J. Miltner, Evaluating GAC adsorbers for the removal of PCBs and Toxaphene, J. Am. Water Works Assoc., 84 (1992) 83–90.
[259] M. Bele, A. Kodre, I. Arcon, J. Grdadolnik, S. Pejovnik, J.O. Besenhard, Adsorption of cetyltrimethylammonium bromide on carbon black from aqueous solution, Carbon, 36 (1998) 1207–1212.
[260] A.N. Malhas, R.A. Abuknesha, R.G. Price, Removal of detergents from protein extracts using activated charcoal prior to immunological analysis, J. Immunol. Methods, 264 (2002) 37–43.
[261] M.E. Flentje, D.G. Hager, Reevaluation of granular-carbon filters for taste and odor control, J. Am. Water Works Assoc., 56 (1964) 191.
[262] S. Lalezary, M. Pirbazari, M.J. McGuire, Evaluating activated carbons for removing low concentrations of taste-and odor-producing organics, J. Am. Water Works Assoc., 78 (1986) 76–82.
[263] D.M. Giusti, R.A. Conway, C.T. Lawson, Activated carbon adsorption of petrochemicals, J. Water Pollut. Control. Fed., 46 (1974) 947–965.
[264] I. Saito, The removal of Hexacyanoferrate(II) and (III) ions in dilute aqueous solution by activated carbon, Water Res., 18 (1984) 319–323.
[265] G. McKay, M.J. Bino, A.R. Altameni, The adsorption of various pollutants from aqueous solutions on to activated carbon, Water Res., 19 (1985) 491–495.
[266] M.C. Annesini, F. Gironi, M. Ruzzi, C. Tomei, Adsorption of organic compounds onto activated carbon, Water Res., 21 (1987) 567–571.
[267] E.H. Smith, Evaluation of multicomponent adsorption equilibria for organic mixtures onto activated carbon, Water Res., 25 (1991) 125–134.
[268] P.S. Kumar, S. Ramalingam, K. Sathishkumar, Removal of methylene blue dye from aqueous solution by activated carbon prepared from cashew nut shell as a new low-cost adsorbent, Korean J. Chem. Eng., 28 (2011) 149–155.
[269] C. Donati, M. Drikas, R. Hayes, G. Newcombe, Microcystin-LR adsorption by powdered activated carbon, Water Res., 28 (1994) 1735–1742.
[270] P.J.M. Carrott, M.M.L. Ribeiro Carrott, I.P.P. Cansado, J.M.V. Nabais, Reference data for the adsorption of benzene on carbon materials, Carbon, 38 (2007) 465–474.
[271] L. Hemphill, V. Ramaiah, M. Valentine, Thermal Regeneration of Activated Carbon, 32nd Purdue Industrial Waste Conference, Purdue University, 1997, pp. 116–126.
[272] M.A. Rollar, M.T. Suidan, W.H. Goss, S.A. Vargo, Regeneration of five activated carbon with methanol, J. Environ. Eng., 108 (1982) 1361.
[273] R.J. Martin, W.J. Ng, The repeated exhaustion and regeneration of activated carbon, Water Res., 21 (1987) 961–965.
[274] G. Newcombe, M. Drikas, Chemical regeneration of granular activated carbon from an operating water treatment plant, Water Res., 27 (1993) 161–165.
[275] S. Notthakum, J.C. Crittenden, D.W. Hand, D.L. Perram, M.E. Mullins, Regeneration of adsorbents using heterogeneous advanced oxidation, J. Environ. Eng., 119 (1993) 695.
[276] R.M. Narbaitz, J. Cen, Electrochemical regeneration of granular activated carbon, Water Res., 28 (1994) 1771–1778.
[277] E.J. Kilduff, C.J. King, Effect of carbon adsorbent surface properties on the uptake and solvent regeneration of phenol, Ind. Eng. Chem. Res., 36 (1997) 1603–1613.
[278] E.A. Taiwo, A. Adesina, Electrochemical regeneration of a native activated carbon, Chem. Biochem. Eng. Q., 19 (2005) 269–273.
[279] M.H. Zhou, L.C. Lei, Electrochemical regeneration of activated carbon loaded with p-nitrophenol in a fluidized electrochemical reactor, Electrochim. Acta, 51 (2005) 4489–4496.
[280] M.A.M. Salleh, D.K. Mahmoud, W.A.W.A. Karim, A. Idris, Cationic and anionic dye adsorption by agricultural solid wastes: a comprehensive review, Desalination, 280 (2011) 1–13.
[281] Y. Zhou, L. Zhang, Z. Cheng, Removal of organic pollutants from aqueous solution using agricultural wastes: a review, J. Mol. Liq., 212 (2015) 739–762.
[282] S. Chowdhury, R. Mishra, P. Saha, P. Kushwaha, Adsorption thermodynamics, kinetics and isosteric heat of adsorption of malachite green onto chemically modified rice husk, Desalination, 265 (2011) 159–168.
[283] J.M. Dias, M.C.M. Alvim-Ferraz, M.F. Almeida, J. Rivera-Utrilla, M. Sanchez-Polo, Waste materials for activated carbon preparation and its use in aqueous-phase treatment: a review, J. Environ. Manage., 85 (2007) 833–846.
[284] O. Ioannidou, A. Zabaniotou, Agricultural residues as precursors for activated carbon production – a review, Renew. Sust. Energy Rev., 11 (2007) 1996–2005.
[285] F.E. Okieimen, C.O. Okiemen, R.A. Wuana, Preparation and characterization of activated carbon from rice husks, J. Chem. Soc., 32 (2007) 126–136.
[286] D. Savova, E. Apak, E. Ekinci, F. Yardim, N. Petrova, T. Budinova, M. Razvigorova, V. Minkova, Biomass conversion to carbon adsorbents and gas, Biomass Bioenergy, 21 (2001) 133–142.
[287] K.A. Adegoke, O.S. Bello, Dye sequestration using agricultural wastes as adsorbents, Water Resour. Ind., 12 (2015) 8–24.
[288] P.J.M. Carrott, M.M.L. Ribeiro Carrott, P.A.M. Mourao, R.P. Lima, Preparation of activated carbons from cork by physical activation in carbon dioxide, Adsorpt. Sci., 21 (2003) 669–681.
[289] R. Sanghi, B. Bhattacharya, Review on decolorisation of aqueous dye solutions by low cost adsorbents, Coloration Technol., 118 (2003) 256–269.
[290] N.H. Phan, S. Rio, C. Faur, L. Le Coq, P. Le Cloirec, T.H. Nguyen, Production of fibrous activated carbons from natural cellulose (jute, coconut) fibers for water treatment applications, Carbon, 44 (2006) 2569–2577.
[291] M.A. Lillo-Rodenas, J.P. Marco-Lozar, D. Cazorla-Amoros, A. Linares-Solano, Activated carbons prepared by pyrolysis of mixtures of carbon precursor/alkaline hydroxide, J. Analyt. Appl. Pyrolysis, 80 (2007) 166–174.
[292] M.A. Ahmad, N.K. Rahman, Equilibrium, kinetics and thermodynamic of Re-mazol Brilliant Orange 3R dye adsorption on coffee husk-based activated carbon, Chem. Eng. J., 170 (2011) 154–161.
[293] K.Y. Foo, B.H. Hameed, Coconut husk derived activated carbon via microwave induced activation: effects of activation agents, preparation parameters and adsorption performance, Chem. Eng. J., 184 (2012) 57–65.
[294] U. Gecgel, H. Kolancilar, Adsorption of Remazol brilliant blue R on activated carbon prepared from a pine cone, Nat. Prod. Res., 26 (2012) 659–664.
[295] M. Lanzetta, C. Di Blasi, Pyrolysis kinetics of wheat and corn straw, J. Anal. Appl. Pyrolysis, 44 (1998) 181–192.

[296] M. Ahmedna, W.E. Marshall, R.M. Rao, Production of granular activated carbons from select agricultural byproducts and evaluation of their physical, chemical and adsorption properties, Bioresour. Technol., 71 (2000) 13–123.
[297] T. Hassanein, B. Koumanova, Evaluation of adsorption potential of the agricultural waste wheat straw for Basic Yellow 21, J. Chem. Technol. Metall., 45 (2010) 407–414.
[298] P.K. Malik, Use of activated carbons prepared from sawdust and rice-husk for adsorption of acid dyes: a case study of Acid Yellow 36, Dyes Pigm., 56 (2003) 239–249.
[299] P.K. Malik, Dye removal from wastewater using activated carbon developed from sawdust: adsorption equilibrium and kinetics, J. Hazard. Mater., 113 (2004) 81–88.
[300] B.G. Prakash Kumar, L.R. Miranda, M. Velan, Adsorption of Bismark Brown dye on activated carbons prepared from rubber wood sawdust (*Hevea brasiliensis*) using different activation methods, J. Hazard. Mater., 126 (2005) 63–70.
[301] R.S. Juang, F.C. Wu, R.L. Tseng, Characterization and use of activated carbons prepared from bagasses for liquid-phase adsorption, Colloids Surf. B, 201 (2002) 191–199.
[302] E. Altintig, G. Arabaci, H. Altundag, Preparation and characterization of the antibacterial efficiency of silver loaded activated carbon from corncobs, Surf. Coat. Technol., 304 (2016) 63–67.
[303] M. Valix, W.H. Cheung, G. McKay, Preparation of activated carbon using low temperature carbonisation and physical activation of high ash raw bagasse for acid dye adsorption, Chemosphere, 56 (2004) 493–501.
[304] A.E. Putun, N. Ozbay, E.P. Onal, E. Putun, Fixed-bed pyrolysis of cotton stalk for liquid and solid products, Fuel Process. Technol., 86 (2005) 1207–1219.
[305] I.A.W. Tan, A.L. Ahmad, B.H. Hameed, Adsorption of basic dye on high surface area activated carbon prepared from coconut husk: equilibrium, kinetic and thermodynamic studies, J. Hazard. Mater., 154 (2008) 337–346.
[306] Y.P. Guo, S.F. Yang, W.Y. Fu, J.R. Qi, R.Z. Li, Z.C. Wang, H.D. Xu, Adsorption of malachite green on micro- and mesoporous rice husk-based active carbon, Dyes Pigm., 56 (2003) 219–229.
[307] M.M. Mohamed, Acid dye removal: comparison of surfactant modified mesoporous FSM-16 with activated carbon derived from rice husk, J. Colloid Interface Sci., 272 (2004) 28–34.
[308] W. Li, J.H. Peng, L.B. Zhang, H.Y. Xia, N. Li, K.B. Yang, X.Y. Zhu, Investigations on carbonization processes of plain tobacco stems and H_3PO_4-impregnated tobacco stems used for the preparation of activated carbons with H_3PO_4 activation, Ind. Crops Prod., 28 (2008) 73–80.
[309] T. Yang, A.C. Lua, Characteristics of activated carbons prepared from pistachio-nut shells by physical activation, J. Colloid Interface Sci., 267 (2003) 408–417.
[310] M. Ahmedna, W.E. Marshall, A.A. Husseiny, R.M. Rao, I. Goktepe, The use of nutshell carbons in drinking water filters for removal of trace metals, Water Res., 38 (2004) 1062–1068.
[311] A. Kumar, H.M. Jena, Removal of methylene blue and phenol onto prepared activated carbon from Fox nutshell by chemical activation in batch and fixed-bed column, J. Cleaner Prod., 137 (2016) 1246–1259.
[312] T. Tay, S. Ucar, S. Karagoz, Preparation and characterization of activated carbon from waste biomass, J. Hazard. Mater., 165 (2009) 481–485.
[313] I.A.W. Tan, A.L. Ahmad, B.H. Hameed, Enhancement of basic dye adsorption uptake from aqueous solutions using chemically modified oil palm shell activated carbon, Colloids Surf. A, 318 (2008) 88–96.
[314] L.S. Tan, K. Jain, C.A. Rozaini, Adsorption of textile dye from aqueous solution on pretreated mangrove bark, an agricultural waste: equilibrium and kinetics studies, J. Appl. Sci. Environ. Sanit., 5 (2010) 283–294.
[315] A.-A. Pelaez-Cid, A.-M. Herrera-Gonzalez, M. Salazar-Villanueva, A. Bautista-Hernandez, Elimination of textile dyes using activated carbons prepared from vegetable residues and their characterization, J. Environ. Manage., 181 (2016) 269–278.
[316] T. Zhang, W.P. Walawender, L.T. Fan, M. Fan, D. Daugaard, R.C. Brown, Preparation of activated carbon from forest and agricultural residues through CO_2 activation, Chem. Eng. J., 105 (2004) 53–59.
[317] B. Royer, N.F. Cardoso, E.C. Lima, J.P. Vaghetti, N.M. Simon, T. Calvete, R.C. Veses, Applications of Brazilian pine-fruit shell in natural and carbonized forms as adsorbents to removal of methylene blue from aqueous solutions: kinetic and equilibrium study, J. Hazard. Mater., 164 (2009) 1213–1222.
[318] G.H. Oh, C.R. Park, Preparation and characteristics of rice-straw based porous carbons with high adsorption capacity, Fuel, 81 (2002) 327–336.
[319] V. Minkova, S.P. Marinov, R. Zanzi, E. Bjornbom, T. Budinova, M. Stefanova, L. Lakov, Thermochemical treatment of biomass in a flow of steam or in a mixture of steam and carbon dioxide, Fuel Process. Technol., 62 (2000) 45–52.
[320] A. Abdel-Nasser, El-Hendawy, S.E. Samra, B.S. Girgis, Adsorption characteristics of activated carbons obtained from corncobs, Colloids Surf. A, 180 (2001) 209–221.
[321] V. Minkova, M. Razvigorova, E. Bjornbom, R. Zanzi, T. Budinova, N. Petrov, Effect of water vapour and biomass nature on the yield and quality of the pyrolysis products from biomass, Fuel Process. Technol., 70 (2001) 53–61.
[322] B.S. Girgis, S.S. Yunis, A.M. Soliman, Characteristics of activated carbon from peanut hulls in relation to conditions of preparation, Mater. Lett., 57 (2002) 164–172.
[323] M. Fan, W. Marshall, D. Daugaard, R.C. Brown, Steam activation of chars produced from oat hulls and corn stover, Bioresour. Technol., 93 (2004) 103–107.
[324] Y.S. Al-Degs, M.I. El-Barghouthi, A.H. El-Sheikh, G.M. Walker, Effect of solution pH, ionic strength, and temperature on adsorption behavior of reactive dyes on activated carbon, Dyes Pigm., 77 (2008) 16–23.
[325] E.N. El Qada, S.J. Allen, G.M. Walker, Adsorption of basic dyes from aqueous solution onto activated carbons, Chem. Eng. J., 135 (2008) 174–184.
[326] M. Abassi, N.R. Asl, Removal of hazardous reactive blue 19 dye from aqueous solution by agricultural waste, J. Iran. Chem. Res., 2 (2009) 221–230.
[327] P.S. Kumar, S.J. Varjani, S. Suganya, Treatment of dye wastewater using an ultrasonic aided nanoparticle stacked activated carbon: kinetic and isotherm modelling, Bioresour. Technol., 250 (2018) 716–722.
[328] S.T. Ong, P.S. Keng, S.L. Lee, M.H. Leong, Y.T. Hung, Equilibrium studies for the removal of basic dye by sunflower seed husk (*Helianthus annus*), Int. J. Phys. Sci., 5 (2010) 1270–1276.
[329] T. Parvathi, T. Maruthvanan, S. Sivamani, C. Prakash, C.V. Koushik, Role of tapioca peel activated carbon (TPAC) in decolourisation of Red Brown C4R reactive dye, Indian J. Sci. Technol., 3 (2010) 290–292.
[330] C. Senthamarai, P.S. Kumar, M. Priyadharshini, P. Vijayalakshmi, V.V. Kumar, P. Baskaralingam, K.V. Thiruvengadaravi, S. Sivanesan, Adsorption behavior of methylene blue dye onto surface modified *Strychnos potatorum* seeds, Env. Prog. Sustain. Energy, 32 (2013) 624–632.
[331] R.R.V. Hemavathy, P.S. Kumar, S. Suganya, V. Swetha, S.J. Varjani, Modelling on the removal of toxic metal ions from aquatic system by different surface modified *Cassia fistula* seeds, Bioresour. Technol., 281 (2019) 1–9.
[332] O.A. Ekpete, M. Horsfall Jr., Preparation and characterization of activated carbon derived from fluted pumpkin stem waste (*Telfairia occidentalis* Hook F), Res. J. Chem. Sci., 1 (2011) 10–17.
[333] S. Patil, S. Renukdas, N. Patil, Removal of methylene blue, a basic dye from aqueous solution by ad-sorption using teak tree (*Tectona grandis*) bark powder, Int. J. Environ. Sci., 1 (2011) 711–725.
[334] R. Srivastava, D.C. Rupainwar, A comparative evaluation for adsorption of dye on neem bark and mango bark powder, Indian J. Chem. Technol., 18 (2011) 67–75.
[335] E. Gunasundari, P.S. Kumar, Adsorption isotherm, kinetics and thermodynamic analysis of Cu(II) ions onto the dried algal biomass (*Spirulina platensis*), J. Ind. Eng. Chem., 56 (2017) 129–144.

[336] P.R. Yaashikaa, P.S. Kumar, S.J. Varjani, A. Saravanan, Advances in production and application of biochar from lignocellulosic feedstocks for remediation of environmental pollutants, Bioresour. Technol., (2019), doi: 10.1016/j.biortech.2019.122030.

[337] S.K. Kansal, A. Kumari, Potential of *M. oleifera* for the treatment of water and wastewater, Chem. Rev., 114 (2014) 4993–5010.

[338] A. Hashem, R.A. Akasha, A. Ghith, D.A. Hussein, Adsorbent based on agri-cultural wastes for heavy metal and dye removal: a review, Energy Educ. Sci. Technol., 19 (2007) 69–86.

[339] M. Balat, Mechanisms of thermochemical biomass conversion processes, Energy Sources Part A, 30 (2010) 649–659.

[340] R.A. Young, Structure, Swelling and Bonding of Cellulose Fibers, in: Cellulose: Structure, Modification, and Hydrolysis, Wiley and Sons, New York, 1986, pp. 91–128.

[341] H.L. Hergert, E.K. Pye, Recent History of Organo Solv Pulping, in: Tappi Notes-Solvent Pulping Symposium, 1992, pp, 9–26.

[342] G.I. Mantanis, R.A. Young, R.M. Rowell, Swelling of compressed cellulose fiber webs in organic liquids, Cellulose, 2 (1995) 1–22.

[343] R. Garcia-Valls, T.A. Hatton, Metal ion complexation with lignin derivatives, Chem. Eng. J., 94 (2003) 99–105.

[344] D. Mohan, C.U. Pittman J., P.H. Steele, Pyrolysis of wood/biomass for bio-oil: a critical review, Energy Fuels, 20 (2006) 848–889.

[345] P.S. Kumar, R.V. Abhinaya, K.G. Lashmi, V. Arthi, R. Pavithra, V. Sathyaselvabala, S.D. Kirupha, S. Sivanesan, Adsorption of methylene blue dye from aqueous solution by agricultural waste: equilibrium, thermodynamics, kinetics, mechanism and process design, Colloid J., 73 (2011) 651–661.

[346] M.H. Liu, S.N. Hong, J.H. Huang, H.Y. Zhan, Adsorption/desorption behavior between a novel amphoteric granular lignin adsorbent and reactive red K-3B in aqueous solutions, J. Environ. Sci., 17 (2005) 212–214.

[347] M.H. Liu, J.H. Huang, Removal and recovery of cationic dyes from aqueous solutions using spherical sulfonic lignin adsorbent, J. Appl. Polym. Sci., 101 (2006) 2284–2291.

[348] P.J.M. Suhas, M.M.L. Ribeiro, Lignin from natural adsorbent to activated carbon: a review, Bioresour. Technol., 98 (2007) 2301–2312.

[349] P.S. Kumar, R. Sivaranjanee, U. Vinothini, M. Raghavi, K. Rajasekar, K. Ramakrishnan, Adsorption of dye onto raw and surface modified tamarind seeds: isotherms, process design, kinetics and mechanism, Desal. Wat. Treat., 52 (2014) 2620–2633.

[350] A.B. Albadarin, M.N. Collins, M. Naushad, S. Shirazian, G. Walker, C. Mangwandi, Activated lignin-chitosan extruded blends for efficient adsorption of methylene blue, Chem. Eng. J., 307 (2017) 264–272.

[351] S.Y.H. Zhang, P. Dubey, J.L. Margrave, S.S. Shukla, The role of sawdust in the removal of unwanted materials from water, J. Hazard. Mater., 95 (2002) 137–152.

[352] Y.S. Ho, G. McKay, Kinetic models for the sorption of dye from aqueous solution by wood, Process. Saf. Environ. Prot., 76 (1998) 183–191.

[353] V.K. Garg, M. Amita, R. Kumar, R. Gupta, Basic dye (methylene blue) removal from simulated wastewater by adsorption using Indian Rosewood sawdust: a timber industry waste, Dyes Pigm., 63 (2004) 243–250.

[354] M. Ozacar, I.A. Sengil, Adsorption of metal complex dyes from aqueous solutions by pine sawdust, Bioresour. Technol., 96 (2005) 791–795.

[355] S.D. Khattri, M.K. Singh, Colour removal from synthetic dye wastewater using a bioadsorbent, Water Air Soil Pollut., 120 (2000) 283–294.

[356] V.K. Garg, R. Gupta, A. Bala-Yadav, R. Kumar, Dye removal from aqueous solution by adsorption on treated sawdust, Bioresour. Technol., 89 (2003) 121–124.

[357] F.A. Batzias, D.K. Sidiras, Dye adsorption by calcium chloride treated beech sawdust in batch and fixed-bed systems, J. Hazard. Mater., 114 (2004) 167–174.

[358] S. Suganya, P.S. Kumar, A. Saravanan, P.S. Rajan, C. Ravikumar, Computation of adsorption parameters for the removal of dye from wastewater by microwave assisted sawdust: theoretical and experimental analysis, Environ. Toxicol. Pharmacol., 50 (2017) 45–57.

[359] F.A. Batzias, D.K. Sidiras, Dye adsorption by prehydrolysed beech sawdust in batch and fixed-bed systems, Bioresour. Technol., 98 (2007) 1208–1217.

[360] A.E. Ofomaja, Y.S. Ho, Effect of temperatures and pH on methyl violet biosorption by Mansonia wood sawdust, Bioresour. Technol., 99 (2008) 5411–5417.

[361] V.S. Mane, P.V. Vijay Babu, Studies on the adsorption of Brilliant Green dye from aqueous solution onto low-cost NaOH treated saw dust, Desalination, 273 (2011) 321–329.

[362] L. Sun, D. Chen, S. Wan, Z. Yu, Performance, kinetics, and equilibrium of methylene blue adsorption on biochar derived from eucalyptus saw dust modified with citric, tartaric, and acetic acids, Bioresour. Technol., 198 (2015) 300–308.

[363] S. Agarwal, I. Tyagi, V.K. Gupta, N. Ghasemi, M. Shahivand, M. Ghasemi, Kinetics, equilibrium studies and thermodynamics of methylene blue adsorption on *Ephedra strobilacea* saw dust and modified using phosphoric acid and zinc chloride, J. Mol. Liq., 218 (2016) 208–218.

[364] P.T. Williams, N. Nugranad, Comparison of products from the pyrolysis and catalytic pyrolysis of rice husks, Energy, 25 (2000) 493–513.

[365] K. Mohanty, J.T. Naidu, B.C. Meikap, M.N. Biswas, Removal of crystal violet from wastewater by activated carbons prepared from rice husk, Ind. Eng. Chem. Res., 45 (2006) 5165–5171.

[366] S. Chakraborty, S. Chowdhury, P.D. Saha, Adsorption of Crystal Violet from aqueous solution onto NaOH-modified rice husk, Carbohydr. Polym., 84 (2011) 1533–1541.

[367] G. McKay, J.F. Porter, G.R. Prasad, The removal of dye colours from aqueous solutions by adsorption on low-cost materials, Water Air Soil Pollut., 114 (1999) 423–438.

[368] D. Kalderis, S. Bethanis, P. Paraskeva, E. Diamadopoulos, Production of activated carbon from bagasse and rice husk by a single-stage chemical activation method at low retention times, Bioresour. Technol., 99 (2008) 6809–6816.

[369] P.S. Kumar, K. Ramakrishnan, S.D. Kirupha, S. Sivanesan, Thermodynamic and kinetic studies of cadmium adsorption from aqueous solution onto rice husk, Braz. J. Chem. Eng., 27 (2010) 347–355.

[370] C. Ravikumar, P.S. Kumar, S.K. Subhashni, P.V. Tejaswini, V. Varshini, Microwave assisted fast pyrolysis of corn cob, corn stover, saw dust and rice straw: experimental investigation on bio-oil yield and high heating values, Sustainable Mater. Technol., 11 (2017) 19–27.

[371] Y. Safa, H.N. Bhatti, Biosorption of Direct Red-31 and Direct Orange-26 dyes by rice husk: application of factorial design analysis, Chem. Eng. Res. Des., 89 (2011) 2566–2574.

[372] F. Adam, L. Muniandy, R. Thankappan, Ceria and titania incorporated silica based catalyst prepared from rice husk: adsorption and photocatalytic studies of methylene blue, J. Colloid Interface Sci., 406 (2011) 209–216.

[373] L. Lin, S.-R. Zhai, Z.-Y. Xiao, Y. Song, Q.-D. An, X.-W. Song, Dye adsorption of mesoporous activated carbons produced from NaOH-pretreated rice husks, Bioresour. Technol., 136 (2013) 437–443.

[374] M.P. Tavlieva, S.D. Genieva, V.G. Georgieva, L.T. Vlaev, Kinetic study of brilliant green adsorption from aqueous solution onto white rice husk ash, J. Colloid Interface Sci., 409 (2013) 112–122.

[375] L. Ding, B. Zou, W. Gao, Q. Liu, Z. Wang, Y. Guo, X. Wang, Y. Liu, Adsorption of Rhodamine-B from aqueous solution using treated rice husk-based activated carbon, Colloids Surf. A, 446 (2014) 1–7.

[376] L. Leng, X. Yuan, G. Zeng, J. Shao, X. Chen, Z. Wu, H. Wang, X. Peng, Surface characterization of rice husk bio-char produced by liquefaction and application for cationic dye (Malachite green) adsorption, Fuel, 155 (2015) 77–85.

[377] G.M.K. Tolba, N.A.M. Barakat, A.M. Bastaweesy, E.A. Ashour, W. Abdelmoez, M.H. El-Newehy, S.S. Al-Deyab, H.Y. Kim,

Effective and highly recyclable nanosilica produced from the rice husk for effective removal of organic dyes, J. Ind. Eng. Chem., 29 (2015) 134–145.

[378] A. Masoumi, K. Hemmati, M. Ghaemy, Low-cost nanoparticles sorbent from modified rice husk and a copolymer for efficient removal of Pb(II) and crystal violet from water, Chemosphere, 146 (2016) 253–262.

[379] S. Chanda, Y. Baravalia, M. Kaneria, K. Rakholiya, Fruit and Vegetable Peels – Strong Natural Source of Antimicrobics, FORMATEX, Badajoz, Spain, 2010, pp. 444–450.

[380] C. Namasivayam, N. Muniasamy, K. Gayatri, M. Rani, K. Ranganathan, Removal of dyes from aqueous solutions by cellulosic waste orange peel, Bioresour. Technol., 57 (1996) 37–43.

[381] R. Sivaraj, C. Namasivayam, K. Kadirvelu, Orange peel as an adsorbent in the removal of acid violet 17 (acid dye) from aqueous solutions, Waste Manage., 21 (2001) 105–110.

[382] C. Namasivayam, R.T. Yamuna, J. Jayanthi, Removal of methylene blue from wastewater by adsorption on cellulosic waste, orange peel, Cellulose Chem. Technol., 37 (2003) 333–339.

[383] M. Arami, N.Y. Limaee, N.M. Mahmoodi, N.S. Tabrizi, Removal of dyes from colored textile wastewater by orange peel adsorbent: equilibrium and kinetic studies, J. Colloid Interface Sci., 288 (2005) 371–376.

[384] F.D. Ardejani, K. Badii, N.Y. Limaee, N.M. Mahmoodi, M. Arami, S.Z. Shafaei, A.R. Mirhabibi, Numerical modelling and laboratory studies on the removal of Direct Red 23 and Direct Red 80 dyes from textile effluents using orange peel, a low-cost adsorbent, Dyes Pigm., 73 (2007) 178–185.

[385] A. Khaled, A. El Nemr, A. El-Sikaily, O. Abdelwahab, Treatment of artificial textile dye effluent containing Direct Yellow 12 by orange peel carbon, Desalination, 238 (2009) 210–232.

[386] A.E. Nemr, O. Abdelwahab, A. El-Sikaily, A. Khaled, Removal of direct blue-86 from aqueous solution by new activated carbon developed from orange peel, J. Hazard. Mater., 161 (2009) 102–110.

[387] J. Liang, J. Wu, P. Li, X.Wang, B. Yang, Shaddock peel as a novel low-cost adsorbent for removal of methylene blue from dye wastewater, Desal. Wat. Treat., 39 (2012) 70–75.

[388] S.X. Hou, Adsorption properties of pomelo peels against methylene blue in dye wastewater, Adv. Mater. Res., 634–638 (2013) 178–181.

[389] M.R. Mafra, L. Igarashi-Mafra, D.R. Zuim, E.C. Vasques, M.A. Ferreira, Adsorption of remazol brilliant blue on an orange peel adsorbent, Brazil. J. Chem. Eng., 30 (2013) 657–665.

[390] GEd. Nascimento, M.M.M.B. Duarte, N.F. Campos, C.M.B.D.M. Barbosa, V.L.D. Silva, Adorption of the reactive gray BF-2R dye on orange peel: kinetics and equilibrium studies, Desal. Wat. Treat., 52 (2013) 1578–1588.

[391] M.E. Argun, D. Guclu, M. Karatas, Adsorption of Reactive Blue 114 dye by using a new adsorbent: Pomelo peel, J. Ind. Eng. Chem., 20 (2014) 1079–1084.

[392] A. Asfaram, M.R. Fathi, S. Khodadoust, M. Naraki, Removal of Direct Red 12B by garlic peel as a cheap adsorbent: kinetics, thermodynamic and equilibrium isotherms study of removal, Spectrochim. Acta A. Mol. Biomol. Spectrosc., 127 (2014) 415–421.

[393] O.S. Bello, M.A. Ahmad, B. Semire, Scavenging malachite green dye from aqueous solutions using pomelo (*Citrus grandis*) peels: kinetic, equilibrium and thermodynamic studies, Desal. Wat. Treat., 56 (2015) 521–535.

[394] M.E. Fernandez, G.V. Nunell, P.R. Bonelli, A.L. Cukierman, Activated carbon developed from orange peels: batch and dynamic competitive adsorption of basic dyes, Ind. Crops Prod., 62 (2014) 437–445.

[395] B.O. Isiuk, M. Horsfall, A.I. Spiff, Removal of methyl red from aqueous solution by NaOH-activated cassava peels carbon in a fixed-bed column, Res. J. Appl. Sci., 9 (2014) 238–243.

[396] S.-W. Liew, S.-T. Ong, Removal of basic blue 3 dye using pomelo peel, Asian J. Chem., 26 (2014) 3808–3814.

[397] L.D. Luo, H.Y. Huang, J.H. Bi, L.L. Tan, H. Zhang, D. Zhang, Optimization of malachite green by KOH-modified grapefruit peel activated carbon: application of response surface methodology, Appl. Mech. Mater., 529 (2014) 611–615.

[398] R. Lafi, S. Rezma, A. Hafiane, Removal of toluidine blue from aqueous solution using orange peel waste (OPW), Desal. Wat. Treat., 56 (2015) 2754–2765.

[399] G. Annadurai, R. Juang, D. Lee, Use of cellulose-based wastes for adsorption of dyes from aqueous solutions, J. Hazard. Mater., 92 (2002) 263–274.

[400] S. Banerjee, M.G. Dastidar, Use of jute processing wastes for treatment of wastewater contaminated with dye and other organics, Bioresour. Technol., 96 (2005) 1919–1928.

[401] K.G. Bhattacharyya, A. Sharma, Kinetics and thermodynamics of methylene blue adsorption on Neem (*Azadirachta indica*) leaf powder, Dyes Pigm., 65 (2005) 51–59.

[402] Z. Aksu, I.A. Isoglu, Use of agricultural waste sugar beet pulp for the removal of Gemazol turquoise blue-G reactive dye from aqueous solution, J. Hazard. Mater., 137 (2006) 418–430.

[403] Y. Bulut, H.A. Aydin, Kinetics and thermodynamics study of methylene blue adsorption on wheat shells, Desalination, 194 (2006) 259–267.

[404] K.V. Kumar, K. Porkodi, Mass transfer, kinetics and equilibrium studies for the biosorption of methylene blue using *Paspalum notatum*, J. Hazard. Mater., 146 (2007) 214–226.

[405] M. Dogan, H. Abak, M. Alkan, Biosorption of methylene blue from aqueous solutions by hazelnut shells: equilibrium, parameters and isotherms, Water Air Soil Pollut., 192 (2008) 141–153.

[406] N.A. Oladoja, I.O. Asia, C.O. Aboluwoye, Y.B. Oladimeji, A.O. Ashogbon, Studies on the sorption of basic dye by rubber (*Hevea brasiliensis*) seed shell, Turk. J. Eng. Environ. Sci., 32 (2008) 143–152.

[407] L.S. Oliveira, A.S. Franca, T.M. Alves, S.D.F. Rocha, Evaluation of untreated coffee husks as potential biosorbents for treatment of dye contaminated waters, J. Hazard. Mater., 155 (2008) 507–512.

[408] V. Ponnusami, S. Vikram, S.N. Srivastava, Guava (*Psidium guajava*) leaf powder: novel adsorbent for removal of methylene blue from aqueous solutions, J. Hazard. Mater., 152 (2008) 276–286.

[409] F. Batzias, D. Sidiras, E. Schroeder, C. Weber, Simulation of dye adsorption on hydrolyzed wheat straw in batch and fixed-bed systems, Chem. Eng. J., 148 (2009) 459–472.

[410] B.H. Hameed, Removal of cationic dye from aqueous solution using jackfruit peel as non-conventional low-cost adsorbent, J. Hazard. Mater., 162 (2009) 344–350.

[411] S.D. Gisi, G. Lofrano, M. Grassi, M. Notarnicola, Characteristics and adsorption capacities of low-cost sorbents for wastewater treatment: a review, Sustain. Mater. Technol., 9 (2016) 10–40.

[412] A. Bhatnagar, M. Sillanpaa, Utilization of agro-industrial and municipal waste materials as potential adsorbents for water treatment - a review, Chem. Eng. J., 157 (2010) 277–296.

[413] A. Bhatnagar, V.J.P. Vilar, C.M.S. Botelho, R.A.R. Boaventura, A review of the use of redmud as adsorbent for the removal of toxic pollutants from water and wastewater, Environ. Technol., 32 (2011) 231–249.

[414] V.K. Gupta, S.K. Srivastava, D. Mohan, Equilibrium uptake, sorption dynamics, process optimization, and column operations for the removal and recovery of malachite green from wastewater using activated carbon and activated slag, Ind. Eng. Chem. Res., 36 (1997) 2207–2218.

[415] A.K. Jain, V.K. Gupta, A. Bhatnagar, M. Suhas, Utilization of industrial waste products as adsorbents for the removal of dyes, J. Hazard. Mater., 101 (2003) 31–42.

[416] P. Janos, H. Buchtova, M. Ryznarova, Sorption of dyes from aqueous solutions onto fly ash, Water Res., 37 (2003) 4938–4944.

[417] K. Okada, N. Yamamoto, Y. Kameshima, A. Yasumori, Adsorption properties of activated carbon fromwaste newspaper prepared by chemical and physical activation, J. Colloid Interface Sci., 262 (2003) 194–199.

[418] S. Wang, Y. Boyjoo, A. Choueib, Z.H. Zhu, Removal of dyes from aqueous solution using fly ash and red mud, Water Res., 39 (2005) 129–138.

[419] S. Wang, L. Li, H. Wu, Z.H. Zhu, Unburned carbon as a low-cost adsorbent for treatment of methylene blue-containing wastewater, J. Colloid Interface Sci., 292 (2005) 336–343.

[420] A. Tor, Y. Cengeloglu, Removal of congo red from aqueous solution by adsorption onto acid activated red mud, J. Hazard. Mater., 138 (2006) 409–415.

[421] J.X. Lin, S.L. Zhan, M.H. Fang, X.Q. Qian, H.Yang, Adsorption of basic dye from aqueous solution onto fly ash, J. Environ. Manage., 87 (2008) 193–200.

[422] W.-T. Tsai, H.-C. Hsu, T.-Y. Su, K.-Y. Lin, C.-M. Lin, Removal of basic dye (methylene blue) from wastewaters utilizing beer brewery waste, J. Hazard. Mater., 154 (2008) 73–78.

[423] Q. Wang, Z. Luan, N. Wei, J. Li, C. Liu, The color removal of dye wastewater by magnesium chloride/red mud (MRM) from aqueous solution, J. Hazard. Mater., 170 (2009) 690–698.

[424] P. Pengthamkeerati, T. Satapanajaru, N. Chatsatapattayakul, P. Chairattanamanokorn, N. Sananwai, Alkaline treatment of biomass fly ash for reactive dye removal from aqueous solution, Desalination, 261 (2010) 34–40.

[425] D. Sun, X. Zhang, Y. Wu, X. Liu, Adsorption of anionic dyes from aqueous solution on fly ash, J. Hazard. Mater., 181 (2010) 335–342.

[426] G. Atun, G. Hisarl, A.E. Kurtoglu, N. Ayar, A comparison of basic dye adsorption onto zeolitic materials synthesized from fly ash, J. Hazard. Mater., 187 (2011) 562–573.

[427] P. Hareesh, K.B. Babitha, S. Shukla, Processing fly ash stabilized hydrogen titanate nano-sheets for industrial dye-removal application, J. Hazard. Mater., 229–230 (2012) 177–182.

[428] S. Banerjee, G.C. Sharma, M.C. Chattopadhyaya, Y.C. Sharma, Kinetic and equilibrium modeling for the adsorptive removal of methylene blue from aqueous solutions on of activated fly ash (AFSH), J. Environ. Chem. Eng., 2 (2014) 1870–1880.

[429] C. Jarusiripot, Removal of reactive dye by adsorption over chemical pretreatment coal based bottom ash, Procedia Chem., 9 (2014) 121–130.

[430] M. Shirzad-Siboni, S.J. Jafari, O. Giahi, I. Kim, S.M. Lee, J.K. Yang, Removal of acid blue 113 and reactive black 5 dye from aqueous solutions by activated red mud, J. Ind. Eng. Chem., 20 (2014) 1432–1437.

[431] M. Visa, A.-M. Chelaru, Hydrothermally modified fly ash for heavy metals and dyes removal in advanced wastewater treatment, Appl. Surf. Sci., 303 (2014) 14–22.

[432] A. Duta, M. Visa, Simultaneous removal of two industrial dyes by adsorption and photocatalysis on a fly-ash–TiO_2 composite, J. Photochem. Photobiol. A, 306 (2015) 21–30.

[433] V. Tharaneedhar, P.S. Kumar, A. Saravanan, C. Ravikumar, V. Jaikumar, Prediction and interpretation of adsorption parameters for the sequestration of methylene blue dye from aqueous solution using microwave assisted corncob activated carbon, Sustain. Mater. Technol., 11 (2017) 1–11.

[434] W. Hajjaji, R.C. Pullar, J.A. Labrincha, F. Rocha, Aqueous Acid Orange 7 dye removal by clay and red mud mixes, Appl. Clay. Sci., 126 (2016) 197–206.

[435] Saakshy, K. Singh, A.B. Gupta, A.K. Sharma, Fly ash as low cost adsorbent for treatment of effluent of handmade paper industry-kinetic and modelling studies for direct black dye, J. Cleaner Prod., 112 (2016) 1227–1240.

[436] W. Cherdcho, S. Nithettham, J. Charoenpanich, Removal of Cr(VI) from synthetic wastewater by adsorption onto coffee ground and mixed waste tea, Chemosphere, 221 (2019) 758–767.

[437] Z. Jiang, D. Hu, Molecular mechanism of anionic dyes adsorption on cationized rice husk cellulose from agricultural wastes, J. Mol. Liq., 276 (2019)105–114.

[438] S. Hashemian, K. Salari, Z.A. Yazdi, Preparation of activated carbon from agricultural wastes (almond shell and orange peel) for adsorption of 2-pic from aqueous solution, J. Ind. Eng. Chem., 20 (2014) 1892–1900.

[439] N. Tahir, H.N. Bhatti, M. Iqbal, S. Noreen, Biopolymers composites with peanut hull waste biomass and application for Crystal Violet adsorption, Int. J. Bio. Macromol., 94 (2017) 210–220.

[440] D. Tian, Z. Xu, D. Zhang, W. Chen, J. Cai, H. Deng, Z. Sun, Y. Zhou, Micro–mesoporous carbon from cotton waste activated by $FeCl_3/ZnCl_2$: preparation, optimization, characterization and adsorption of methylene blue and eriochrome black T, J. Solid State Chem., 269 (2019) 580–587.

[441] A.L. Denardin da rosa, E. Carissimi, G.L. Dotto, H. Sander, L.A. Feris, Biosorption of Rhodamine B dye from dyeing stones effluents using the green microalgae *Chlorella pyrenoidosa*, J. Cleaner Prod., 198 (2018) 1302–1310.

[442] R. Dallel, A. Kesraoui, M. Seffeh, Biosorption of cationic dye onto "*Phragmites australis*" fibers: characterization and mechanism, J. Environ. Chem. Eng., 6 (2018) 7247–7256.

[443] D. tomato, F.C. Drumm, P. Grassi, J. Georgin, A.E. Gerhardt, G.L. Dotto, M.A. Mazutti, Residual biomass of *Nigrospora* sp, from process of the microbial oil extraction for the biosorption of procion red H-E7B dye, J. Water Process Eng., 31 (2019) 100818.

[444] P.T. Juchen, H.H. Piffer, M.T, Veit, G. Goncalves, S.M. Palacio, J.C. Zanette, Biosorption of reactive blue BF-5G dye by malt bagasse: kinetic and equilibrium studies, J. Environ. Chem. Eng., 6 (2018) 7111–7118.

[445] T.A. Nguyen, C.C. fu, R.S. Juang, Biosorption and biodegradation of a sulphur dye in high-strength dyeing wastewater by *Acidithiobacillus thioxidans*, J. Environ. Manage., 182 (2016) 265–271.

[446] H.D. Bouras, A.R. Yeddou, N. Bouras, D. Hellel, M.D. Holtz, N. Sabaou, A. Chergui, B. Nadjemi, Biosorption of Congo red dye by *Aspergillus carbonsrius* M333 and *Penicillium glabrum* Pg1: kinetics, equilibrium and thermodynamic studies, J. Taiwan Inst. Chem. Eng., 80 (2017) 915–923.

[447] N. Mokhtar, E.A. Aziz, A. Aris, W.F.W. Ishak, N.S. Mohd Ali, Biosorption of azo-dye using marine macro alga of *Euchema spinosum*, J. Environ. Chem. Eng., 5 (2017) 5721–5731.

[448] S. Mona, A. Kaushik, C.P. Laushik, Biosorption of reactive dye by waste biomass of *Nostoc linckia*, Ecol. Eng., 37 (2011) 1589–1594.

[449] I.G. Coroniulla, L.M. Barrera, E.C. Urbina, Kinetic, isotherm abnd thermodynamic studies of amaranth dye biosorption from aqueous solution onto water hyacinth leaves, J. Environ. Manage., 152 (2015) 99–108.

[450] M. Daoud, O. Benturki, P. Girods, A. Donnot, S. Fontona, Adsorption ability of activated carbons from *Phoenix dactylifera* rachis and *Ziziphus jujuba* stones for the removal of commercial dye and the treatment of dyestuff wastewater, Microchem. J., 148 (2019) 49–502.